

The effect of potassium iodide (KI) addition to aqueous-based electrolyte (sulfuric acid/H₂ SO₄) for increase the performance of supercapacitor cells

by Rika Taslim

Submission date: 21-Jan-2021 11:39AM (UTC+0700)

Submission ID: 1491243530

File name: 1-s2.0-S2214785320391100-main.pdf (990.83K)

Word count: 2361

Character count: 12874



Contents lists available at ScienceDirect

Materials Today: Proceedings

journal homepage: www.elsevier.com/locate/matpr

The effect of potassium iodide (KI) addition to aqueous-based electrolyte (sulfuric acid/H₂SO₄) for increase the performance of supercapacitor cells

E. Taer^{a,*}, A. Putri^a, R. Farma^a, Awitdrus^a, R. Taslim^b, Apriwandi^a, Agustino^a, D.A. Yusra^a^a Department of Physics, University of Riau, 28293 Simpang Baru, Riau, Indonesia^b Department of Industrial Engineering, State Islamic University of Sultan Syarif Kasim, 28293 Simpang Baru, Riau, Indonesia

ARTICLE INFO

Article history:

Received 4 August 2020

Accepted 17 November 2020

Available online xxxx

Keywords:

Aqueous electrolyte

Potassium iodide

Electrode materials

Specific capacitance

Supercapacitor

ABSTRACT

Potassium iodide (KI) has been added to aqueous-based electrolyte (sulfuric acid/H₂SO₄) has succeeded in showing the pseudo-capacitance properties that can increase the specific capacitance of supercapacitor cells. The carbon electrodes for supercapacitor cell made from bamboo stems. As supporting data, surface morphology and crystallinity of carbon electrodes have also been analyzed by using scanning electron microscopy (SEM) and X-ray diffract (XRD) characterization. Whereas in determining specific capacitance of supercapacitor cells, it was carried out using the cyclic voltammetry (CV) method. The CV test results present the addition of KI 0.05 M in 1 M H₂SO₄ solution has increased the specific capacitance from 159 g⁻¹ to 200F g⁻¹.

© 2020 Elsevier Ltd. All rights reserved.

Selection and peer-review under responsibility of the scientific committee of the 7th International Conference of Advanced Materials Science and Technology 2019.

1. Introduction

Supercapacitors are one of the energy storage devices that support the effectiveness of alternative energy today. Supercapacitors have advantages compared to other storage energy such as low-cost production, high security, long life time, and relatively fast charge/discharge times [1]. The component of the supercapacitor cell affects the energy and power densities of the electrode. Electrodes can be made from activated carbon because it has advantages including high conductivity, large surface area and high energy storage capability [2]. Activated carbon can be produced from biomass materials such as cotton [3] coconut, wood and bamboo [4]. Biomass materials are popular carbon sources because it is cheap, easy to production and has abundant availability in nature. In addition to electrodes, electrolytes also affect the performance of supercapacitor cells. Electrolytes must be able to produce a high charge and be able to enter the pores contained in the electrode to be good in increasing specific capacitance. H₂SO₄ is one of the electrolytes which is good for supercapacitor cell applications, it has a dissociation potential of 1.23 V, conductivity of ± 8/Ω, can

be used at high temperatures of 150 °C and the ion diameter size of 0.26 nm. The ion size of the H₂SO₄ is smaller than other aqueous electrolytes such as KOH and KNO₃. The small ion size of H₂SO₄ allows the number of ions to enter the electrode pores. Electrolytes with the addition of additive materials have been used to increase the value of specific capacitance up to three times [5]. One of the additive materials that can be used as an electrolyte is Potassium iodide (KI). KI is chosen for its relatively cheap price, wide availability and good chemical stability [6]. This study presents the effect of H₂SO₄ and KI + H₂SO₄ electrolytes on the electrochemical properties of supercapacitor cells. The carbon materials derived from bamboo stems are chosen as electrode because possess excellent performance of the larger surface area and higher total pore volume, which provide reaction place and transport channel for the ions in the electrolyte. Furthermore, one stage integrated pyrolysis both carbonization and physical activation and ZnCl₂ impregnation are selected to bamboo stems into activated carbon electrode. Based on this result, the addition of KI 0.05 M in 1 M H₂SO₄ solution has been potential to enhance the performance of supercapacitor electrode.

* Corresponding author.

E-mail address: erman.taer@lecturer.unri.ac.id (E. Taer).

17

<https://doi.org/10.1016/j.matpr.2020.11.447>

2214-7853/© 2020 Elsevier Ltd. All rights reserved.

Selection and peer-review under responsibility of the scientific committee of the 7th International Conference of Advanced Materials Science and Technology 2019.

12

2. Materials and methods

2.1. Preparation of activated carbon electrodes

Activated carbon made from bamboo stem collected in the Riau province. The preparation process activated carbon made from bamboo stem carried out by similar method that has been previous reported [7–10]. The carbon electrode was synthesized by the direct carbonization in N₂ gas atmosphere at a temperature of 600 °C for 2.5 h. The electrolyte provided were 1 M H₂SO₄ and 1 M H₂SO₄ + 0.05 M KI. Mixed electrolytes were prepared by adding 0.05 M KI solution into 1 M H₂SO₄ solution under magnetic stirring at a temperature of 80°C. Based on electrolyte variations, the samples were labeled KF and KFI for activated carbon with H₂SO₄ electrolytes and activated carbon with H₂SO₄ + KI electrolytes, respectively. In detail, the preparation of activated carbon electrodes shown in Fig. 1.

16

2.2. Characterization of carbon electrode

The electrochemical properties of various electrolytes were reviewed using the Cyclic Voltammetry (CV) method. The instrument used is the Physics CV UR Rad-Er 5481 scan rate of 1 mV s⁻¹ and a potential of 1.0 V. The physical properties of activated carbon electrodes also analyzed to support the electrochemical analysis. Several physical properties such as density, microstructure, surface morphology, and chemical content were characterized by using the X-Ray Diffraction, Scanning electron microscopy and Energy Dispersive X-ray.

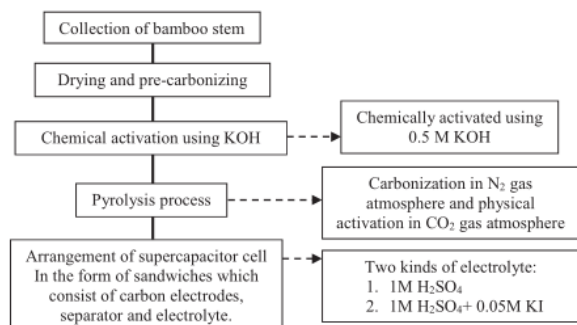


Fig. 1. Schematic diagram for the preparation of activated carbon.

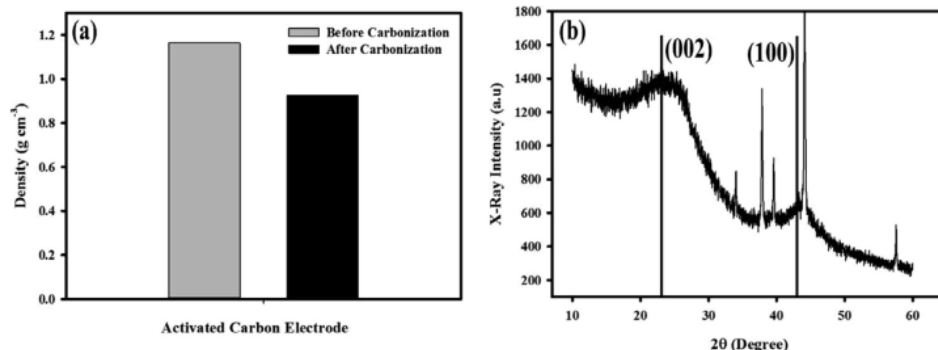


Fig. 2. (a) Density before and after carbonization (b) XRD pattern for KF.

3. Result and discussion

3.1. Physical properties analysis

Activated carbon electrodes before and after the carbonization process measured the density in all samples. In Fig. 2(a) shows the average density of the activated carbon electrode before the carbonization process as high as 1.1644 g m⁻³ is greater than after carbonization process of 0.9234 g m⁻³ it is caused in the carbonization process occurs evaporation of other elements than carbon in samples such as hydrogen, oxygen and other impurities [11], evaporation in the sample results pores so it can affect the mass, thickness and diameter where this affects the density in the sample. The microstructure of the carbon electrode is characterized using XRD which shown in Fig. 2(b). Fig. 2(b) shows a wide peak at 2θ angle in range of 24 and 44, indicating the sample has an amorphous structure. Sharp peaks also seen in Fig. 2(b) indicate the presence of silica (SiO₂) elements that often appear in biomass materials [12].

The surface morphology of activated carbon electrodes is characterized by using SEM method with magnification of 5000x which shown in Fig. 3(a). Fig. 3(a) shows pores formation with average diameter size of 0.811 μm. Pore diameter is measured on the surface of the electrode but needs another method such as TEM to determine the inner pore diameter. The carbonization process increase pore size due to the breakdown of carbon particles forming new particles and expanding existing pores [13,14]. Fig. 3(b) shows the SEM micrograph with a magnification of 40000x. Its exhibit fibres with average diameter of 72.65 nm, indicates the sample has a homogeneous pore area so ion will be easy to diffuse and impact the specific capacitance of the supercapacitor cell. The chemical content analysis of the samples possessed by using energy dispersive spectroscopy (EDS) method. Fig. 3(c) shows the highest peak is found by the carbon element of 93.15%, furthermore there are other elements such as oxygen, silica, potassium and calcium. The appearance of oxygen is due to the carbonization process. Silica elements appear because natural content element in biomass [12], potassium elements arise due to KOH activators during the chemical activation process while calcium elements arise due to natural content in bamboo stem.

3.2. The electrochemical properties analysis

The electrochemical behaviors of KF and KFI samples are initially studied using a two-electrode system, and the CV results are exhibited in Fig. 4. In details, Fig. 4 shows the CV curves of the KF sample with fairly rectangular shape in 1 M H₂SO₄ electrolyte at 1 mV s⁻¹ scan rate, indicating almost ideal feature of electric double layer capacitances (EDLCs) [15]. The large rectangle size

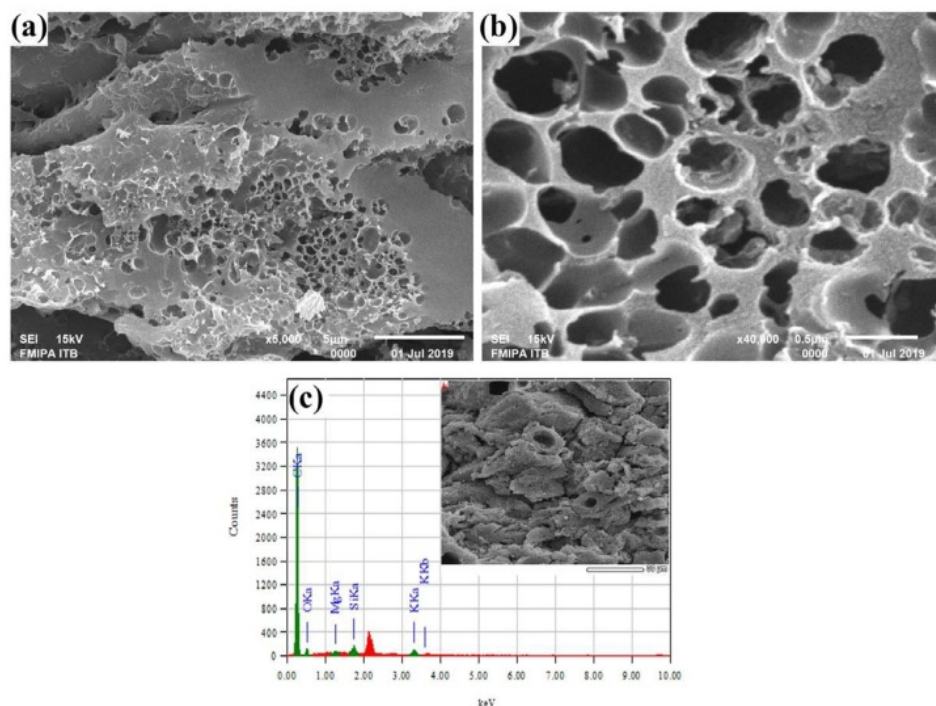


Fig. 3. (a) SEM macrograph of carbon electrode with magnification of 5000x; (b) SEM macrograph of carbon electrode with magnification of 40000x; (c) EDX pattern for carbon electrode of bamboo stem.

indicates the high specific capacitance. KI as a redox additive was tested with 1 M H_2SO_4 exhibit oxidation/reduction peaks in the KFI sample while no peak exists in the KF sample. This added redox peaks provide extra pseudo-capacitances for supercapacitors. KI solutions in electrolytes add to the pseudo-capacitance properties cause H_2SO_4 to synergize in redox reactions [5]. Redox reactions that occur significantly increase specific capacitance, i.e. from 159F g^{-1} for KF samples up to 200F g^{-1} for KFI samples. Based on the results has been analyzed, KI + H_2SO_4 electrolytes have been increased specific capacitance. This work is similar to several other studies which also discuss the effect of KI solution to electrolytes for the performance of supercapacitors [5,6].

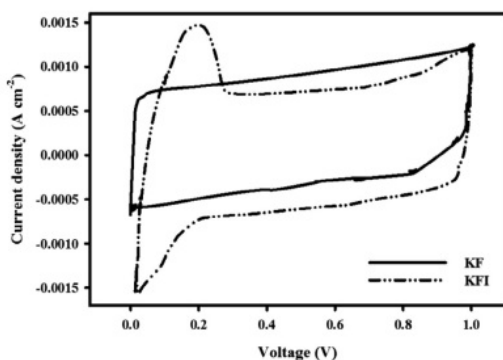


Fig. 4. Cyclic Voltammogram curve of KF and KFI electrodes.

4. Conclusion

The supercapacitor cell has been prepared from bamboo stem based activated carbon in H_2SO_4 and H_2SO_4 + KI as aqueous electrolyte. There exists synergistic effect of 0.05 M KI in 1 M H_2SO_4 electrolyte, which is due to the simultaneous redox reaction of KI solution. This added redox provides extra pseudo-capacitances for supercapacitors which increase specific capacitance from 159F g^{-1} to 200F g^{-1} . The other hands, physical properties of bamboo based activated carbon electrode support the electrochemical properties of H_2SO_4 + KI as aqueous electrolyte.

CRediT authorship contribution statement

E. Taer: Conceptualization, Methodology, Software. **A. Putri:** Writing - original draft. **R. Farma:** Formal analysis, Data curation. **Awitrus:** Validation, Visualization. **R. Taslim:** Visualization, Investigation. **Apriwandi:** Writing - review & editing. **Agustino:** Project administration. **D.A. Yusra:** Investigation, Methodology.

1 Declaration of Competing Interest

The authors declare that they have no known competing financial interests or personal relationships that could have appeared to influence the work reported in this paper.

Acknowledgements

The author would like to thank the DRPM Kemenristek-Dikti through the third year Project of PDUPT with the title "Potential of Urban Solid Waste Utilization as a Supercapacitor Electrode" with contract number: 759/UN.19.5.1.3/PT.01.03/2019.

References

- [1] R. Farma, M. Deraman, A. Awitdrus, I.A. Talib, E. Taer, N.H. Basri, J.G. Manjunatha, M.M. Ishak, B.N.M. Dollah, S.A. Hashmi, Preparation of highly porous binderless activated carbon electrodes from fibres of oil palm empty fruit bunches for application in supercapacitors, *J. Bioresource Technol.* 132 (2013) 254–261.
- [2] J. Hong, W. Xiaomin, G. Zhengrong, P. Joseph, Carbon materials from highashbiochar for supercapacitor and improvement of capacitance with HNO_3 surface oxidation, *J. Power Sourc.* 236 (2013) 285–292.
- [3] Y.J. Kim, B.J. Lee, H. Yohei, N. Goro, O. Shinya, M. Yutaka, Fabrication and electrochemical properties of carbon nanotube film electrodes, *Carbon* 44 (2006) 1963–1968.
- [4] C.-S. Yang, Y.S. Jang, H.K. Jeong, Bamboo-based activated carbon for supercapacitor applications, *Curr. Appl. Phys.* 14 (12) (2014) 1616–1620, <https://doi.org/10.1016/j.cap.2014.09.021>.
- [5] S.T. Senthilkumar, R.K. Selvan, Y.S. Lee, J.S. Melo, Electric double layer capacitor and its improved specific capacitance using redox additive electrolyte, *J. Mater. Chem. A* 1 (2013) 1086–1095.
- [6] D. Xu, W. Hu, X.N. Sun, P. Cui, X.Y. Chen, Redox additives of Na_2MoO_4 and KI: Synergistic effect and the improved capacitive performances for carbon-based supercapacitors, *J. Power Sources* 341 (2017) 448–456, <https://doi.org/10.1016/j.jpowsour.2016.12.031>.
- [7] E. Taer, A. Apriwandi, R. Taslim, U. Malik, Z. Usman, Single step carbonization-activation of durian shells for producing activated carbon monolith electrodes, *Int. J. Electrochem. Sci.* 14 (2019) 1318–1330.
- [8] E. Taer, Apriwandi, Yusriwandi, W.S. Mustika, Zulkifli, R. Taslim, Sugianto, B. Kurniasih, Agustino, P. Dewi. Comparative study of CO_2 and H_2O activation in the synthesis of carbon electrode for supercapacitors. *AIP Conf. Proc.* 1927 (2018) 030036.
- [9] Erman Taer, Rika Taslim, Brief review: Preparation techniques of biomass based activated carbon monolith electrode for supercapacitor applications, *AIP Conf. Proc.* 1927 (2018) 020004.
- [10] E. Taer, A. Afrianda, Apriwandi, R. Taslim, A. Agustino, Awitdrus, R. Farma. Production of activated carbon electrodes from Sago Waste and its application for an electrochemical double-layer capacitor. *Int. J. Electrochem. Sci.*, 13 (2018) 10688–10699.
- [11] Michio Inagaki, Hidetaka Konno, Osamu Tanaike, Carbon materials for electrochemical capacitors, *J. Power Sources* 195 (24) (2010) 7880–7903, <https://doi.org/10.1016/j.jpowsour.2010.06.036>.
- [12] H. Jankowski, A. Swiatkowski, J. Choma, Active Carbon, Ellis Horwood, (1991) London.
- [13] S. Hayashi, A.P. McMahon. 2002. Efficient Recombination in Diverge Tissues by a Tamoxifen-Inducible Form of Cre: A tool for Temporally Regulated Gene Activation/Inactivation in the Mouse, National Conference on Chemical Engineering Science and Application (CHESA), Banda Aceh, Indonesia.
- [14] G. Leofanti, M. Padofan, G. Tozzola, B. Venturelli, Surface area and pore texture of catalysis, *Catal. Today* 41 (1998) 217–219.
- [15] Ander González, Eider Goikolea, Jon Andoni Barrena, Roman Mysyk, Review on supercapacitors: Technologies and materials, *Renew. Sustain. Energy Rev.* 58 (2016) 1189–1206, <https://doi.org/10.1016/j.rser.2015.12.249>.

The effect of potassium iodide (KI) addition to aqueous-based electrolyte (sulfuric acid/H₂ SO₄) for increase the performance of supercapacitor cells

ORIGINALITY REPORT

19%

SIMILARITY INDEX

11%

INTERNET SOURCES

17%

PUBLICATIONS

%

STUDENT PAPERS

PRIMARY SOURCES

1

lume.ufrgs.br

Internet Source

2%

2

electrochemsci.org

Internet Source

2%

3

E Taer, A Agustino, R Farma, R Taslim et al.
"The relationship of surface area to cell capacitance for monolith carbon electrode from biomass materials for supercapacitor application",
Journal of Physics: Conference Series, 2018

Publication

2%

4

www.science.gov

Internet Source

1%

5

Mohammad Hatami, Maryam Hasanpour, Dengwei Jing. "Recent developments of nanoparticles additives to the consumables liquids in internal combustion engines: Part I: Nano-fuels", Journal of Molecular Liquids, 2020

Publication

1%

6

Zhang, You, Lei Zu, Huiqin Lian, Zhongkai Hu, Yanhua Jiang, Yang Liu, Xiaodong Wang, and Xiuguo Cui. "An ultrahigh performance supercapacitors based on simultaneous redox in both electrode and electrolyte", Journal of Alloys and Compounds, 2017.

Publication

1%

7

Hemant Jain, Jaya Tripathi, Ravindra Bharilya, Sanjay Jain, Avinash Kumar. "Optimisation and Evaluation of Machining Parameters for Turning Operation of Inconel-625", Materials Today: Proceedings, 2015

Publication

1%

8

akita-pu.repo.nii.ac.jp

Internet Source

1%

9

researchonline.rca.ac.uk

Internet Source

1%

10

Erman Taer, Martauli Sihombing, Rika Taslim, Agustino, Apriwandi. "Bamboo-Based Activated Carbon as Binder-Free Electrode of Supercapacitor Application", Journal of Physics: Conference Series, 2020

Publication

1%

11

Shengjie Li, Danhui Li, Jianchen Fang, Qiang Liu, Wenjun Cao, Xinghuai Sun, Gezhi Xu. "SARS-CoV-2 receptor ACE2 is expressed in human conjunctival tissue, especially in

1%

diseased conjunctival tissue", Cold Spring Harbor Laboratory, 2020

Publication

12

e-sciencecentral.org

Internet Source

1 %

13

www.ijitee.org

Internet Source

1 %

14

Qingling Wei, Zhimin Chen, Yanyan Cheng, Xiaofeng Wang, Xiaomin Yang, Zichen Wang. "Preparation and electrochemical performance of orange peel based-activated carbons activated by different activators", Colloids and Surfaces A: Physicochemical and Engineering Aspects, 2019

Publication

1 %

15

Wei Hu, Dong Xu, Xiao Na Sun, Zheng Hui Xiao, Xiang Ying Chen, Zhong Jie Zhang. "Template Synthesis of Nitrogen-Doped Carbon Nanosheets for High-Performance Supercapacitors Improved by Redox Additives", ACS Sustainable Chemistry & Engineering, 2017

Publication

1 %

16

Ana I. Zárate-Guzmán, Linda V. González-Gutiérrez, Raúl Ocampo-Pérez, Francisco Carrasco-Marín, Luis A. Romero-Cano. "Iron precursor salt effect on the generation of OH

1 %

radicals and sulfamethoxazole degradation through a heterogeneous Fenton process using Carbon-Fe catalysts", Journal of Water Process Engineering, 2020

Publication

17

rgu-repository.worktribe.com

Internet Source

<1 %

18

Zhang, Zhong Jie, Xuan Huang, and Xiang Ying Chen. "Polyacrylamide-derived carbon materials: outstanding enhancement of supercapacitor capacitance simply by introducing redox additive of p-aminobenzenesulfonate into KOH electrolyte", RSC Advances, 2015.

Publication

<1 %

19

Adekunle Moshood Abioye, Zulkarnain Ahmad Noorden, Farid Nasir Ani. "Synthesis and Characterizations of Electroless Oil Palm Shell Based-Activated Carbon/Nickel Oxide Nanocomposite Electrodes for Supercapacitor Applications", Electrochimica Acta, 2017

Publication

<1 %

20

upcommons.upc.edu

Internet Source

<1 %

21

Enke Feng, Guofu Ma, Kanjun Sun, Feitian Ran, Hui Peng, Ziqiang Lei. "Superior performance of an active electrolyte enhanced supercapacitor

<1 %

based on a toughened porous network gel polymer", New J. Chem., 2017

Publication

22

Xiao-fei Tan, Shao-bo Liu, Yun-guo Liu, Yan-ling Gu, Guang-ming Zeng, Xin-jiang Hu, Xin Wang, Shao-heng Liu, Lu-hua Jiang. "Biochar as potential sustainable precursors for activated carbon production: Multiple applications in environmental protection and energy storage", Bioresource Technology, 2017

Publication

<1 %

23

Zhong, Cheng, Yida Deng, Wenbin Hu, Daoming Sun, Xiaopeng Han, Jinli Qiao, and Jiujun Zhang. "Electrolytes for Electrochemical Supercapacitors", Electrochemical Energy Storage and Conversion, 2016.

Publication

<1 %

24

Nanfei He, Seunghyun Yoo, Jiajia Meng, Ozkan Yildiz, Philip D. Bradford, Sunkyu Park, Wei Gao. "Engineering biorefinery residues from loblolly pine for supercapacitor applications", Carbon, 2017

Publication

<1 %

Exclude quotes On

Exclude matches Off

Exclude bibliography On