

---

**Taslim, Rika ao-2022-04301k - Manuscript Submission to ACS Omega 08-Jul-2022**

1 message

**ACS Omega** <onbehalfof@manuscriptcentral.com>

Fri, Jul 8, 2022 at 11:48 AM

Reply-To: support@services.acs.org

To: rikataslim@gmail.com

Cc: rikataslim@gmail.com, apriwandi95@gmail.com, erman.taer@lecturer.unri.ac.id

08-Jul-2022

Journal: ACS Omega

Manuscript ID: ao-2022-04301k

Title: "Novel &lt;i&gt;Moringa oleifera&lt;/i&gt; leaves 3D porous carbon-based electrode material as high performance EDLC supercapacitor"

Authors: Taslim, Rika; Apriwandi, Apriwandi; Taer, Erman

Manuscript Status: Submitted

Dear Dr. Taslim:

Your manuscript has been successfully submitted to ACS Omega, a multidisciplinary, open access journal for the publication of original and scientifically valid research. The journal offers expedited editorial decision-making and immediate open availability. Authors can rapidly publish their important research results and broadly distribute them to the global scientific community. Please note that there are publishing charges associated with this journal. Details can be found at <http://acsopenscience.org>. Should your manuscript be accepted, you will be required to pay for the Article Publishing Charges prior to publication. Authors may qualify for discounts. Article Publishing Charges are waived for invited Editorials and Perspectives.

Please reference the above manuscript ID in all future correspondence. If there are any changes in your contact information, please log in to ACS Paragon Plus with your ACS ID at <http://acsparagonplus.acs.org/> and select "Edit Your Profile" to update that information.

You can view the status of your manuscript by checking your "Authoring Activity" tab on ACS Paragon Plus after logging in to <http://acsparagonplus.acs.org/>.

**Journal Publishing Agreement and Copyright**

Upon acceptance, ACS Publications will require the corresponding author to sign and submit a Journal Publishing Agreement. This agreement gives authors a number of rights regarding the use of their manuscripts. At acceptance, the corresponding author will receive an email linking through to the Journal Publishing Agreement Wizard, which helps you select the most appropriate license for your manuscript.

For more information please see: [https://pubs.acs.org/page/copyright/journals/jpa\\_faqs.html](https://pubs.acs.org/page/copyright/journals/jpa_faqs.html)

**ACS Authoring Services**

Did you know that ACS provides authoring services to help scientists prepare their manuscripts and communicate their research more effectively? Trained chemists with field-specific expertise are available to edit your manuscript for grammar, spelling, and other language errors, and our figure services can help you increase the visual impact of your research.

Visit <https://authoringservices.acs.org> to see how we can help you! Please note that the use of these services does not guarantee that your manuscript will be accepted for publication.

Thank you for submitting your manuscript to ACS Omega.

Sincerely,

Dr. Krishna Ganesh and Dr. Deqing Zhang  
ACS Omega

-----  
PLEASE NOTE: This email message, including any attachments, contains confidential information related to peer review and is intended solely for the personal use of the recipient(s) named above. No part of this communication or any related attachments may be shared with or disclosed to any third party or organization without the explicit prior written consent of the journal Editor and ACS. If the reader of this message is not the intended recipient or is not responsible for delivering it to the intended recipient, you have received this communication in error. Please notify the sender immediately by e-mail, and delete the original message.

As an author or reviewer for ACS Publications, we may send you communications about related journals, topics or products and services from the American Chemical Society. Please email us at [pubs-comms-unsub@acs.org](mailto:pubs-comms-unsub@acs.org) if you do not want to receive these. Note, you will still receive updates about your manuscripts, reviews, or future invitations to review.

Thank you.

This document is confidential and is proprietary to the American Chemical Society and its authors. Do not copy or disclose without written permission. If you have received this item in error, notify the sender and delete all copies.

**Novel *Moringa oleifera* leaves 3D porous carbon-based electrode material as high performance EDLC supercapacitor**

Journal:	<i>ACS Omega</i>
Manuscript ID	Draft
Manuscript Type:	Article
Date Submitted by the Author:	n/a
Complete List of Authors:	Taslim, Rika; State Islamic University Sultan Syarif Kasim, Department of Industrial Engineering Apriwandi, Apriwandi; University of Riau - Bina Widya Campus, Department of Physics Taer, Erman; Universitas Riau - Kampus Binawidja, Department of physics

SCHOLARONE™  
Manuscripts

# Novel *Moringa oleifera* leaves 3D porous carbon-based electrode material as high performance EDLC supercapacitor

Rika Taslim,<sup>\*[a]</sup> Apriwandi Apriwandi,<sup>[b]</sup> and Erman Taer,<sup>[b]</sup>

<sup>[a]</sup> Department of Industrial Engineering, State Islamic University of Sultan Syarif Kasim, Riau, Simpang Baru-Tampan Pekanbaru, Indonesia

<sup>[b]</sup> Department of Physics, Faculty of Mathematics and Natural Sciences, University of Riau, Panam, Pekanbaru, Indonesia

E-mail: [rikataslim@gmail.com](mailto:rikataslim@gmail.com)

**Abstract.** Biomass-based activated carbon has great potential of versatile 3D porous structures as excellent electrode material in presenting high conductivity, large porosity, and outstanding stability for electrochemical energy storage devices. In this study, the electrode material was developed through a novel consolidated carbon disc binder-free design, which was derived from *Moringa oleifera* leaves (MOLs) for electrochemical double-layer capacitor applications. The carbon discs were prepared in a series of treatments of pre-carbonized, chemical impregnation of zinc chloride, and integrated pyrolysis of N<sub>2</sub> carbonization and CO<sub>2</sub> physical activation. The physical activation temperatures were applied at 650, 750, and 850°C to optimize the precursor potential. By optimizing the 3D hierarchical pore properties of the MOL750, the carbon disc binder-free design demonstrated optimal symmetric supercapacitor performance with a high specific capacitance of 307 F g<sup>-1</sup> at a current density of 1 A g<sup>-1</sup> in an aqueous electrolyte solution of 1 M H<sub>2</sub>SO<sub>4</sub>. Furthermore, the extremely low internal resistance (0.006Ω) of the carbon disc initiated excellent electrical conductivity. The supercapacitors also maintained their high capacitive properties in aqueous electrolyte solutions of 6 M KOH, and 1 M Na<sub>2</sub>SO<sub>4</sub>, respectively. The results showed that a novel consolidated carbon discs binder-free design can be obtained from biomass MOLs through a reasonable approach to develop superior electrode materials to enhance high-performance electrochemical energy storage devices.

## 1. INTRODUCTION

The rapid growth of the world's population with the demands for prosperous life management has made the energy crisis the main global challenge. At the end of 2021, the energy consumption was 4.5% higher than the previous year <sup>1</sup> and is estimated to increase by more than half in the next 4 years <sup>2</sup>. Moreover, approximately 90% of the total energy demand is obtained from coal, which is non-renewable. Studies have shown that the use of coal energy sources causes significant problems in the production of CO<sub>2</sub> emissions and greenhouse gas effects, which leads to global warming and climate change <sup>3</sup>. This makes it necessary to develop effective, efficient, and pollution-free green energy technology and renewable energy conversion

systems. In the past decade, people have focused on abundant, low-cost, safe, and environmentally friendly renewable energy sources such as wind, ocean waves, solar, and biomass. However, their use was limited due to a relatively low supply of technology and complex supporting components. Several developed countries such as China and the United States have implemented renewable energy technologies as alternative sources of energy <sup>4</sup>. This situation led to the development of energy storage systems and devices with high specifications, good stability, low cost, effectiveness, and efficiency to perfect green energy technologies <sup>5,6</sup>. Among the various energy storage technologies investigated, supercapacitors received much attention due to their outstanding power transmission specifications, fast energy storage, infinite cycle stability, high

conductivity, and eco-friendly nature <sup>7,8</sup>. The main key to the superior characteristics of supercapacitor devices is their electrode-based material <sup>9,10</sup>. Various electrode-based materials can produce high and low characteristics of electronic and ionic conductivity. This significantly affects the ability of the electric charge transfusion rate and cyclic resistance of the supercapacitor <sup>11,12</sup>. Therefore, there is a need to design and develop excellent electrode materials for high-performance supercapacitors. In recent years, electrode materials have shown high specifications such as metal oxides, conducting polymers, and carbon materials. The metal oxide materials such as MnO<sub>2</sub>, TiO<sub>2</sub>, and RuO<sub>2</sub> offer high oxidation states for efficient charge transfer during redox reactions, which generate Faradic currents and ion intercalation that favor charge storage, high capacity and conductivity, as well as low toxicity <sup>13–15</sup>. According to Wang *et al.* (2021), the mixed metal oxide material has produced a specific capacitance of 788 F g<sup>-1</sup> with an energy density of 138 Wh kg<sup>-1</sup> <sup>16</sup>. Similar results were also confirmed in polymeric materials that produce high energy density <sup>17</sup>. The polymeric materials allow flexible design, which is considered to be more practical, modern, and generally acceptable. The excessive consumption of metal and high-cost polymeric materials with their complicated production methods, low porosity, and corrosive properties significantly increased the risk of mass production and limit their wider application.

Similarly, carbon materials, especially activated carbon, are of greater concern due to their lower production costs, abundant availability, suitable pore structure, and very high porosity properties <sup>7,18</sup>. The biomass-based activated carbon provides a 3D hierarchical pore structure of a combination of micro, meso, and macropores that enable the electrode material to produce high energy and power densities simultaneously <sup>19,20</sup>. Moreover, the self-doping of N/O/P on carbon-based biomass also confirmed their high advantage <sup>21</sup>. Activated carbon from the leaves of *Parthenium hysterophorus* (biomass) has shown a 3D porous structure with a high surface area of 4014 m<sup>2</sup> g<sup>-1</sup> recently, followed by oxygen self-doping <sup>22</sup>. This characteristic has increased the storage capacity of a symmetric supercapacitor to 270 F g<sup>-1</sup>. The adjustable micro:macropores ratio of activated carbon from pecan shells can also produce an extraordinary specific capacitance of 447 F g<sup>-1</sup> <sup>23</sup> and display high electrochemical properties with a surface area of 1,785 m<sup>2</sup> g<sup>-1</sup>. This showed that the high surface area does not guarantee the high electrochemical

properties of the supercapacitor. Some suspicions of tuning micro-mesopore, heteroatom self-doping, and the natural conductivity of the materials also contribute to the improvement of their electrochemical properties. Similar results were also obtained from other organic-based activated carbon sources such as wood powders <sup>24</sup>, feather finger grass flower <sup>25</sup>, camellia pollen <sup>26</sup>, and peach gum <sup>27</sup>. Meanwhile, the electrode materials of biomass-based activated carbon possessed energy density disproportionately with their power density and electrical/ionic conductivity far from metal oxide materials and conducting polymer due to high porosity, which hinders their practical application. Therefore, it is necessary to design a biomass-based porous carbon with a novel, easy, inexpensive, and approach for environmentally friendly, pollution-free, and high-performance supercapacitors.


Therefore, this study aims to develop a novel electrode material design from *Moringa oleifera* leaves biomass-based consolidated solid carbon discs to increase the storage capacity of symmetric supercapacitor devices. The proposed carbon discs are prepared binder-free, whose treatment consists of pre-carbonization, chemical impregnation (ZnCl<sub>2</sub>), and integrated pyrolysis of N<sub>2</sub> carbonization and physical activation of CO<sub>2</sub>. The potential for activated carbon precursors was also maximized through different pyrolysis temperatures 650, 750, and 850°C. Moreover, the carbon discs of MOLs exhibit 3D hierarchical pore properties with oxygen heteroatoms as their additional oxidative property. The optimized carbon disc exhibits a high specific capacitance of 307 F g<sup>-1</sup> in the 1 M H<sub>2</sub>SO<sub>4</sub> electrolyte. This showed that the proposed design is a reasonable approach to increase the symmetric storage capacity of pollution-free, low-cost, and high-performance supercapacitors.

## 2. RESULTS AND DISCUSSION

### 2.1. Material analysis

Density analysis is an important aspect for the evaluation of carbon MOLs in form of binder-free consolidated discs. This section shows the analysis of changes in the density of the carbon discs of MOLs at different temperatures of pyrolysis treatments. The precursor powder pressed at a predetermined load was properly compacted at a diameter of ±19.00 mm, a thickness of ±2.00 mm, and a mass of ±0.70 gr (see Figure 1a). The potential precursors of the confirmed MOLs formed a strong/resistant and a fracture-free consolidated disc with a smooth surface. Their biological composition and complex compounds can act as

self-adhesives to enable the formation of binder-free strong discs.

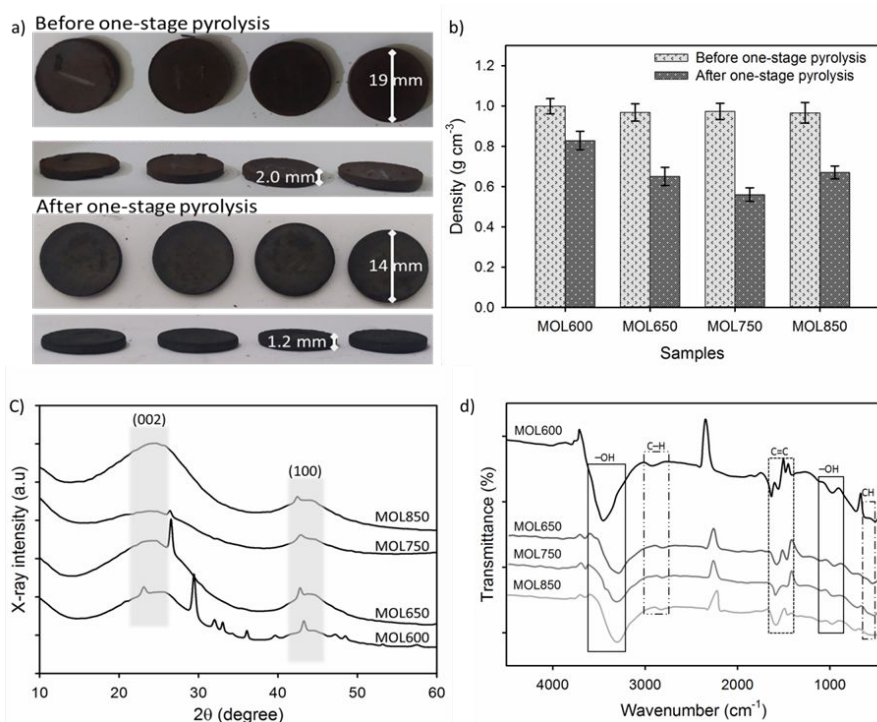

**Figure 1.** a) Dimensions of binder-free consolidated discs before and after pyrolysis, b) Changes in the density of the carbon discs of MOLs at different temperatures of pyrolysis treatments, c) XRD pattern of MOLs disc at different pyrolysis temperatures, and d) FTIR spectrum of the MOLs carbon disc at a wavenumber of 4500-450 cm<sup>-1</sup>.

A similar case was also stated in a previous study using banana leaves as a precursor<sup>28</sup>. In this study, the average densities of the samples MOL600, MOL650, MOL750, and MOL850 were 0.9990, 0.9680, 0.9730, and 0.9660 g cm<sup>-3</sup>, respectively. The discs of consolidated MOLs were pyrolyzed at high temperatures, including carbonization in an N<sub>2</sub> gas environment and physical activation in a CO<sub>2</sub> gas environment and their final process was evaluated for overall dimensional changes. As shown in Figure 1b, the disc density of the consolidated MOLs degraded significantly after the high-temperature pyrolysis process due to a significantly large mass loss. Pyrolysis initiated from 30°C to 850°C for over 10 hours significantly degraded the disc dimensions, where their diameter, thickness, and average mass were reduced to ±14.00mm, ±1.2mm, and 0.2 gr, respectively. After the pyrolysis process, the MOLs disc density decreased to 0.8280, 0.6500, 0.5600, and 0.6700 g cm<sup>-3</sup> for samples MOL600, MOL650, MOL750, and MOL850, respectively.

The evaporation of volatile compounds, water content, and decomposition of the biological composition of the precursor during the chemical reaction of ZnCl<sub>2</sub> at high-pyrolysis temperature caused the reduction of the density of MOLs discs. Furthermore, the physical appearance of the disc

sample is relatively solid black, which indicated a high fixed carbon content. The 42.44% density degradation initiated the formation of a diverse pore framework which is needed as a good electrode material for electrochemical energy storage devices. The different pyrolysis temperatures from 600°C to 750°C affect their respective densities by degrading the MOLs disc density to 32.36%. This is due to the erosion of the carbon framework which causes the expansion of larger pores and initiates the formation of macropores within the micron scale. From the pyrolysis temperature of 750°C to 850°C, the density of the disc increased by 16.41% due to excessive erosion of the carbon pore walls. This makes the carbon skeleton unable to maintain the structure above, thereby, it collapsed and covered the pores below. However, these results are relatively normal for solid carbon samples.

The material structure of the carbon disc MOLs was evaluated through X-ray diffraction (XRD) and Fourier transforms infrared (FTIR) techniques. Figure 1c shows the XRD pattern of disc MOLs at different pyrolysis temperatures of 600, 650, 750, and 850°C. The carbon discs showed strong broad peaks at angles 24° and 44° correlated with the (002) and (100) scattering planes, which confirmed the turbostratic carbon structure (JCPDS No. 29-1126, 29-1127)<sup>29</sup>. The high-temperature pyrolysis

of the precursor MOLs allows the decomposition and rearrangement of the carbon structure to initiate good amorphous behavior<sup>30</sup>.

**Table 1.** Microcrystalline parameters and elemental status of MOLs carbon disc at different physical activation temperature.

Carbon disc MOLs	Microcrystalline parameters				Elemental status				
	$d_{002}$ (Å)	$d_{100}$ (Å)	$L_c$ (Å)	$L_a$ (Å)	C (%)	O (%)	Ca (%)	Cl (%)	Zn (%)
MOL600	3.524	2.077	13.391	22.159	79.45	17.41	2.28	0.87	0.00
MOL650	3.616	2.051	12.297	16.903	85.97	10.49	0.63	0.68	2.24
MOL750	3.698	1.994	7.481	23.866	88.54	8.06	1.11	0.64	1.65
MOL750	3.689	1.993	10.323	18.144	88.91	8.45	1.38	0.60	0.66

Furthermore, the properties of the carbon disc structure of MOLs changed during the high-temperature pyrolysis process including carbonization and physical activation. The hkl (002) plane possesses broad peak attenuation from 600 to 850°C, which significantly reduced the crystalline properties and initiate the formation of abundant micro-mesoporosity<sup>31</sup>. This property improves the electro-active site of the electrode material in energy storage systems. Meanwhile, the sharp peaks in the sample were significantly reduced from 600 to 850°C, indicating the presence of a small amount of crystal structure of the compound CaCO<sub>3</sub> and ZnO at angles of 23°, 26°, 29°, 32°, 36°, and 43°.

These compounds are the contribution of organic precursor components and by-products of their chemical impregnation. The CaCO<sub>3</sub> compound is located at an angle of 23.165°, 29.255°, 32.050°, 36.095° (JCPDS No. 06-0230) and the ZnO compound in very small amounts at 26.05°-26.395° (JCPDF No. 36-1451)<sup>32,33</sup>. The MOLs600 sample that was carbonized at 600°C produced an XRD pattern, containing several CaCO<sub>3</sub> crystalline compounds. The application of physical activation in the CO<sub>2</sub> gas environment reduced the CaCO<sub>3</sub> compounds as shown in MOLs650, MOLs750, and MOLs850, as described EDS technique in Table 1. Moreover, high-temperature pyrolysis obtains carbon discs with a well amorphous structure. Table 1 summarizes the interlayer spacing and microcrystalline dimensions of the MOLs carbon discs at pyrolysis temperatures ranging from 600 to 850°C. The value of  $d_{(002)}$  of MOLs is slightly higher than  $d_{(002)}$  of graphite by approximately 3.46%, while  $d_{(100)}$  indicates a relatively ideal for

amorphous carbon-based biomass as stated in previous studies<sup>34,35</sup>. Furthermore, the microcrystalline dimension ( $L_c$ ) is closely related to the specific surface area and the active channel on the electrode material, which is often related through empirical equations<sup>36,37</sup>. Based on this empirical equation,  $L_c$  showed that the specific surface area inversely, where a low  $L_c$  allows the electrode disc to obtain a high surface area. From Table 1, the carbon discs pyrolyzed at 750°C temperature showed higher surface area than others.


Figure 1d shows the FTIR spectrum of the carbon disc MOLs at a wavenumber of 4500-450 cm<sup>-1</sup>. Generally, different pyrolysis temperatures, namely 600, 650, 750, and 850°C of the MOLs precursors exhibited stretching vibrations of -OH, C-H, C=C, C-O, CH<sub>2</sub>, and C-H aromatics<sup>38,39</sup>. This functional group is considered normal for porous activated carbon based on organic waste. The carbon discs pyrolyzed at 600°C (carbonization only) showed significant absorption at several wavenumbers compared to higher temperatures. Furthermore, the highest absorption was discovered in the band 3,463-3,309 cm<sup>-1</sup> due to stretching vibration of -OH<sup>40</sup>, which was also discovered in wavenumber 1,491-1,422 cm<sup>-1</sup>. Stretching vibration of C-H was indicated at wavenumbers 2,926 cm<sup>-1</sup> and 978 cm<sup>-1</sup>, while 1,652 cm<sup>-1</sup> and 1,553 cm<sup>-1</sup> were the stretching vibrations of C=C. Meanwhile, the absorption band in the range 1,300-1,010 cm<sup>-1</sup> represents the C-O functional group, while CH aromatic is were in the 770-709 cm<sup>-1</sup> and 540-518 cm<sup>-1</sup><sup>41</sup>. The abundance of C and O in this functional group indicates their relatively high content in carbon disc MOLs as shown in Table 1. At higher temperatures, the pyrolysis of

MOL650, MOLs750, and MOL850 integrated with the one-stage carbonization and physical activation process showed relatively different absorption patterns. The stretching vibrations of C-O and -OH decreased significantly at MOL650, MOL750, and MOL850, as shown in the absorption bands of 3,400-3,300  $\text{cm}^{-1}$  and 1,300-1,010  $\text{cm}^{-1}$ . This is due to the physical activation in the  $\text{CO}_2$  gas environment treatment, maximizing the evaporation process of organic compounds and rearranges the carbon framework, thereby, possessing FTIR spectra that are nearly ideal for porous activated carbon. Meanwhile, MOL750 showed the lowest absorption band, followed by the removal of some absorbance, especially on stretching vibration of C-O and CH aromatic<sup>38,41</sup>. This indicated that the FTIR spectra obtained are the most ideal compared to the others. The presence of a relatively confirmed -OH functional group provides wettability and hydrophilicity properties for the electrode material<sup>42,43</sup>. This property is used as a heteroatom to increase the effect of extra pseudo-capacitance in electrochemical energy storage devices. Similar results were also shown by EDS and electrochemical properties analyses.

The energy dispersive spectroscopy (EDS) was carried out at a voltage of 15.0kV within the energy range of 0-20.0 keV to analyze the elements of consolidated carbon discs MOLs that were pyrolyzed at high temperature. Meanwhile, the details elemental status of the carbon disc MOLs is summarized in Table 1. It was shown that carbon (C) is the component of the highest consolidated disc with approximately 79-89% and oxygen (O) heteroatoms 8-17%, followed by other elements in very small amounts such as potassium (Ca), chlorine (Cl), and zinc (Zn). These results are in line with the previously discussed XRD and FTIR analyzes. The carbonization process at 600°C in the  $\text{N}_2$  atmosphere significantly obtained high pure carbon of 79.45%. This

also supported the density analysis where volatile, water content, complex organic compounds evaporated and degraded. However, as a by-product, they still leave oxygen in form of an oxide compound of 17.41%. An increase in the pyrolysis temperature on physical activation using  $\text{CO}_2$  increased the elemental carbon by 88.91% at MOL850, while the elemental oxygen is reduced regularly and remains 8.06% at MOLs750. The element Zn appears because the byproduct of chemical impregnation  $\text{ZnCl}_2$  is not completely evaporated. Meanwhile, the elements Ca and Cl are the contributions of the organic components of the precursor MOLs. The high pure carbon element obtained in the consolidated disc MOLs also allows the electrode material to have high conductivity properties to boost the electrochemical behavior of the supercapacitor<sup>44</sup>. The elemental oxygen can also contribute to self-heteroatom and provide additional pseudo-capacitance to the disc carbon-based electrode material of consolidated MOLs. The morphological structures of the obtained consolidated MOL carbon discs were reviewed by scanning electron microscopy (SEM) as shown in Figure 2. Binder-free carbon discs pyrolyzed using 600-850°C different temperatures exhibited a 3D connected pore-rich surface structure. Precursor MOLs that were impregnated with  $\text{ZnCl}_2$  at 600°C showed a smooth surface with clear micron-scale pore channels. In the selected area, MOL600 maintains the natural pore structure of MOLs at the nano and micro scale. The pores obtained were dominated by mesopores in the 23-46nm range and rich in micropores. Furthermore, the  $\text{ZnCl}_2$  impregnation maximizes the potential of MOLs precursors to provide rich pores through evaporation and gradation of their organic compounds<sup>45</sup>. Figure 2b confirms the mesoporous rich structure in the range of 24 to 49nm and macropores in the 100 nm scale.



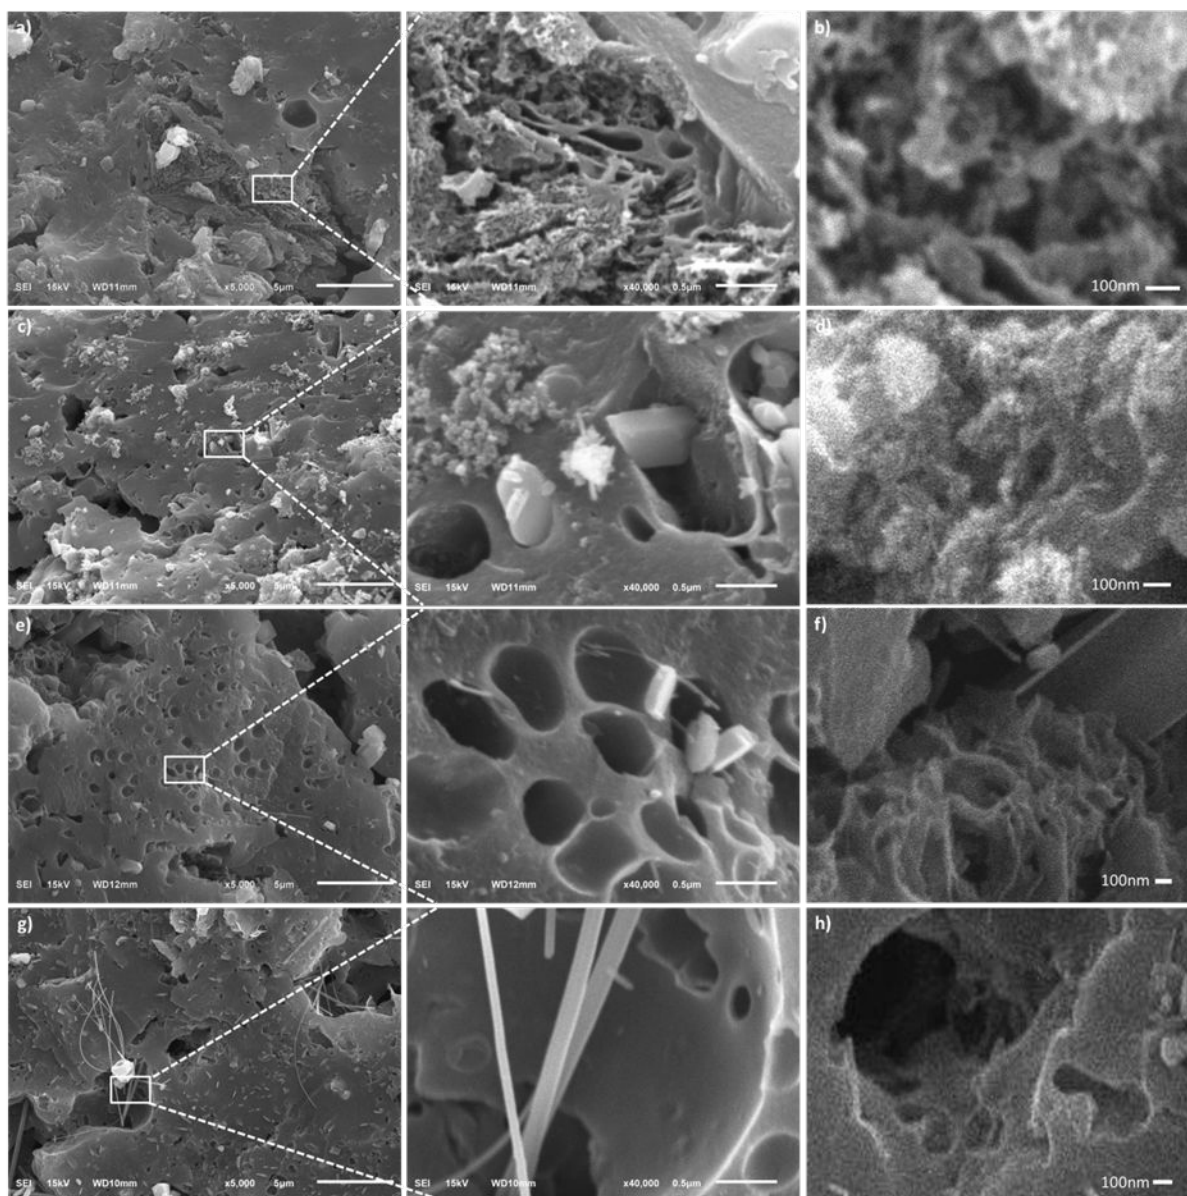


**Figure 2.** SEM image of (a) MOL600, (b) MOL600 at closer zoom, (c) MOL650, (d) MOL650 at closer zoom, (e) MOL750, (f) MOL600 at closer zoom, (g) MOL850, and (h) MOL850 at closer zoom.

This is useful as an electrolyte reservoir in the electrochemistry of supercapacitors<sup>46</sup>. When the pyrolysis temperature was increased to 650°C in the CO<sub>2</sub> physical activation process, the surface structure was decorated with holes in the diameter which ranged from 65 nm to 1,261 nm as shown in Figure 2c. The physical activation of CO<sub>2</sub> significantly grows the rich macropores by grinding the carbon skeleton, which is released in form of CO, H<sub>2</sub>O, and CO<sub>2</sub><sup>47</sup>. Through a closer zoom, SEM micrographs

confirmed the presence of multiple pores connected in 3D hierarchies, where the macropore walls contain mesopores in small numbers. Figure 2d also shows the expansion of the pores towards a larger direction due to high-temperature carbon skeleton grinding compared to Figure 2b. Meanwhile, increasing the pyrolysis temperature to a higher at 750°C allows MOLs750 to have abundant pores as shown in Figure 2e. The various pore structures obtained range from 500-900 nm. Figure 2f


shows morphology 3D carbon foam-like interconnected by thin sheet-like struts and open pores with a diameter of several tens of nanometers.

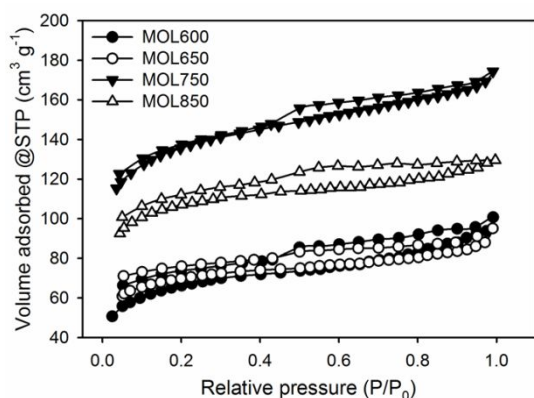


**Figure 3.** N<sub>2</sub> gas adsorption profiles of the MOLs carbon disc.

This pore structure significantly contributes to an increase in the amount of ionic charge transfer and electro-active activity in the MOLs of the electrode material<sup>48</sup>. These morphological properties are expected to cause high capacitive properties with greater energy density and power in symmetric supercapacitor devices. Increasing the pyrolysis temperature to 850°C at MOL850 led to a more severe etching of the carbon matrix, causing considerable pore dilation.

Subsequently, the 3D hierarchical porous structure becomes visible as shown in Figure 2g and their magnification selected area. Moreover, MOL850 exhibits a 2D nanofiber structure at a diameter of approximately 73-188nm, which can lead to the distribution of micropores on their surface. Figure 4h shows the abundant 3D pore morphology connected hierarchically between mesopores and macropores. The analysis showed that increasing the pyrolysis temperature etches the carbon framework giving rise to a 3D porous carbon framework connected to nanoscale 2D nanosheets and nanofibers on MOLs carbon discs. These results indicated that the proposed approach can significantly increase the proportion of hierarchically connected mesopores/macropores in carbon MOLs. Therefore, excellent material properties can be achieved to improve the performance of electrode materials in electrochemical energy storage devices. A more detailed analysis of the pore structure was confirmed through the N<sub>2</sub> adsorption-desorption isotherm characterization. The MOLs carbon discs obtained from the integrated single-stage pyrolysis process at different temperatures of 600-850°C have type N<sub>2</sub> gas adsorption profiles as shown in Figure 3.

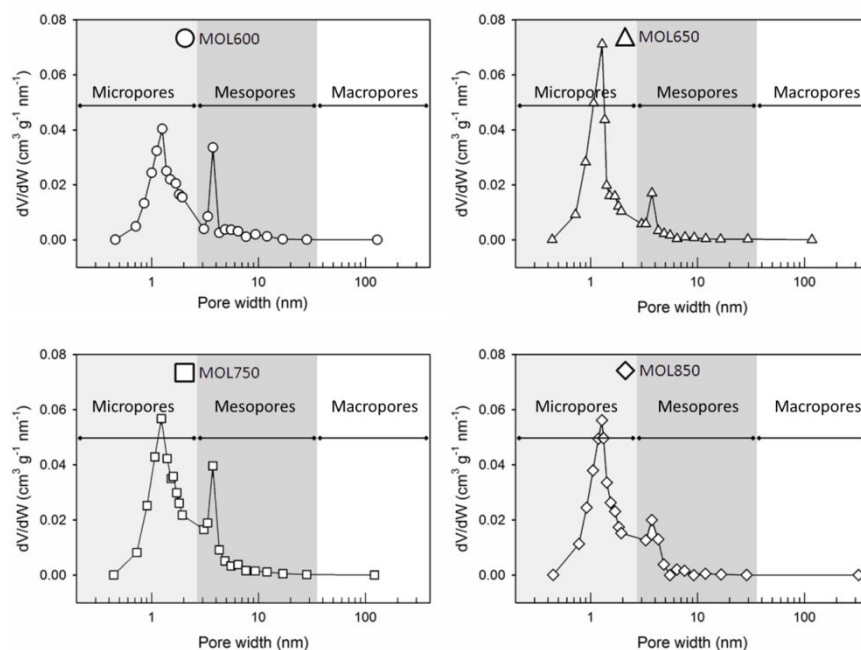

**Figure 4.** Pore size distribution of the MOLs carbon discs

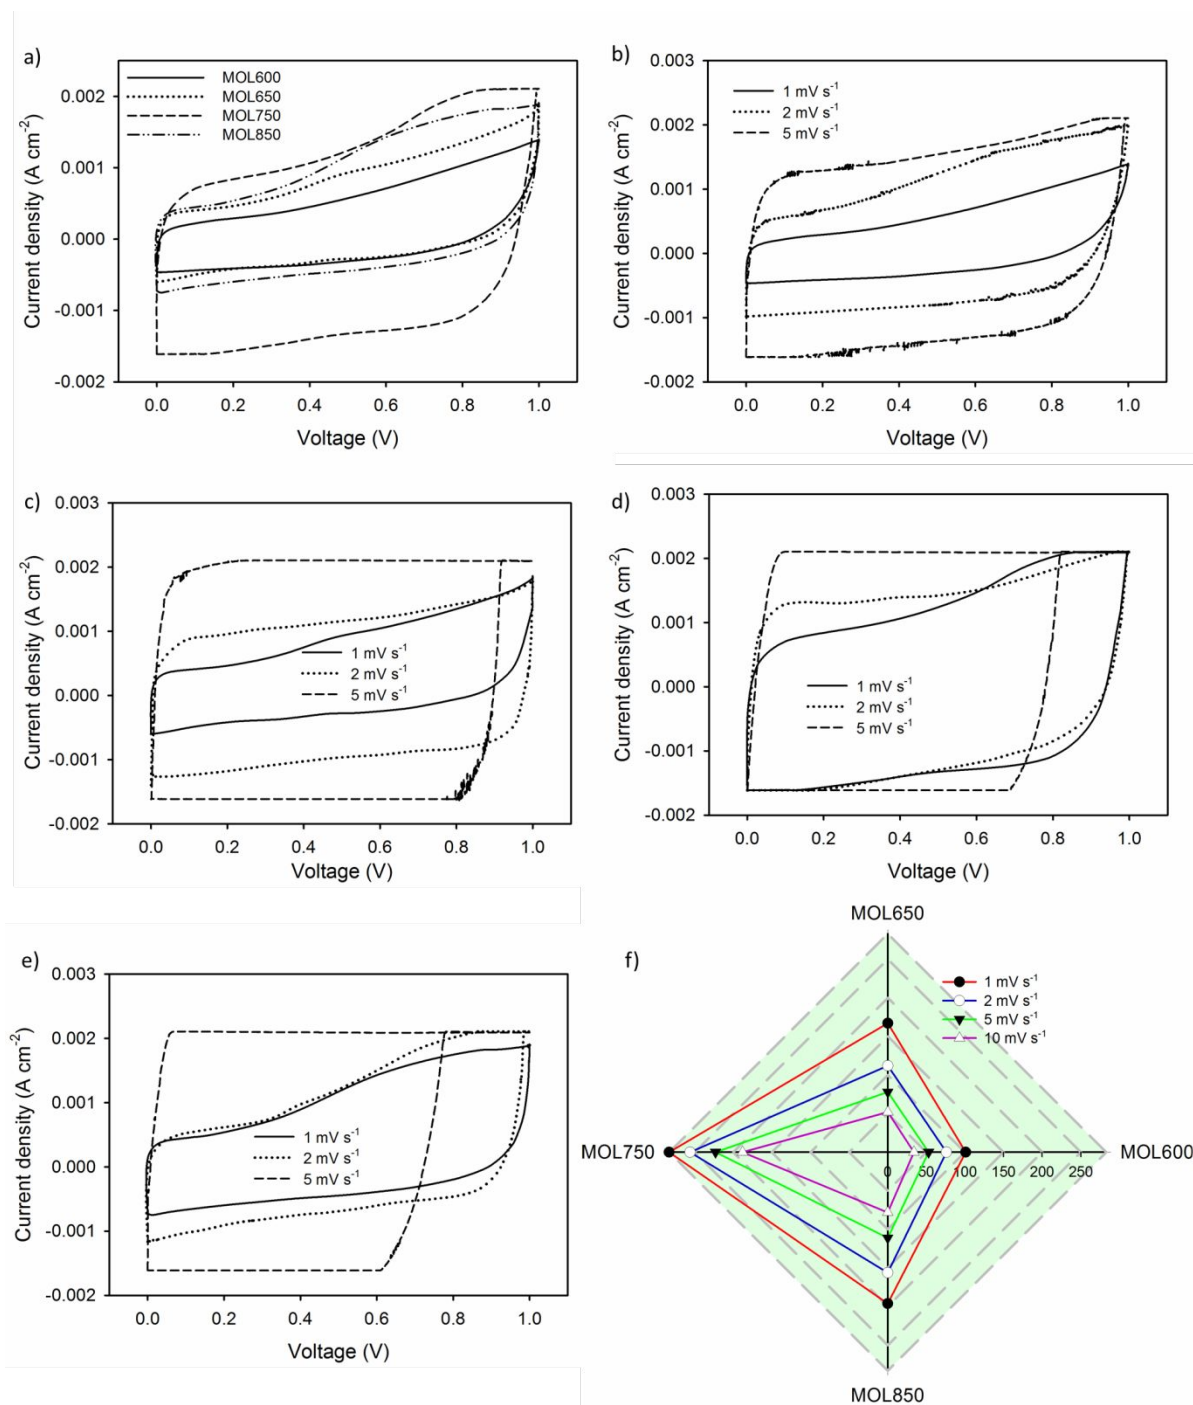

**Figure 5.** a) CV curve of the MOLA carbon disc at a scan rate of 1 mV s<sup>-1</sup>, b)-e) CV curve in different scan rate of MOL600, MOL650, MOL750, and MOL850, and f) capacitive performance of carbon MOLA in different scan rate in 1M H<sub>2</sub>SO<sub>4</sub> electrolyte

The MOL600 carbon discs obtained by carbonization at 600 temperatures have the lowest isotherm curve with mixed types I and IV. This confirmed a low specific surface area of 207 m<sup>2</sup>g<sup>-1</sup> with micro and mesopore structures at a ratio of 65.30% and 34.70%, respectively. After the physical

activation of CO<sub>2</sub> on MOL650, MOL750, and MOL850 carbon discs, the absorption curve regularly increased. This indicated higher pore properties and specific surface areas that exhibit mixed type I and IV isotherm curves with an H4 type hysteresis loop. It also showed a hierarchical pore

combination of micropores and mesopores that are connected<sup>49,50</sup>. Furthermore, the hysteresis loops are open due to the physical structure of the imperfectly developed pores, where their upper surface is smaller than the inner structure and is usually called a bottleneck pore in several studies<sup>34</sup>. Increasing the physical activation temperature from 650 to 750°C can significantly increase the specific surface area by approximately 2 times from 211 to 412 m<sup>2</sup>g<sup>-1</sup>. The distribution of their micro and meso surface areas also changes, which affects the electro-active properties of the electrode material. Abundant micropores promote the material by providing rich channels for ion adsorption, which create an electrical layer, while high mesopores contribute to increased barrier-free charge flow<sup>51,52</sup>. Moreover, MOLs750 indicated the presence of a macropore structure in small amounts as shown by an increase in uptake at a relative pressure of  $0.95 \leq P/P_0 \leq 1.0$ . The macropore structure can also act as a reservoir for electrolyte ions after the confirmation of the electrochemical properties of the supercapacitor<sup>53</sup>, which is in line with the SEM analysis as shown in Figure 2. The complete combination of micro, meso, and macroporous structures in MOL750 is expected to increase the high performance of MOLs precursor-based supercapacitors. An increase in the physical activation temperature to approximately 850°C in the MOL850 samples exhibited a reduction in N<sub>2</sub> gas uptake with their specific surface area of about 322 m<sup>2</sup>g<sup>-1</sup>. There is a possibility that the overgrowth of the pores prevents their walls from maintaining the carbon skeleton for the top to collapse and cover the pores below. The pore structure parameters are shown in Table 2, while the pore size distribution of the MOLs carbon discs is shown in Figure 4. The pyrolyzed carbon disc MOLs at different temperatures showed an abundant pore distribution of micropores ( $\leq 2$ nm), which is rich in mesopores ( $2 \leq x \leq 18$ nm). Carbonized discs at 600°C temperatures gave a relatively balanced micro-mesopores

distribution with an average pore diameter of 3.0 nm. The physical activation treatment of CO<sub>2</sub> at a temperature of 650-850°C also gave abundant micropores, which were dominated by 1.7nm micropores. In addition, this treatment reduced the mean pore diameter to approximately 2.4 nm as shown in Table 2. These results confirm the formation of a hierarchical pore structure that develops more conducive to charge/ion storage at the electrode/electrolyte interface<sup>54,55</sup>. Furthermore, the physical activation of CO<sub>2</sub> at different temperatures indicated that the hierarchical pore structure varied in the pore ranging from 1.4 to 2.7 nm. The potential for MOLs precursors was also confirmed to obtain 3D hierarchical porous carbon discs.


**Table 2.** Porosity properties of MOLs

Carbon samples	S <sub>BET</sub> (m <sup>2</sup> g <sup>-1</sup> )	S <sub>micro</sub> (m <sup>2</sup> g <sup>-1</sup> )	S <sub>meso</sub> (m <sup>2</sup> g <sup>-1</sup> )	V <sub>tot</sub> (cm <sup>3</sup> g <sup>-1</sup> )	D <sub>aver</sub> (nm)
MOL600	207.482	135.500	71.982	0.1558	3.0
MOL650	211.334	165.167	46.167	0.1470	2.7
MOL750	412.196	313.343	98.853	0.2697	2.6
MOL850	322.008	264.035	57.973	0.2004	2.4

## 2.2. Electrochemical performance analysis

The electro-active interactions of ionic charge and carbon-based MOLs electrodes were reviewed in detail through cyclic voltammetry (CV) and galvanostatic charge-discharge (GCD) in a two-electrode system in 1 M H<sub>2</sub>SO<sub>4</sub> electrolyte. Figure 5a shows the CV curve of the carbon disc MOLs at a scan rate of 1 mV s<sup>-1</sup>, showing a nearly perfect rectangular shape in a potential window of 0 to 1 V. This showed the electro-active properties of the normal electrically double-layered carbon disc MOLs. Furthermore, the spike in current density in the potential window of 0.4 to 0.6 V characterizes the additional pseudocapacitance due to the contribution of the heteroatoms as self-doping<sup>56</sup>. It was also discovered that the highest specific capacitance was in the MOL750 carbon disc of 283 Fg<sup>-1</sup>, characterized by the largest rectangular shape, while the lowest

capacitance was in MOL600 of  $101 \text{ Fg}^{-1}$ . The CV curve of MOL650 shows a rectangular shape that is larger than MOL600. This indicated that the  $\text{CO}_2$  physical activation treatment can significantly increase the capacitive properties of MOL650 discs to approximately  $196 \text{ Fg}^{-1}$ . The physical activation of  $\text{CO}_2$  can significantly maximize the impurity evaporation process, thereby, initiating the formation of a rich micro-mesopore structure, which allows more ions to diffuse at the electrolyte/electrode interface.

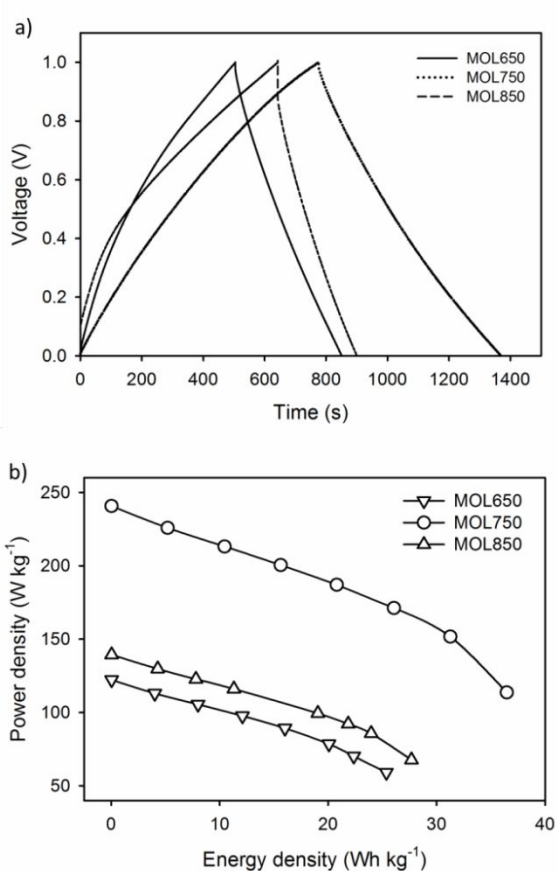


**Figure 6.** a) GCD curves of the disc electrode MOLs in  $1\text{M H}_2\text{SO}_4$  electrolyte, and b) Ragone plot of the disc electrode MOLs in  $1 \text{ M H}_2\text{SO}_4$  electrolyte

The application of a higher activation temperature can maximize the potential of the MOL750 carbon disc also confirmed the greatest capacitive properties. This is contributed by their compactly consolidated material structure with a 3D hierarchical structure, followed by an increase in specific

surface area. However, the addition of a higher temperature to  $850^\circ\text{C}$  reduces the specific capacitance to  $211 \text{ Fg}^{-1}$ . This is because the intense pore expansion can reduce their surface area as shown in Figure 3 and Table 1, which reduced the electrochemical properties of MOL850. The carbon discs MOL600, MOLs650, MOLs750, MOL850 were evaluated at various scanning levels as shown in Figure 5b-e to confirm the effect of pores on the performance of the electrode material. It was also discovered that the curve presents a wide rectangular distortion at a scanning speed of  $2\text{-}5 \text{ mV s}^{-1}$ , which shows a good EDLC performance. The pseudo-capacitance property was not confirmed at the scanning levels of  $2$  and  $5 \text{ mV s}^{-1}$ , therefore, it can be speculated that the electrode material has a weak heteroatom self-doping<sup>57</sup>. Moreover, the higher scan rate also confirms the performance of the capacitive properties of carbon MOLs as shown in Figure 5f. The scan rate treatment of  $1$  to  $10 \text{ mV s}^{-1}$  significantly reduced the specific capacitance caused by their pore size distribution. However, the MOLs750 carbon disc was able to maintain a specific capacitance of  $78\%$  at a scan rate of  $10 \text{ mV s}^{-1}$ . Figure 6a shows the GCD curves of the disc electrode MOLs at higher physical activation temperatures of  $650$ ,  $750$ , and  $850^\circ\text{C}$  in a current density of  $1 \text{ Ag}^{-1}$ . It also showed a distorted isosceles triangle shape, which indicated the nature of the ideal electric double layer. Furthermore, the  $iR$  drop on the barely visible curve indicates low ion diffusion resistance<sup>58</sup>. Their charge times, which were greater than discharge times indicated ion degradation due to the presence of self-doping heteroatoms associated with the redox reactions of oxygenated surface functions in the aqueous electrolyte of  $1 \text{ M H}_2\text{SO}_4$ <sup>21,59</sup>. This is supported by the high level of oxygen in the MOLs carbon disc of approximately  $8.06\text{--}17.41\%$ . The long charge-discharge time of the MOLs disc electrodes characterizes the increase in specific capacitance after the  $\text{CO}_2$  physical activation

process at temperatures of 650, 750, and 850°C. The MOLs750 disc electrodes exhibited the longest discharge time,

showing that their highest capacitance was 307 Fg<sup>-1</sup>, followed by MOLs850 and MOLs650 221 and 156 Fg<sup>-1</sup>, respectively.

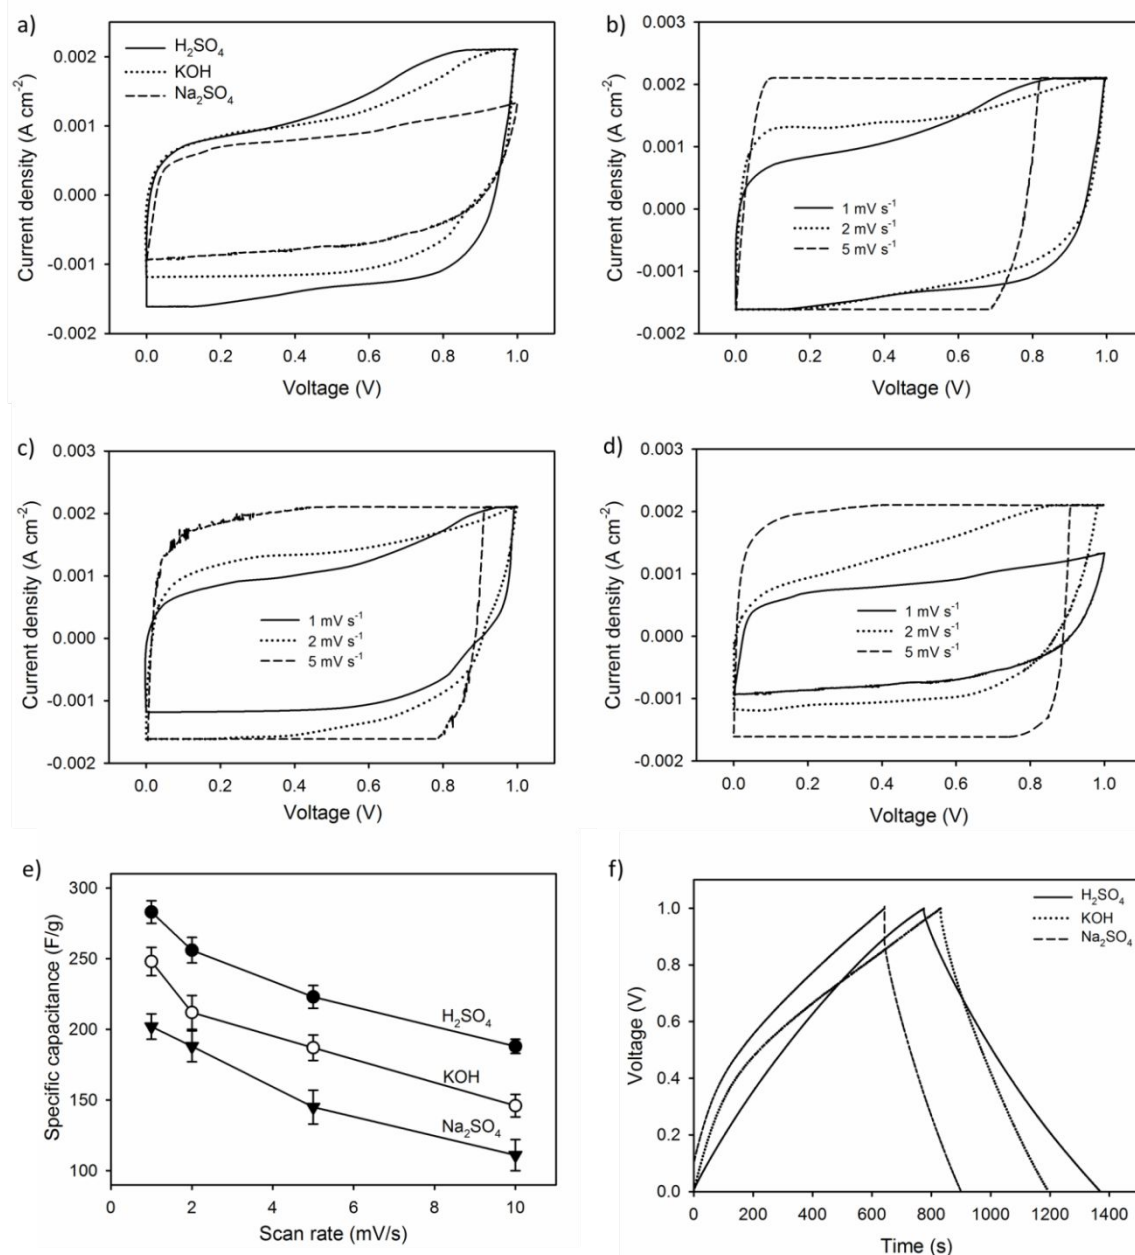

**Figure 7.** a) CV curve of the MOLs750 carbon in different aqueous electrolytes, b)-d) Improved CV scanning was also applied to MOLs750 in different aqueous electrolytes, e) capacitive performance of carbon MOLs in different scan rate in different aqueous electrolytes, and f) GCD curve of the MOLs750 carbon in different aqueous electrolytes

This is directly affected by the increase in surface area and accessible pore volume in the carbon disc MOLs, which are required for electrolytic ion charge accumulation and fast unimpeded transport. The physical activation at a high temperature can

significantly increase the specific surface area, followed by an increase in the total pore volume and their pore size distribution, which is rich in 3D micro-mesopores<sup>52,60</sup>. The results also showed that MOLs carbon discs have the highest specific surface area

of 433 m<sup>2</sup>g<sup>-1</sup> with a maximum total volume of 0.244 cm<sup>3</sup>g<sup>-1</sup>. This allows them to have a high accumulation of electrolyte ions, thereby, forming more electro-active layers. The hierarchically connected 3D rich mesopores structure of MOLs750 confirms their almost unimpeded access to ion transport and the range of diffusion in all directions acting as a reservoir for electrolyte ions<sup>61</sup>. This can significantly improve the capacitive properties of the MOLs carbon electrodes as shown in the MOLs650 to MOLs750 electrodes. An increase in temperature to approximately 850°C at the MOLs850 carbon disc reduced its capacitive properties as shown by excessive pore expansion. This can cause the pore framework to collapse and cover the hierarchical pores below, which reduced their surface area and pore volume (Table 1). However, the GCD curve of MOLs750 has the least symmetrical isosceles triangle shape due to the pseudo-capacitance effect of oxygen heteroatoms [17,50]. The results obtained from GCD are very similar to SEM, EDS, N<sub>2</sub> adsorption/desorption, and CV images. The Ragone plots confirm the energy and power densities of the MOL650, MOL750, and MOL850 disc electrodes as shown in Figure 6b. Meanwhile, the Ragone

plot tends to show that the energy density rises as the physical activation temperature increases at high power density. The MOL650 disc electrode produces an energy density of 25.37 Wh kg<sup>-1</sup> at a power density of 122.25 W kg<sup>-1</sup>. An increase in the physical activation temperature on the MOL750 carbon disc gave the most significant energy density of 36.47 Wh kg<sup>-1</sup> at a power density of 240.73 W kg<sup>-1</sup> due to the contribution of hierarchically connected 3D micro-mesopores, specific surface area, and self-doping heteroatom. The MOLs850 disc electrode shows an energy density of 27.6876 Wh kg<sup>-1</sup> with a power density of almost 139.4286 W kg<sup>-1</sup>. These results indicated that the disc electrode MOLs can produce high properties for electrochemical energy storage applications. Although the specific surface area of MOL750 is not very high, it can have extraordinary energy density and compete with other studies as summarized in Table 3. This is due to the efficiency of the electrode material designed as solid consolidated carbon discs, which optimized 3D hierarchical pores leading to low internal resistance, high conductivity, and producing high electrochemical performance<sup>25,26</sup>.

**Table 3.** Electrochemical performance of MOLs carbon disc in CV and GCD techniques.

Electrolyte	CV		GCD		
	C <sub>sp</sub> (F g <sup>-1</sup> )	C <sub>sp</sub> (F g <sup>-1</sup> )	E (Wh kg <sup>-1</sup> )	P (W kg <sup>-1</sup> )	R (Ω)
1 M H <sub>2</sub> SO <sub>4</sub>	283	307	36.47	240.73	0.006
6 M KOH	248	254	33.21	220.75	0.012
1 M Na <sub>2</sub> SO <sub>4</sub>	202	201	31.59	144.75	0.031


The MOL750 carbon disc electrode was evaluated through different aqueous electrolytes, namely 1 M H<sub>2</sub>SO<sub>4</sub>, 6 M KOH, and 1 M Na<sub>2</sub>SO<sub>4</sub> to confirm the high electrochemical performance. Figure 7a shows the CV curve of the MOLs750 carbon in different aqueous electrolytes. Generally, all aqueous electrolytes showed a distorted rectangular shape, which indicated good EDLC properties. In H<sub>2</sub>SO<sub>4</sub> and KOH electrolytes, there was a sudden increase in current density in the voltage range of 0.6-

0.8 V. This is closely related to the redox reaction of oxygen heteroatoms under acidic and alkaline aqueous electrolytes that confirms the presence of apparent capacitance. However, it was not discovered in the neutral aqueous electrolyte Na<sub>2</sub>SO<sub>4</sub>. Based on the magnitude of the formed CV curve, the performance of MOL750 on different electrolytes can be ordered by H<sub>2</sub>SO<sub>4</sub>>KOH>Na<sub>2</sub>SO<sub>4</sub> with specific capacitances of 283, 248, and 202 F g<sup>-1</sup>. Improved CV scanning was also applied to

MOLs750 in different aqueous electrolytes as shown in Figure 7b-d. All three aqueous electrolytes still produced a distorted rectangular shape, although showing widening towards a parallelogram at scan rates of 2 and 5  $\text{mV s}^{-1}$ . This generally exhibited good EDLC performance on acidic, alkaline, and neutral electrolytes. Furthermore, it was discovered that higher scan rates reduced their capacitive properties as shown in Figure 7e. Although specific capacitance was decreased at a scan rate of 10  $\text{mV s}^{-1}$  for all electrolytes, they still maintain their capacitive properties of 61-78% with the order  $\text{H}_2\text{SO}_4 > \text{KOH} > \text{Na}_2\text{SO}_4$ . This was significantly contributed by rich mesoporosity  $>30\%$ , allowing electrolyte ions to diffuse smoothly when their scan is enhanced. Moreover, the contribution of this aqueous electrolyte modification is also reviewed through the GCD technique. Figure 7f depicts the GCD curves of the MOL750 carbon disc electrodes on different electrolytes. It exhibits a nearly ideal isosceles triangular shape, which indicates the normal EDLC properties of an aqueous electrolyte. However, the KOH electrolyte appeared a GCD curve that contained the greatest ion degradation characterized by a charging time, which is significantly different from the discharging time. This is closely related to oxygen heteroatoms with the potential of the evolution of  $\text{O}_2$  and  $\text{H}_2$  in aqueous electrolyte systems<sup>62</sup>. It was also discovered that the  $iR$  drop was relatively very low, confirming the high conductivity properties of the MOLs750 precursor as summarized in Table 3.

This phenomenon initiates the high storage capacity of supercapacitors despite their relatively low surface area. Based on the length of the discharge time, the  $\text{H}_2\text{SO}_4$  electrolyte exhibited the highest specific capacitance, followed by KOH and  $\text{Na}_2\text{SO}_4$  with their capacitive values of 307, 254, and 201  $\text{F g}^{-1}$ , respectively. This result is in line with the CV analysis, which also revealed almost similar results. Moreover, modifying the cations and anions in the aqueous electrolyte can affect the electrochemical

substance of the supercapacitor, especially at the MOL750 carbon disc electrode. This is due to Ionic mobility, ionic hydrated radius, conductivity, and impact on charge/ion exchange as well as diffusion<sup>63</sup>. The small dehydrated sphere of  $\text{H}^+$  cations compared to  $\text{K}^+$  and  $\text{Na}^+$  allows the charge on the cations to produce the greatest molar ionic conductivity and ionic mobility<sup>64</sup>. These characteristics are needed to obtain fast charge transfer and high ion adsorption at the electrolyte/electrode interface. Similarly, the specification of the cationic radius is also closely related to long-term cycle stability for the MOL750 electrode material, as shown in Figure 10e, where the  $\text{H}_2\text{SO}_4$  electrolyte maintained a specific capacitance of 78%. Anion specifications were also studied in their interactions with the MOL750 disc electrode. The results showed that the  $\text{OH}^-$  has a narrower hydration ball radius, initiating better conductivity and ionic mobility. Meanwhile, the  $\text{SO}_4^{2-}$  exhibited a larger hydration ball radius, leading to a decrease in the number of ions accessing the pores and lower electrical double sheet formation<sup>65</sup>. Relative to other anions,  $\text{SO}_4^{2-}$  ion has poor conductivity and ion mobility, which makes  $\text{Na}_2\text{SO}_4$  electrolytes show the lowest capacitive properties compared to  $\text{H}_2\text{SO}_4$  and KOH electrolytes.

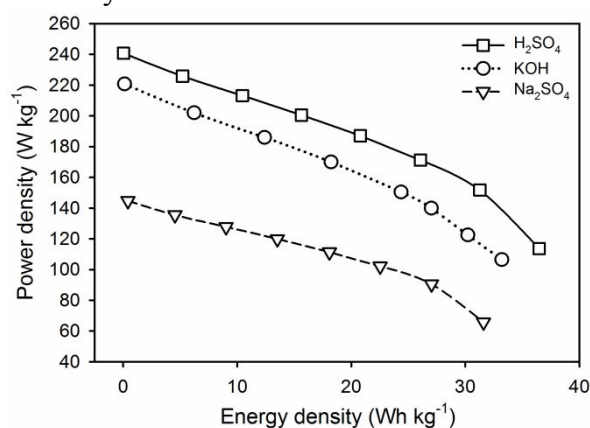

**Figure 8.** Ragone plot of the disc electrode MOLs in different aqueous electrolytes

For detailed confirmation, the potential of the MOL750 disc electrode in different aqueous electrolytes was reviewed through



the Ragone plot as shown in Figure 8. The H<sub>2</sub>SO<sub>4</sub> electrolyte demonstrated the highest performance with an energy density of 36.47 Wh kg<sup>-1</sup> at a power density of 240.73 W kg<sup>-1</sup>. Furthermore, 3D hierarchical pore properties with micro and meso ratio of approximately 3:1 perfectly match the criteria for H<sup>+</sup> anions and SO<sub>4</sub><sup>2-</sup> cations in aqueous electrolyte H<sub>2</sub>SO<sub>4</sub> to possess high energy density in supercapacitor energy

storage devices. The alkaline electrolyte KOH also displays an energy density of 33.2047 Wh kg<sup>-1</sup> at a power density of 220.750 W kg<sup>-1</sup>, while the neutral electrolyte Na<sub>2</sub>SO<sub>4</sub> exhibits an energy density of 31.5964 Wh kg<sup>-1</sup> at a power density of 144.7541 W kg<sup>-1</sup>. This result is relatively high compared to previous reports, which are summarized in Table 4.

**Table 4.** Comparison of electrochemical performance in different carbon sources.

Sources	S <sub>BET</sub> (m <sup>2</sup> g <sup>-1</sup> )	Electrolyte	Electrode design	C <sub>sp</sub> (F g <sup>-1</sup> )	E (Wh kg <sup>-1</sup> )	R (Ω)	Ref
Wood powders	282.4	6 M KOH	Powder with PTFE	150.1	-	-	24
Feather finger grass flower	637.1	6 M KOH	Powder with PTFE	315	18.75	-	25
Camellia pollen	852	6 M KOH	Powder with PTFE	300	14.3	0.68	26
Sword bean shell	2282	6 M KOH	Powder with PVDF	264	12.5	1.38	42
foxtail grasses	819	6 M KOH	Powder with PTFE	358	18.2	0.8	51
Calcium D-gluconate	539	1 M H <sub>2</sub> SO <sub>4</sub>	Powder with PTFE	355	40.5	-	66
Rubber wood sawdust	2820	1 M H <sub>2</sub> SO <sub>4</sub>	Powder with PTFE	185	6.93	1.32	67
Kapok flower	1904.1	6 M KOH	Powder with PTFE	286.8	-	0.79	68
Banana leaves	1459	[BMIM][PF <sub>6</sub> ]	Powder with PVP	190	59	-	69
Shallot peel	1182.2	1 M H <sub>2</sub> SO <sub>4</sub>	Solid coin without binder	170.12	16.67	0.031	70
MOLs	412.196	1 M Na <sub>2</sub> SO <sub>4</sub>	Concolidate disc binder-free	201	31.59	0.031	This work
MOLs	412.196	6 M KOH	Concolidate disc binder-free	254	33.21	0.012	This work
MOLs	412.196	1 M H <sub>2</sub> SO <sub>4</sub>	Concolidate disc binder-free	307	36.47	0.006	This work

### 3. CONCLUSION

The green *Moringa oleifera* leaves (MOLs) were converted into a novel consolidated carbon disc-based electrode material through a facile, simple, and environmental approach. The MOLs carbon discs obtained showed a rich 3D hierarchical micro-

mesopore structure decorated nanofibers. Furthermore, oxygen heteroatoms (8.06-17.41%) were confirmed with a high carbon content of 88.91%. Furthermore, the electrochemical properties of the carbon disc electrodes of MOLs were evaluated in a symmetric supercapacitor system on

1  
2  
3 different aqueous electrolytes. The MOL750  
4 disc electrode showed the best  
5 electrochemical properties with a specific  
6 capacitance of  $307 \text{ Fg}^{-1}$  on aqueous  
7 electrolyte  $\text{H}_2\text{SO}_4$ . Moreover, the MOLs750  
8 discs can maintain their high performance  
9 on aqueous electrolytes KOH and  $\text{Na}_2\text{SO}_4$   
10 with specific capacitances of 254 and 201  
11  $\text{Fg}^{-1}$  in a current density of  $1 \text{ Ag}^{-1}$ . The  
12 design of binder-free consolidated carbon  
13  
14

## 15 16 17 **4. EXPERIMENTAL SECTION**

### 18 **4.1. Synthesis of porous consolidated** 19 **carbon disc from MOLs**

20 Green *Moringa oleifera* leaves, hereinafter  
21 referred to MOLs, were obtained from a  
22 vegetable supplier of Pekanbaru grand-  
23 market, separated from the stalks, and  
24 cleaned. After the soil and sand elements are  
25 removed, the leaves were sundried for 2  
26 days and further oven-dried at  $110^\circ\text{C}$  (Oven  
27 food warmer 10-110C type FW-35) for 35  
28 hours until the green precursors turned  
29 wilted and brittle. The precursor was  
30 converted into powder form through pre-  
31 carbonization, crusher, and sieving. Pre-  
32 carbonization was carried out by preparing  
33 30 g of dried leaves sample in a closed  
34 container and placing it in an oven with a  
35 temperature of  $250^\circ\text{C}$  (KIRIN Oven 10L  
36 KBO 100 M) for 2 hours 30 minutes. The  
37 sample obtained from the pre-carbonization  
38 was inserted into the crusher instrument for  
39 24 hours. The precursor powder from the  
40 crusher was sieved using a 250 mesh (CBN  
41 test sieve analysis, Cat No. KB-31) to obtain  
42 a homogeneous powder, which was  
43 chemically activated by zinc chloride  
44 impregnated in solution  $0.5 \text{ mol/L}$  solution.  
45 Zinc chloride for analysis was purchased  
46 from EMSURE ACS, ISO, Reag. Ph Eur.  
47 CAS No. 7646-85-7, EC Number 231-592-  
48 0. Subsequently, the dried powder precursor  
49 was mixed with  $\text{ZnCl}_2$  solution on a Digital  
50 Lab Thermostatic Hot-Plate instrument  
51 (WiseStir Wisd MSH30D) with a rotation  
52 rate of 300 rpm at a temperature of  $80^\circ\text{C}$  for  
53 2 hours, while the impregnated samples  
54 were dried in an oven at  $110^\circ\text{C}$  for 2 days.  
55  
56  
57  
58  
59  
60

disc MOLs showed their great potential in  
producing high capacitive properties, lower  
internal resistance, high conductivity,  
despite the relatively low surface area of  
 $412.196 \text{ m}^2\text{g}^{-1}$ . Therefore, the MOLs can be  
developed as a novel approach for producing  
excellent biomass-based electrode material  
to enhance the performance of energy  
storage devices in symmetric  
supercapacitors.

As a novelty in this study, the carbon  
powder was converted into a consolidated  
disc without a binder. For one solid disc  
sample, 0.7 g of sample powder was pressed  
through a hydraulic press (Hydraulic Press  
Bench Type 10T Krisbow KW0500135) at a  
pressure equal to a mass of 8 tons. A total of  
15 monolith solid discs were further put into  
a vertical furnace (Box Furnace NDT-LB 5,  
Payun Tech) for high-temperature pyrolysis.  
The pyrolysis process including  
carbonization and physical activation was  
carried out in a single-stage integrated  
system. This process starts with  
carbonization in the  $\text{N}_2$  gas environment  
from a temperature of 30 to  $600^\circ\text{C}$  with a  
gas increase rate of  $3^\circ\text{C}/\text{min}$ . The gas  
environment is replaced with  $\text{CO}_2$  as a  
physical activation stage to a high different  
temperature of 650, 750, and  $850^\circ\text{C}$ , with an  
increased rate of  $10^\circ\text{C}/\text{min}$ . For comparison,  
a sample was further prepared at  $600^\circ\text{C}$   
without physical activation. Meanwhile, the  
3D porous carbon samples obtained were  
neutralized by soaking in distilled water  
made on a lab-scale. The immersion water  
was confirmed to be neutral ( $\text{pH}=7$ ) using a  
universal pH strip indicator, which was  
purchased from Merck KGaA, 64271  
Darmstadt, Germany. Several labels were  
made to facilitate the analysis and  
comparison of materials, as well as  
electrochemical properties of 3D porous  
activated carbon-based MOLs. It includes  
MOL600 as a precursor as well as  
MOLs650, MOLs750, and MOLs850 from  
 $\text{ZnCl}_2$  impregnation and physical activation  
with different temperatures of 650, 750, and  
 $850^\circ\text{C}$ .

## 4.2. Material characterizations

The initial porosity properties of solid consolidated disc carbon samples were evaluated through density reduction in high temperatures before and after the pyrolysis process. The density was calculated based on measurements of mass using a Labtronics GM-303 analytical balance, thickness, and diameter of the solid carbon monolith pellets using a QRC5 digital caliper<sup>71</sup>. The porosity properties of carbon MOLs were further evaluated through the N<sub>2</sub> gas adsorption/desorption using Quantachrome version 10.01 at a temperature of 77 K in the P/P<sub>0</sub> relative pressure range of 0.00-0.985. The specific surface area was determined with the Breunauer-Emmet-Teller (BET) technique and the pore size distribution was calculated using the density functional theory (DFT) approach. Furthermore, the structure and morphology of activated carbon were reviewed through X-ray diffraction (XRD) and scanning electron microscopy (SEM) methods. X-ray diffraction (XRD) was examined in CuK $\alpha$  source ( $\lambda=1.54051$ ) at an angle range of 10-60° (Malvern Panalytical's X-ray diffractometers), while interlayer spacing was calculated using Bragg's law and lattice parameters ( $L_c$  and  $L_a$ ), which were determined by equation debye-scheerer<sup>34,35</sup>. Similarly, scanning electron microscopy (SEM) was reviewed at a voltage of 15 kV in the energy range 0-20 KeV using JEOL-JSM6510LA instrument. The elemental status of MOLs was also reviewed through the energy dispersive spectroscopy method (JEOL-JSM-6510-LA instrument).

## 4.3. Measurement of electrochemical properties

The working electrodes were prepared in a two-system configuration similar to a binder-free two solid disc carbon MOLs with a loading mass of approximately  $\pm 10.0$  mg. The carbon disc electrodes were prepared in diameter of  $\pm 8$  mm with a thickness of 0.19 mm. They were separated by an organic separator made from eggshell

membranes. As a support for the electrode, the cell body was made in a rectangular geometry with a hole of  $\pm 9.0$  mm diameter in the middle. The current collector was prepared from 0.2mm stainless steel and an aqueous electrolyte consisting of 1 M H<sub>2</sub>SO<sub>4</sub>, 6 M KOH, and 1 M Na<sub>2</sub>SO<sub>4</sub> was selected. Subsequently, the electrochemical properties were reviewed using cyclic voltammetry technique with CV, RAD-ER 5841, calibrated error  $\pm 6.0\%$  in a potential window range of 0.0-1.0V at different scanning rates of 1, 2, 5, and 10 mV s<sup>-1</sup>. Specific capacitance, energy and power densities, and internal resistance were further evaluated through the galvanostatic charge-discharge technique using GCD, RAD-ER 2018 at a constant current density of 1.0 A g<sup>-1</sup> based on the standard equation<sup>72</sup>.

## ACKNOWLEDGEMENTS

The research was financially supported by second years Project of Word Class Research (WCR) in *Kementerian Pendidikan, Kebudayaan, Riset, dan Teknologi*, Republic of Indonesia with the title "High energy and power densities of supercapacitor for the optimization of electrode supply process".

## REFERENCES

- (1) International Energy Agency. *Global Energy Review 2021*; 2021.
- (2) BP. *Statistical Review of World Energy*; 2021; Vol. 70.
- (3) BPSTATS. *Review of World Energy Statistical Review of World, 68th Edition*; 2019.
- (4) REN21. *Renewables 2021 Global Status Report*; 2021.
- (5) Burke, A. Ultracapacitors: Why, How, and Where Is the Technology. *J. Power Sources* **2000**, *91* (1), 37–50.
- (6) Li, X.; Zhang, J.; Liu, B.; Su, Z. A Critical Review on the Application and Recent Developments of Post-Modified Biochar in Supercapacitors. *J. Clean. Prod.* **2021**, *310* (April), 127428.

- (7) Zhang, W.; Cheng, R. R.; Bi, H. H.; Lu, Y. H.; Ma, L. B.; He, X. J. A Review of Porous Carbons Produced by Template Methods for Supercapacitor Applications. *Xinxing Tan Cailiao/New Carbon Mater.* **2021**, *36* (1), 69–81.
- (8) Miller, E. E.; Hua, Y.; Tezel, F. H. Materials for Energy Storage: Review of Electrode Materials and Methods of Increasing Capacitance for Supercapacitors. *J. Energy Storage* **2018**, *20* (February), 30–40.
- (9) González, A.; Goikolea, E.; Barrena, J. A.; Mysyk, R. Review on Supercapacitors: Technologies and Materials. *Renew. Sustain. Energy Rev.* **2016**, *58*, 1189–1206. <https://doi.org/10.1016/j.rser.2015.12.249>.
- (10) Wang, G.; Zhang, L.; Zhang, J. A Review of Electrode Materials for Electrochemical Supercapacitors. *Chem. Soc. Rev.* **2012**, *41* (2), 797–828.
- (11) Dessie, Y.; Tadesse, S.; Eswaramoorthy, R.; Abebe, B. Recent Developments in Manganese Oxide Based Nanomaterials with Oxygen Reduction Reaction Functionalities for Energy Conversion and Storage Applications: A Review. *J. Sci. Adv. Mater. Devices* **2019**, *4* (3), 353–369.
- (12) Soltani, S.; Khanian, N.; Choong, T. S. Y.; Rashid, U. Recent Progress in the Design and Synthesis of Nanofibers with Diverse Synthetic Methodologies: Characterization and Potential Applications. *New J. Chem.* **2020**, *44* (23), 9581–9606. <https://doi.org/10.1039/d0nj01071e>.
- (13) Zhang, Q. Z.; Zhang, D.; Miao, Z. C.; Zhang, X. L.; Chou, S. L. Research Progress in MnO<sub>2</sub>–Carbon Based Supercapacitor Electrode Materials. *Small* **2018**, *14* (24), 1–15.
- (14) Arunachalam, R.; Prataap, R. K. V.; Pavul Raj, R.; Mohan, S.; Vijayakumar, J.; Péter, L.; Al Ahmad, M. Pulse Electrodeposited RuO<sub>2</sub> Electrodes for High-Performance Supercapacitor Applications. *Surf. Eng.* **2019**, *35* (2), 103–109.
- (15) Li, J.; Hu, H.; Li, H.; Yao, C. Recent Developments in Electrochemical Sensors Based on Nanomaterials for Determining Glucose and Its Byproduct H<sub>2</sub>O<sub>2</sub>. *J. Mater. Sci.* **2017**, *52* (17), 10455–10469.
- (16) Wang, J.; Zheng, F.; Yu, Y.; Hu, P.; Li, M.; Wang, J.; Fu, J.; Zhen, Q.; Bashir, S.; Liu, J. L. Symmetric Supercapacitors Composed of Ternary Metal Oxides (NiO/V<sub>2</sub>O<sub>5</sub>/MnO<sub>2</sub>) Nanoribbon Electrodes with High Energy Storage Performance. *Chem. Eng. J.* **2021**, *426* (August).
- (17) Zang, S.; Jiang, J.; An, Y.; Li, Z.; Guo, H.; Sun, Y.; Dou, H.; Zhang, X. A Novel Porous Organic Polymer-Derived Hierarchical Carbon for Supercapacitors with Ultrahigh Energy Density and Durability. *J. Electroanal. Chem.* **2020**, *876*, 114723.
- (18) Majid, S.; Ali, A. S. G.; Cao, W. Q.; Reza, R.; Ge, Q. Biomass-Derived Porous Carbons as Supercapacitor Electrodes-A Review. *New Carbon Mater.* **2021**, *36* (3), 546–572. [https://doi.org/10.1016/S1872-5805\(21\)60038-0](https://doi.org/10.1016/S1872-5805(21)60038-0).
- (19) Saini, S.; Chand, P.; Joshi, A. Biomass Derived Carbon for Supercapacitor Applications: Review. *J. Energy Storage* **2021**, *39* (April), 102646.
- (20) Li, Z.; Guo, D.; Liu, Y.; Wang, H.; Wang, L. Recent Advances and Challenges in Biomass-Derived Porous Carbon Nanomaterials for Supercapacitors. *Chem. Eng. J.* **2020**, *397* (October 2019), 125418.
- (21) Gopalakrishnan, A.; Badhulika, S. Effect of Self-Doped Heteroatoms on the Performance of Biomass-Derived Carbon for Supercapacitor Applications. *J. Power Sources* **2020**, *480* (August), 228830.
- (22) Aruchamy, K.; Dharmalingam, K.; Lee, C. W.; Mondal, D.; Sanna Kotrappanavar, N. Creating Ultrahigh Surface Area Functional Carbon from Biomass for High Performance Supercapacitor and Facile Removal of Emerging Pollutants. *Chem. Eng. J.* **2022**, *427* (April 2021), 131477.
- (23) Zhang, Y.; Wu, C.; Dai, S.; Liu, L.; Zhang, H.; Shen, W.; Sun, W.; Ming Li, C. Rationally Tuning Ratio of Micro- to Meso-Pores of Biomass-Derived Ultrathin Carbon Sheets toward Supercapacitors with High

1  
2  
3 Energy and High Power Density. *J. Colloid*  
4 *Interface Sci.* **2022**, *606*, 817–825.

5 (24) Wang, C.; Wang, H.; Dang, B.;  
6 Wang, Z.; Shen, X.; Li, C.; Sun, Q.  
7 Ultrahigh Yield of Nitrogen Doped Porous  
8 Carbon from Biomass Waste for  
9 Supercapacitor. *Renew. Energy* **2020**, *156*,  
10 370–376.

11 (25) Senthil, R. A.; Yang, V.; Pan, J.;  
12 Sun, Y. A Green and Economical Approach  
13 to Derive Biomass Porous Carbon from  
14 Freely Available Feather Finger Grass  
15 Flower for Advanced Symmetric  
16 Supercapacitors. *J. Energy Storage* **2021**, *35*  
17 (January), 102287.

18 (26) Cao, L.; Li, H.; Xu, Z.; Zhang, H.;  
19 Ding, L.; Wang, S.; Zhang, G.; Hou, H.; Xu,  
20 W.; Yang, F.; Jiang, S. Comparison of the  
21 Heteroatoms-Doped Biomass-Derived  
22 Carbon Prepared by One-Step Nitrogen-  
23 Containing Activator for High Performance  
24 Supercapacitor. *Diam. Relat. Mater.* **2021**,  
25 *114* (November 2020), 108316.

26 (27) Wang, L.; Li, X.; Huang, X.; Han,  
27 S.; Jiang, J. Activated Green Resources to  
28 Synthesize N, P Co-Doped O-Rich  
29 Hierarchical Interconnected Porous Carbon  
30 for High-Performance Supercapacitors. *J.*  
31 *Alloys Compd.* **2021**, *891*, 161908.  
32 <https://doi.org/10.1016/j.jallcom.2021.161908>  
33 8.

34 (28) Apriwandi, A.; Taer, E.; Farma, R.;  
35 Setiadi, R. N.; Amiruddin, E. A Facile  
36 Approach of Micro-Mesopores Structure  
37 Binder-Free Coin/Monolith Solid Design  
38 Activated Carbon for Electrode  
39 Supercapacitor. *J. Energy Storage* **2021**, *40*  
40 (June), 102823.

41 (29) Taer, E.; Apriwandi; Dalimunthe, B.  
42 K. L.; Taslim, R. A Rod-like Mesoporous  
43 Carbon Derived from Agro-Industrial  
44 Cassava Petiole Waste for Supercapacitor  
45 Application. *J. Chem. Technol. Biotechnol.*  
46 **2021**, *96* (3), 662–671.

47 (30) Martínez-Casillas, D. C.; Mascorro-  
48 Gutiérrez, I.; Arreola-Ramos, C. E.;  
49 Villafán-Vidales, H. I.; Arancibia-Bulnes, C.  
50 A.; Ramos-Sánchez, V. H.; Cuentas-  
51 Gallegos, A. K. A Sustainable Approach to  
52 Produce Activated Carbons from Pecan

Nutshell Waste for Environmentally  
53 Friendly Supercapacitors. *Carbon N. Y.*  
54 **2019**, *148*, 403–412.

55 (31) Wei, H.; Wang, H.; Li, A.; Li, H.;  
56 Cui, D.; Dong, M.; Lin, J.; Fan, J.; Zhang,  
57 J.; Hou, H.; Shi, Y.; Zhou, D.; Guo, Z.  
58 Advanced Porous Hierarchical Activated  
59 Carbon Derived from Agricultural Wastes  
toward High Performance Supercapacitors.  
*J. Alloys Compd.* **2020**, *820*, 153111.

(32) Achour, A.; Arman, A.; Islam, M.;  
Zavarian, A. A.; Al-zubaidi, A. B.; Szade, J.  
Synthesis and Characterization of Porous  
CaCO<sub>3</sub> Micro/Nano-Particles. *Eur. Phys. J.*  
*PLUS* **2017**, *132*, 267.

(33) Jose, A.; Devi, K. R. S.; Pinheiro,  
D.; Lakshmi, S. Electrochemical Synthesis,  
Photodegradation and Antibacterial  
Properties of PEG Capped Zinc Oxide  
Nanoparticles. *J. Photochem. Photobiol. B*  
*Biol.* **2018**, *187*, 25–34.

(34) Ayinla, R. T.; Dennis, J. O.; Zaid, H.  
M.; Sanusi, Y. K.; Usman, F.; Adebayo, L.  
L. A Review of Technical Advances of  
Recent Palm Bio-Waste Conversion to  
Activated Carbon for Energy Storage. *J.*  
*Clean. Prod.* **2019**, *229*, 1427–1442.

(35) Yaya, A.; Agyei-Tuffour, B.; Dodoo-  
Arhin, D.; Nyankson, E.; Annan, E.;  
Konadu, D. S.; Sinayobye, E.; Baryeh, E. a.;  
Ewels, C. P. Layered Nanomaterials- A  
Review. *Glob. J. Eng. Des. Technol.* **2012**, *1*  
(2), 32–41.

(36) Deraman, M.; Daik, R.; Soltaninejad,  
S.; Nor, N. S. M.; Awitdrus; Farma, R.;  
Mamat, N. F.; Basri, N. H.; Othman, M. A.  
R. A New Empirical Equation for  
Estimating Specific Surface Area of  
Supercapacitor Carbon Electrode from X-  
Ray Diffraction. *Adv. Mater. Res.* **2015**,  
*1108*, 1–7.

(37) Kumar, K.; Saxena, R. K.; Kothari,  
R.; Suri, D. K.; Kaushik, N. K.; Bohra, J. N.  
Correlation between Adsorption and X-Ray  
Diffraction Studies on Viscose Rayon Based  
Activated Carbon Cloth. *Carbon N. Y.* **1997**,  
*35* (12), 1842–1844. \

(38) Riyanto, C.; Kristen, U.; Wacana, S.;  
Ampri, M. S.; Martono, Y.; Kristen, U.;  
Wacana, S. Synthesis and Characterization

of Nano Activated Carbon from Annatto Peels (*Bixa Orellana* L.) Viewed from Temperature Activation and Impregnation Ratio of H<sub>3</sub>PO<sub>4</sub>. *J. Sci. data Anal.* **2020**, *1* (1), 44–50.

(39) Salakhum, S.; Yutthalekha, T.; Chareonpanich, M.; Limtrakul, J.; Wattanakit, C. Synthesis of Hierarchical Faujasite Nanosheets from Corn Cob Ash-Derived Nanosilica as Efficient Catalysts for Hydrogenation of Lignin-Derived Alkylphenols. *Microporous Mesoporous Mater.* **2018**, *258*, 141–150. <https://doi.org/10.1016/j.micromeso.2017.09.009>.

(40) Pourhosseini, S. E. M.; Norouzi, O.; Naderi, H. R. Study of Micro/Macro Ordered Porous Carbon with Olive-Shaped Structure Derived from *Cladophora Glomerata* Macroalgae as Efficient Working Electrodes of Supercapacitors. *Biomass and Bioenergy* **2017**, *107* (October), 287–298.

(41) Li, J.; Zou, Y.; Xiang, C.; Xu, F.; Sun, L.; Li, B.; Zhang, J. Osmanthus Fragrans-Derived N-Doped Porous Carbon for Supercapacitor Applications. *J. Energy Storage* **2021**, *42*, 103017.

(42) Chen, T.; Luo, L.; Luo, L.; Deng, J.; Wu, X.; Fan, M.; Du, G.; Weigang Zhao. High Energy Density Supercapacitors with Hierarchical Nitrogen-Doped Porous Carbon as Active Material Obtained from Bio-Waste. *Renew. Energy* **2021**, *175*, 760–769.

(43) Liang, Y.; Lu, Y.; Xiao, G.; Zhang, J.; Chi, H.; Dong, Y. Hierarchical Porous Nitrogen-Doped Carbon Microspheres after Thermal Rearrangement as High Performance Electrode Materials for Supercapacitors. *Appl. Surf. Sci.* **2020**, *529*, 147141.

(44) Bhat, V. S.; Kanagavalli, P.; Sriram, G.; B, R. P.; John, N. S.; Veerapandian, M.; Kurkuri, M.; Hegde, G. Low Cost, Catalyst Free, High Performance Supercapacitors Based on Porous Nano Carbon Derived from Agriculture Waste. *J. Energy Storage* **2020**, *32* (August), 101829.

(45) Márquez-Montesino, F.; Torres-Figueroa, N.; Lemus-Santana, A.; Trejo, F. Activated Carbon by Potassium Carbonate

Activation from Pine Sawdust (*Pinus Montezumae* Lamb.). *Chem. Eng. Technol.* **2020**, *43* (9), 1716–1725.

(46) Zhang, Y.; Yu, S.; Lou, G.; Shen, Y.; Chen, H.; Shen, Z.; Zhao, S.; Zhang, J.; Chai, S.; Zou, Q. Review of Macroporous Materials as Electrochemical Supercapacitor Electrodes. *J. Mater. Sci.* **2017**, *52* (19), 11201–11228.

<https://doi.org/10.1007/s10853-017-0955-3>.

(47) Boujibar, O.; Ghamouss, F.; Ghosh, A.; Achak, O.; Chafik, T. Efficient CO<sub>2</sub> Capture by Ultra-High Microporous Activated Carbon Made from Natural Coal. *Chem. Eng. Technol.* **2021**, *44* (1), 148–155.

(48) Yakaboylu, G. A.; Jiang, C.; Yumak, T.; Zondlo, J. W.; Wang, J.; Sabolsky, E. M. Engineered Hierarchical Porous Carbons for Supercapacitor Applications through Chemical Pretreatment and Activation of Biomass Precursors. *Renew. Energy* **2021**, *163*, 276–287.

(49) Sing, K. S. W. Reporting Physisorption Data for Gas/Solid Systems with Special Reference to the Determination of Surface Area and Porosity. *Pure Appl. Chem.* **1982**, *54* (11), 2201–2218.

(50) Zheng, G.; Huang, Z.; Liu, Z. Cooperative Utilization of Beet Pulp and Industrial Waste Fly Ash to Produce N/P/O Self-Co-Doped Hierarchically Porous Carbons for High-Performance Supercapacitors. *J. Power Sources* **2021**, *482* (September 2020), 228935.

(51) Liang, X.; Liu, R.; Wu, X. Biomass Waste Derived Functionalized Hierarchical Porous Carbon with High Gravimetric and Volumetric Capacitances for Supercapacitors. *Microporous Mesoporous Mater.* **2021**, *310* (September 2020), 110659.

(52) Zhang, X.; Liu, B.; Yan, X.; Zhao, X.; Zhang, Y.; Wei, Y.; Cao, Q. Design and Structure Optimization of 3D Porous Graphitic Carbon Nanosheets for High-Performance Supercapacitor. *Microporous Mesoporous Mater.* **2020**, *309* (August), 110580.

<https://doi.org/10.1016/j.micromeso.2020.110580>.

(53) Wang, Y.; Qiao, M.; Mamat, X. Nitrogen-Doped Macro-Meso-Micro Hierarchical Ordered Porous Carbon Derived from ZIF-8 for Boosting Supercapacitor Performance. *Appl. Surf. Sci.* **2021**, *540* (P1), 148352.

(54) Wu, J.; Xia, M.; Zhang, X.; Chen, Y.; Sun, F.; Wang, X.; Yang, H.; Chen, H. Hierarchical Porous Carbon Derived from Wood Tar Using Crab as the Template: Performance on Supercapacitor. *J. Power Sources* **2020**, *455* (February), 227982.

(55) Yang, V.; Senthil, R. A.; Pan, J.; Kumar, T. R.; Sun, Y.; Liu, X. Hierarchical Porous Carbon Derived from Jujube Fruits as Sustainable and Ultrahigh Capacitance Material for Advanced Supercapacitors. *J. Colloid Interface Sci.* **2020**, *579*, 347–356.

(56) Huo, S.; Zhang, X.; Liang, B.; Zhao, Y.; Li, K. Synthesis of Interconnected Hierarchically Porous Carbon Networks with Excellent Diffusion Ability Based on NaNO<sub>3</sub> Crystal-Assisted Strategy for High Performance Supercapacitors. *J. Power Sources* **2020**, *450* (December 2019), 227612.

(57) Sekhon, S. S.; Park, J. S. Biomass-Derived N-Doped Porous Carbon Nanosheets for Energy Technologies. *Chem. Eng. J.* **2021**, *425* (December 2020), 129017.

(58) Hor, A. A.; Hashmi, S. A. Optimization of Hierarchical Porous Carbon Derived from a Biomass Pollen-Cone as High-Performance Electrodes for Supercapacitors. *Electrochim. Acta* **2020**, *356*, 136826.

(59) Liu, H.; Liu, R.; Xu, C.; Ren, Y.; Tang, D.; Zhang, C.; Li, F.; Wei, X.; Zhang, R. Oxygen–Nitrogen–Sulfur Self-Doping Hierarchical Porous Carbon Derived from Lotus Leaves for High-Performance Supercapacitor Electrodes. *J. Power Sources* **2020**, *479*, 228799.

(60) Zhang, Q.; Han, K.; Li, S.; Li, M.; Li, J.; Ren, K. Synthesis of Garlic Skin-Derived 3D Hierarchical Porous Carbon for High-Performance Supercapacitors. *Nanoscale* **2018**, *10* (5), 2427–2437.

(61) Liu, H.; Gao, F.; Fan, Q.; Wei, C.;

Ma, C.; Shi, J. Preparation of Novel 3D Hierarchical Porous Carbon Membrane as Flexible Free-Standing Electrode for Supercapacitors. *J. Electroanal. Chem.* **2020**, *873*, 114409.

(62) Taer, E.; Taslim, R.; Apriwandi, A. Ultrahigh Capacitive Supercapacitor Derived from Self-Oxygen Doped Biomass-Based 3D Porous Carbon Sources. *ChemNanoMat* **2022**, *8* (2), e202100388.

(63) Sajjad, M.; Khan, M. I.; Cheng, F.; Lu, W. A Review on Selection Criteria of Aqueous Electrolytes Performance Evaluation for Advanced Asymmetric Supercapacitors. *J. Energy Storage* **2021**, *40*, 102729.

(64) Aldama, I.; Barranco, V.; Kunowsky, M.; Ibañez, J.; Rojo, J. M. Contribution of Cations and Anions of Aqueous Electrolytes to the Charge Stored at the Electric Electrolyte/Electrode Interface of Carbon-Based Supercapacitors. *J. Phys. Chem. C* **2017**, *121* (22), 12053–12062.

(65) Selvaraj, A. R.; Muthusamy, A.; Inho-Cho; Kim, H. J.; Senthil, K.; Prabakar, K. Ultrahigh Surface Area Biomass Derived 3D Hierarchical Porous Carbon Nanosheet Electrodes for High Energy Density Supercapacitors. *Carbon N. Y.* **2021**, *174*, 463–474.

(66) Chen, C.; Zhao, M.; Cai, Y.; Zhao, G.; Xie, Y.; Zhang, L.; Zhu, G.; Pan, L. Scalable Synthesis of Strutted Nitrogen Doped Hierarchical Porous Carbon Nanosheets for Supercapacitors with Both High Gravimetric and Volumetric Performances. *Carbon N. Y.* **2021**, *179*, 458–468.

(67) Sangtong, N.; Chaisuwan, T.; Wongkasemjit, S.; Ishida, H.; Redpradit, W.; Seneesrisakul, K.; Thubsuang, U. Ultrahigh-Surface-Area Activated Biocarbon Based on Biomass Residue as a Supercapacitor Electrode Material: Tuning Pore Structure Using Alkalis with Different Atom Sizes. *Microporous Mesoporous Mater.* **2021**, *326* (June), 111383.

(68) Zheng, L. H.; Chen, M. H.; Liang, S. X.; Lü, Q. F. Oxygen-Rich Hierarchical

1  
2  
3 Porous Carbon Derived from Biomass  
4 Waste-Kapok Flower for Supercapacitor  
5 Electrode. *Diam. Relat. Mater.* **2021**, *113*  
6 (January), 108267.

7  
8 (69) Roy, C. K.; Shah, S. S.; Reaz, A. H.;  
9 Sultana, S.; Chowdhury, A. N.; Firoz, S. H.;  
10 Zahir, M. H.; Ahmed Qasem, M. A.; Aziz,  
11 M. A. Preparation of Hierarchical Porous  
12 Activated Carbon from Banana Leaves for  
13 High-Performance Supercapacitor: Effect of  
14 Type of Electrolytes on Performance. *Chem.*  
15 *- An Asian J.* **2021**, *16* (4), 296–308.

16  
17 (70) Taer, E.; Apriwandi, A.; Rama, D.  
18 Solid Coin-like Design Activated Carbon  
19 Nanospheres Derived from Shallot Peel  
20 Precursor for Boosting Supercapacitor  
21 Performance. *J. Mater. Res. Technol.* **2021**,  
22 *15*, 1732–1741.

23  
24 (71) Taer, E.; Natalia, K.; Apriwandi, A.;  
25 Taslim, R.; Agustino, A.; Farma, R. The  
26 Synthesis of Activated Carbon Nano Fiber  
27 Electrode Made from Acacia Leaves  
28 (Acacia Mangium Wild) as Supercapacitors.  
29 *Adv. Nat. Sci. Nanosci. Nanotechnol.* **2020**,  
30 *11* (2), 25007.

31  
32 (72) Yao, Y.; Chen, X.; Yu, N.; Wei, F.;  
33 Feng, H. Preparation and Supercapacitive  
34 Performance of Lead Dioxide Electrodes  
35 with Three-Dimensional Porous Structure.  
36 *Russ. J. Electrochem.* **2018**, *54* (7), 585–  
37 591.  
38  
39  
40  
41  
42  
43  
44  
45  
46  
47  
48  
49  
50  
51  
52  
53  
54  
55  
56  
57  
58  
59  
60



---

**Taslim, Rika ao-2022-04301k - Manuscript Revision Request 19-Aug-2022**

1 message

ACS Omega &lt;onbehalf@manuscriptcentral.com&gt;

Fri, Aug 19, 2022 at 2:42 PM

Reply-To: guo-office@omega.acs.org

To: rikataslim@gmail.com

19-Aug-2022

Journal: ACS Omega

Manuscript ID: ao-2022-04301k

Title: "Novel &lt;i&gt;Moringa oleifera&lt;/i&gt; leaves 3D porous carbon-based electrode material as high performance EDLC supercapacitor"

Author(s): Taslim, Rika; Apriwandi, Apriwandi; Taer, Erman

COVID-19 Support: Please visit the following website to access important information for ACS authors and reviewers during the COVID-19 crisis: <https://axial.acs.org/2020/03/25/chemists-covid-19-coronavirus/>

We are flexible in these unprecedented times affecting the global research community. If you need more time to complete authoring or reviewing tasks, please contact the editorial office and request an extension.

Dear Dr. Taslim:

Thank you for submitting your manuscript to ACS Omega, a multidisciplinary, open access journal for the publication of original and scientifically valid research. The journal offers expedited editorial decision-making and immediate open availability. Authors can rapidly publish their important research results and broadly distribute them to the global scientific community. Please note that there are publishing charges associated with this journal. Details can be found at <http://acsopenscience.org>. Should your manuscript be accepted, you will be required to pay for the Article Publishing Charges prior to publication. Authors may qualify for discounts. Article Publishing Charges are waived for invited Editorials and Perspectives.

"Novel <i>Moringa oleifera</i> leaves 3D porous carbon-based electrode material as high performance EDLC supercapacitor" has been examined by expert reviewers. In its current form, your manuscript is not suitable for publication in ACS Omega. The reviewers have raised points that require significant consideration. However, with an adequate point-by-point response and the appropriate revisions, your paper may become acceptable for publication.

We would like to receive your revision no later than 09-Sep-2022. The revision should address the reviewers' comments and include a point-by-point response. Your manuscript will be subject to further peer review.

Please note that you will receive a follow-up message within 24 hours describing the non-scientific changes you must make to your manuscript before you submit the revision.

To revise your manuscript, log into ACS Paragon Plus with your ACS ID at <http://acsparagonplus.acs.org/> and select "My Authoring Activity". There you will find your manuscript title listed under "Revisions Requested by Editorial Office." Your original files are available to you when you upload your revised manuscript. If you are replacing files, please remove the old version of the file from the manuscript before uploading the new file.

When submitting your revised manuscript through ACS Paragon Plus, you will be able to respond to the comments made by the reviewer(s) in the text box provided or by attaching a file containing your detailed responses to all of the points raised by the reviewers.

Please upload manuscript file that is free of any annotations or highlights.

Funding Sources: Authors are required to report ALL funding sources and grant/award numbers relevant to this manuscript. Enter all sources of funding for ALL authors relevant to this manuscript in BOTH the Open Funder Registry tool in ACS Paragon Plus and in the manuscript to meet this requirement. See [http://pubs.acs.org/page/4authors/funder\\_options.html](http://pubs.acs.org/page/4authors/funder_options.html) for complete instructions.

ORCID: Authors submitting manuscript revisions are required to provide their own validated ORCID iDs before

completing the submission, if an ORCID iD is not already associated with their ACS Paragon Plus user profiles. This iD may be provided during original manuscript submission or when submitting the manuscript revision. You can provide only your own ORCID iD, a unique researcher identifier. If your ORCID iD is not already validated and associated with your ACS Paragon Plus user profile, you may do so by following the ORCID-related links in the Email/Name section of your ACS Paragon Plus account. All authors are encouraged to register for and associate their own ORCID iDs with their ACS Paragon Plus profiles. The ORCID iD will be displayed in the published article for any author on a manuscript who has a validated ORCID iD associated with ACS Paragon Plus when the manuscript is accepted. Learn more at <http://www.orcid.org>.

In publishing only original research, ACS is committed to deterring plagiarism, including self-plagiarism. ACS Publications uses Crossref Similarity Check Powered by iThenticate to screen submitted manuscripts for similarity to published material, and other software to screen previous submissions to ACS journals. Note that your manuscript may be screened during the submission process.

We look forward to seeing your paper in ACS Omega.

Sincerely,

Prof. Shaojun Guo  
Associate Editor  
ACS Omega  
Email: [guo-office@omega.acs.org](mailto:guo-office@omega.acs.org)

-----  
Reviewer(s)' Comments to Author:

Reviewer: 1

Recommendation: Publish after minor revisions.

Comments:

This work reported a novel consolidated carbon disc binder-free electrode for electrochemical double-layer capacitor. The authors studied the influence of physical activation temperatures and three aqueous electrolytes on the supercapacitor performances. After reviewing the manuscript carefully, I suggest the manuscript should be accepted after minor revision, and the comments are as follows:

1. The abstract should be written in the present tense.
2. For MOL600, MOL650, MOL750, and MOL850 carbon disc electrodes, there are many water-insoluble inorganic salts, such as CaCO<sub>3</sub> and ZnO, how does the author remove them from the disc electrodes. If that is the case, the specific surface area and the specific capacitance may not be accurate.
3. How do the oxygen heteroatoms affect the capacitance? Can the author make some discussions about it?
4. There are some format errors, such as 49nm, a space should be added between 49 and nm. The authors should check the grammars and revise them

Additional Questions:

Is the technical quality of the research reported within valid and appropriate?: Yes

Please evaluate the degree of novelty and originality of the research reported: Fair

Are the conclusions adequately supported by the data presented?: Yes

Are the literature references appropriate and up to date?: Yes

Reviewer: 2

Recommendation: Publish after major revisions.

Comments:

In this manuscript, the authors report the biomass-derived activated carbon through pre-carbonization, carbonization and physical activation for supercapacitors. High specific capacitance of 307 F/g is achieved at a current density of 1 A/g in an aqueous electrolyte solution of 1 M H<sub>2</sub>SO<sub>4</sub>. However, some conclusions cannot be fully supported by the presently provided data. Thus I would recommend publication of it if the following questions could be properly addressed.

1. The carbon disc electrodes were prepared in diameter of  $\pm 8$  mm with a thickness of 0.19 mm. How to obtain the electrode with the above size? The authors should clearly point this out in the Experimental section.
2. The density of the MOLs disc is decreased to 0.8280, 0.6500, 0.5600, and 0.6700 g cm<sup>-3</sup> for samples MOL600, MOL650, MOL750, and MOL850. However, the diameter, thickness and average mass for the MOL850 are  $\pm 14.00$ mm,  $\pm 1.2$ mm, and 0.2 g, respectively. The density is calculated to be 1.08 g cm<sup>-3</sup>, which is much different from the value 0.67 g cm<sup>-3</sup>. Thus the authors should double-check all the density values.
3. TEM and HRTEM images of the obtained samples should be provided.
4. Fig. 3 The N<sub>2</sub> absorption/desorption isothermals should be retested to highlight the existence of micropores.
5. Fig. 5c-e The shape of the CV curves at 5 mV/s is obviously different from those at other scan rates. Some reasonable explanations should be provided.
6. For the curves, the unit of current density should be A/g rather than A/cm<sup>2</sup>.
7. The calculation of energy density seems incorrect. The authors should give the calculation equations of specific capacitance and energy density in Experimental section.
8. The specific surface area of the obtained MOL750 is just 412 m<sup>2</sup>/g, however, its specific capacitance is as high as 307 F/g, which seems quite puzzling. How to understand it? Some reasonable explanations should be provided.
9. Since volumetric performance is very important for practical applications (Science 2011, 334, 917-918; Energy Environ. Sci. 2016, 9, 729; etc.), so the authors should calculate the volumetric performances and cite these important references in their manuscript.

Additional Questions:

Is the technical quality of the research reported within valid and appropriate?: Yes

Please evaluate the degree of novelty and originality of the research reported: Fair

Are the conclusions adequately supported by the data presented?: No

Are the literature references appropriate and up to date?: Yes

-----  
FOR ASSISTANCE WITH YOUR MANUSCRIPT SUBMISSION PLEASE CONTACT:  
ACS Publications Customer Services & Information (CSI)  
Email: [support@services.acs.org](mailto:support@services.acs.org)  
Phone: 202-872-4357  
Toll-Free Phone: 800-227-9919 (USA/Canada only)

-----  
PLEASE NOTE: This email message, including any attachments, contains confidential information related to peer review and is intended solely for the personal use of the recipient(s) named above. No part of this communication or any related attachments may be shared with or disclosed to any third party or organization without the explicit prior written consent of the journal Editor and ACS. If the reader of this message is not the intended recipient or is not responsible for delivering it to the intended recipient, you have received this communication in error. Please notify the sender immediately by e-mail, and delete the original message.

As an author or reviewer for ACS Publications, we may send you communications about related journals, topics or products and services from the American Chemical Society. Please email us at [pubs-comms-unsub@acs.org](mailto:pubs-comms-unsub@acs.org) if you do not want to receive these. Note, you will still receive updates about your manuscripts, reviews, or future invitations to review.

Thank you.


This document is confidential and is proprietary to the American Chemical Society and its authors. Do not copy or disclose without written permission. If you have received this item in error, notify the sender and delete all copies.

**Novel *Moringa oleifera* leaves 3D porous carbon-based electrode material as high performance EDLC supercapacitor**

Journal:	ACS Omega
Manuscript ID	ao-2022-04301k.R1
Manuscript Type:	Article
Date Submitted by the Author:	n/a
Complete List of Authors:	Taslim, Rika; State Islamic University Sultan Syarif Kasim, Department of Industrial Engineering Apriwandi, Apriwandi; University of Riau - Bina Widya Campus, Department of Physics Taer, Erman; Universitas Riau - Kampus Binawidja, Department of physics

SCHOLARONE™  
Manuscripts

1  
2  
3  
4  
5  
6  
7  
8  
9  
10  
11  
12  
13  
14  
15  
16  
17  
18  
19  
20  
21  
22  
23  
24  
25  
26  
27  
28  
29  
30  
31  
32  
33  
34  
35  
36  
37  
38  
39  
40  
41  
42  
43  
44  
45  
46  
47

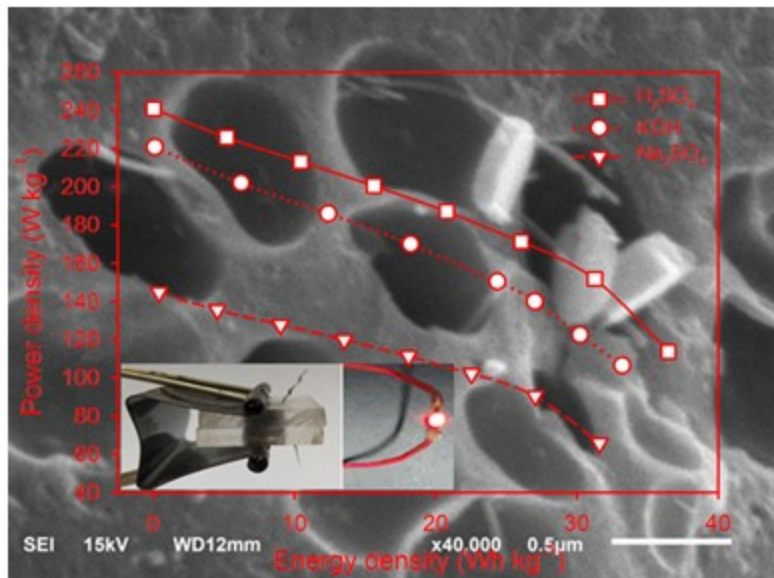

*Moringa oleifera* leaves



# Novel *Moringa oleifera* leaves 3D porous carbon-based electrode material as high performance EDLC supercapacitor

Rika Taslim,<sup>\*[a]</sup> Apriwandi Apriwandi,<sup>[b]</sup> and Erman Taer,<sup>[b]</sup>

<sup>[a]</sup> Department of Industrial Engineering, State Islamic University of Sultan Syarif Kasim, Riau, Simpang Baru-Tampan Pekanbaru, 28293 Indonesia

<sup>[b]</sup> Department of Physics, Faculty of Mathematics and Natural Sciences, University of Riau, Panam, Pekanbaru, 28293 Indonesia

E-mail: [rikataslim@gmail.com](mailto:rikataslim@gmail.com)

**Abstract.** Biomass-based activated carbon has great potential of versatile 3D porous structures as excellent electrode material in presenting high conductivity, large porosity, and outstanding stability for electrochemical energy storage devices. In this study, the electrode material develops through a novel consolidated carbon disc binder-free design, which derived from *Moringa oleifera* leaves (MOLs) for electrochemical double-layer capacitor applications. The carbon discs prepare in a series of treatments of pre-carbonized, chemical impregnation of zinc chloride, and integrated pyrolysis of N<sub>2</sub> carbonization and CO<sub>2</sub> physical activation. The physical activation temperatures apply at 650, 750, and 850°C to optimize the precursor potential. By optimizing the 3D hierarchical pore properties of the MOL750, the carbon disc binder-free design demonstrate optimal symmetric supercapacitor performance with a high specific capacitance of 307 F g<sup>-1</sup> at a current density of 1 A g<sup>-1</sup> in an aqueous electrolyte solution of 1 M H<sub>2</sub>SO<sub>4</sub>. Furthermore, the extremely low internal resistance (0.006Ω) of the carbon disc initiated excellent electrical conductivity. The supercapacitors also maintain their high capacitive properties in aqueous electrolyte solutions of 6 M KOH, and 1 M Na<sub>2</sub>SO<sub>4</sub>, respectively. The results show that a novel consolidate carbon discs binder-free design can be obtained from biomass MOLs through a reasonable approach to develop superior electrode materials to enhance high-performance electrochemical energy storage devices.

## 1. INTRODUCTION

The rapid growth of the world's population with the demands for prosperous life management has made the energy crisis the main global challenge. At the end of 2021, the energy consumption was 4.5% higher than the previous year <sup>1</sup> and is estimated to increase by more than half in the next 4 years <sup>2</sup>. Moreover, approximately 90% of the total energy demand is obtained from coal, which is non-renewable. Studies have shown that the use of coal energy sources causes significant problems in the production of CO<sub>2</sub> emissions and greenhouse gas effects, which leads to global warming and climate change <sup>3</sup>. This makes it necessary to develop effective, efficient, and pollution-free green energy technology and renewable energy conversion

systems. In the past decade, people have focused on abundant, low-cost, safe, and environmentally friendly renewable energy sources such as wind, ocean waves, solar, and biomass. However, their use was limited due to a relatively low supply of technology and complex supporting components. Several developed countries such as China and the United States have implemented renewable energy technologies as alternative sources of energy <sup>4</sup>. This situation led to the development of energy storage systems and devices with high specifications, good stability, low cost, effectiveness, and efficiency to perfect green energy technologies <sup>5,6</sup>. Among the various energy storage technologies investigated, supercapacitors received much attention due to their outstanding power transmission specifications, fast energy storage, infinite cycle stability, high

conductivity, and eco-friendly nature<sup>7-9</sup>. The main key to the superior characteristics of supercapacitor devices is their electrode-based material<sup>10,11</sup>. Various electrode-based materials can produce high and low characteristics of electronic and ionic conductivity. This significantly affects the ability of the electric charge transfusion rate and cyclic resistance of the supercapacitor<sup>12,13</sup>. Therefore, there is a need to design and develop excellent electrode materials for high-performance supercapacitors. In recent years, electrode materials have shown high specifications such as metal oxides, conducting polymers, and carbon materials. The metal oxide materials such as MnO<sub>2</sub>, TiO<sub>2</sub>, and RuO<sub>2</sub> offer high oxidation states for efficient charge transfer during redox reactions, which generate Faradic currents and ion intercalation that favor charge storage, high capacity and conductivity, as well as low toxicity<sup>14-16</sup>. According to Wang *et al.* (2021), the mixed metal oxide material has produced a specific capacitance of 788 F g<sup>-1</sup> with an energy density of 138 Wh kg<sup>-1</sup><sup>17</sup>. Similar results were also confirmed in polymeric materials that produce high energy density<sup>18</sup>. The polymeric materials allow flexible design, which is considered to be more practical, modern, and generally acceptable. The excessive consumption of metal and high-cost polymeric materials with their complicated production methods, low porosity, and corrosive properties significantly increased the risk of mass production and limit their wider application.

Similarly, carbon materials, especially activated carbon, are of greater concern due to their lower production costs, abundant availability, suitable pore structure, and very high porosity properties<sup>7,19</sup>. The biomass-based activated carbon provides a 3D hierarchical pore structure of a combination of micro, meso, and macropores that enable the electrode material to produce high energy and power densities simultaneously<sup>20,21</sup>. Moreover, the self-doping of N/O/P on carbon-based biomass also confirmed their high advantage<sup>22</sup>. Activated carbon from the leaves of *Parthenium hysterophorus* (biomass) has shown a 3D porous structure with a high surface area of 4014 m<sup>2</sup> g<sup>-1</sup> recently, followed by oxygen self-doping<sup>23</sup>. This characteristic has increased the storage capacity of a symmetric supercapacitor to 270 F g<sup>-1</sup>. The adjustable micro:macropores ratio of activated carbon from pecan shells can also produce an extraordinary specific capacitance of 447 F g<sup>-1</sup><sup>24</sup> and display high electrochemical properties with a surface area of 1,785 m<sup>2</sup> g<sup>-1</sup>. This showed that the high surface area does not guarantee the high electrochemical

properties of the supercapacitor. Some suspicions of tuning micro-mesopores, heteroatom self-doping, and the natural conductivity of the materials also contribute to the improvement of their electrochemical properties. Similar results were also obtained from other organic-based activated carbon sources such as wood powders<sup>25</sup>, feather finger grass flower<sup>26</sup>, camellia pollen<sup>27</sup>, and peach gum<sup>28</sup>. Meanwhile, the electrode materials of biomass-based activated carbon possessed energy density disproportionately with their power density and electrical/ionic conductivity far from metal oxide materials and conducting polymer due to high porosity, which hinders their practical application. Therefore, it is necessary to design a biomass-based porous carbon with a novel, easy, inexpensive, and approach for environmentally friendly, pollution-free, and high-performance supercapacitors.


Therefore, this study aims to develop a novel electrode material design from *Moringa oleifera* leaves biomass-based consolidated solid carbon discs to increase the storage capacity of symmetric supercapacitor devices. The proposed carbon discs are prepared binder-free, whose treatment consists of pre-carbonization, chemical impregnation (ZnCl<sub>2</sub>), and integrated pyrolysis of N<sub>2</sub> carbonization and physical activation of CO<sub>2</sub>. The potential for activated carbon precursors was also maximized through different pyrolysis temperatures 650, 750, and 850°C. Moreover, the carbon discs of MOLs exhibit 3D hierarchical pore properties with oxygen heteroatoms as their additional oxidative property. The optimized carbon disc exhibits a high specific capacitance of 307 F g<sup>-1</sup> in the 1 M H<sub>2</sub>SO<sub>4</sub> electrolyte. This showed that the proposed design is a reasonable approach to increase the symmetric storage capacity of pollution-free, low-cost, and high-performance supercapacitors.

## 2. RESULTS AND DISCUSSION

### 2.1. Material analysis

Density analysis is an important aspect for the evaluation of carbon MOLs in form of binder-free consolidated discs. This section shows the analysis of changes in the density of the carbon discs of MOLs at different temperatures of pyrolysis treatments. The precursor powder pressed at a predetermined load was properly compacted at a diameter of ±19.00 mm, a thickness of ±2.00 mm, and a mass of ±0.70 gr (see Figure 1a). The potential precursors of the confirmed MOLs formed a strong/resistant and a fracture-free consolidated disc with a smooth surface. Their biological composition and complex compounds can act as

self-adhesives to enable the formation of binder-free strong discs.

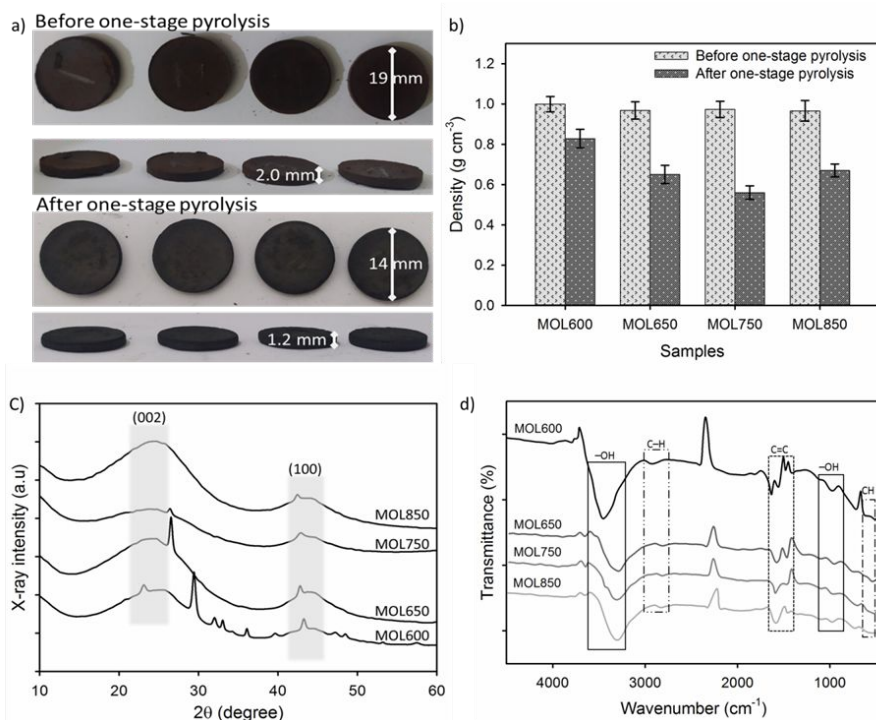

**Figure 1.** a) Dimensions of binder-free consolidated discs before and after pyrolysis, b) Changes in the density of the carbon discs of MOLs at different temperatures of pyrolysis treatments, c) XRD pattern of MOLs disc at different pyrolysis temperatures, and d) FTIR spectrum of the MOLs carbon disc at a wavenumber of 4500-450 cm<sup>-1</sup>.

A similar case was also stated in a previous study using banana leaves as a precursor<sup>29</sup>. In this study, the average densities of the samples MOL600, MOL650, MOL750, and MOL850 were 0.9990, 0.9680, 0.9730, and 0.9660 g cm<sup>-3</sup>, respectively. The discs of consolidated MOLs were pyrolyzed at high temperatures, including carbonization in an N<sub>2</sub> gas environment and physical activation in a CO<sub>2</sub> gas environment and their final process was evaluated for overall dimensional changes<sup>30</sup>. As shown in Figure 1b, the disc density of the consolidated MOLs degraded significantly after the high-temperature pyrolysis process due to a significantly large mass loss. Pyrolysis initiated from 30°C to 850°C for over 10 hours significantly degraded the disc dimensions, where their diameter, thickness, and average mass were reduced to ±14.00-13.00mm, ±1.2-1.0mm, and 0.2-0.1 gr, respectively. After the pyrolysis process, the MOLs disc density decreased to 0.8280, 0.6500, 0.5600, and 0.6700 g cm<sup>-3</sup> for samples MOL600, MOL650, MOL750, and MOL850, respectively.

The evaporation of volatile compounds, water content, and decomposition of the biological composition of the precursor during the chemical reaction of ZnCl<sub>2</sub> at high-pyrolysis temperature caused the reduction of the density of MOLs discs. Furthermore, the physical appearance of the disc

sample is relatively solid black, which indicated a high fixed carbon content. The 42.44% density degradation initiated the formation of a diverse pore framework which is needed as a good electrode material for electrochemical energy storage devices. The different pyrolysis temperatures from 600°C to 750°C affect their respective densities by degrading the MOLs disc density to 32.36%. This is due to the erosion of the carbon framework which causes the expansion of larger pores and initiates the formation of macropores within the micron scale. From the pyrolysis temperature of 750°C to 850°C, the density of the disc increased by 16.41% due to excessive erosion of the carbon pore walls. This makes the carbon skeleton unable to maintain the structure above, thereby, it collapsed and covered the pores below. However, these results are relatively normal for solid carbon samples.

The material structure of the carbon disc MOLs was evaluated through X-ray diffraction (XRD) and Fourier transforms infrared (FTIR) techniques. Figure 1c shows the XRD pattern of disc MOLs at different pyrolysis temperatures of 600, 650, 750, and 850°C. The carbon discs showed strong broad peaks at angles 24° and 44° correlated with the (002) and (100) scattering planes, which confirmed the turbostratic carbon structure (JCPDS No. 29-1126, 29-1127)<sup>31</sup>. The high-temperature pyrolysis



of the precursor MOLs allows the decomposition and rearrangement of the carbon structure to initiate good amorphous behavior<sup>32</sup>.

**Table 1.** Microcrystalline parameters and elemental status of MOLs carbon disc at different physical activation temperature.

Carbon disc MOLs	Microcrystalline parameters				Elemental status				
	$d_{002}$ (Å)	$d_{100}$ (Å)	$L_c$ (Å)	$L_a$ (Å)	C (%)	O (%)	Ca (%)	Cl (%)	Zn (%)
MOL600	3.524	2.077	13.391	22.159	79.45	17.41	2.28	0.87	0.00
MOL650	3.616	2.051	12.297	16.903	85.97	10.49	0.63	0.68	2.24
MOL750	3.698	1.994	7.481	23.866	88.54	8.06	1.11	0.64	1.65
MOL750	3.689	1.993	10.323	18.144	88.91	8.45	1.38	0.60	0.66

Furthermore, the properties of the carbon disc structure of MOLs changed during the high-temperature pyrolysis process including carbonization and physical activation. The hkl (002) plane possesses broad peak attenuation from 600 to 850°C, which significantly reduced the crystalline properties and initiate the formation of abundant micro-mesoporosity<sup>33</sup>. This property improves the electro-active site of the electrode material in energy storage systems. Meanwhile, the sharp peaks in the sample were significantly reduced from 600 to 850°C, indicating the presence of a small amount of crystal structure of the compound CaCO<sub>3</sub> and ZnO at angles of 23°, 26°, 29°, 32°, 36°, and 43°.

These compounds are the contribution of organic precursor components and by-products of their chemical impregnation. The CaCO<sub>3</sub> compound is located at an angle of 23.165°, 29.255°, 32.050°, 36.095° (JCPDS No. 06-0230) and the ZnO compound in very small amounts at 26.05°-26.395° (JCPDF No. 36-1451)<sup>34,35</sup>. The MOLs600 sample that was carbonized at 600°C produced an XRD pattern, containing several CaCO<sub>3</sub> crystalline compounds. The application of physical activation in the CO<sub>2</sub> gas environment reduced the CaCO<sub>3</sub> compounds as shown in MOLs650, MOLs750, and MOLs850, as described EDS technique in Table 1. Moreover, high-temperature pyrolysis obtains carbon discs with a well amorphous structure. Table 1 summarizes the interlayer spacing and microcrystalline dimensions of the MOLs carbon discs at pyrolysis temperatures ranging from 600 to 850°C. The value of  $d_{(002)}$  of MOLs is slightly higher than  $d_{(002)}$  of graphite by approximately 3.46%, while  $d_{(100)}$  indicates a relatively ideal for

amorphous carbon-based biomass as stated in previous studies<sup>36,37</sup>. Furthermore, the microcrystalline dimension ( $L_c$ ) is closely related to the specific surface area and the active channel on the electrode material, which is often related through empirical equations<sup>38,39</sup>. Based on this empirical equation,  $L_c$  showed that the specific surface area inversely, where a low  $L_c$  allows the electrode disc to obtain a high surface area. From Table 1, the carbon discs pyrolyzed at 750°C temperature showed higher surface area than others.


Figure 1d shows the FTIR spectrum of the carbon disc MOLs at a wavenumber of 4500-450 cm<sup>-1</sup>. Generally, different pyrolysis temperatures, namely 600, 650, 750, and 850°C of the MOLs precursors exhibited stretching vibrations of -OH, C-H, C=C, C-O, CH<sub>2</sub>, and C-H aromatics<sup>40,41</sup>. This functional group is considered normal for porous activated carbon based on organic waste. The carbon discs pyrolyzed at 600°C (carbonization only) showed significant absorption at several wavenumbers compared to higher temperatures. Furthermore, the highest absorption was discovered in the band 3,463-3,309 cm<sup>-1</sup> due to stretching vibration of -OH<sup>42</sup>, which was also discovered in wavenumber 1,491-1,422 cm<sup>-1</sup>. Stretching vibration of C-H was indicated at wavenumbers 2,926 cm<sup>-1</sup> and 978 cm<sup>-1</sup>, while 1,652 cm<sup>-1</sup> and 1,553 cm<sup>-1</sup> were the stretching vibrations of C=C. Meanwhile, the absorption band in the range 1,300-1,010 cm<sup>-1</sup> represents the C-O functional group, while CH aromatic is were in the 770-709 cm<sup>-1</sup> and 540-518 cm<sup>-1</sup><sup>43</sup>. The abundance of C and O in this functional group indicates their relatively high content in carbon disc MOLs as shown in Table 1. At higher temperatures, the pyrolysis of

MOL650, MOLs750, and MOL850 integrated with the one-stage carbonization and physical activation process showed relatively different absorption patterns. The stretching vibrations of C-O and -OH decreased significantly at MOL650, MOL750, and MOL850, as shown in the absorption bands of 3,400-3,300  $\text{cm}^{-1}$  and 1,300-1,010  $\text{cm}^{-1}$ . This is due to the physical activation in the  $\text{CO}_2$  gas environment treatment, maximizing the evaporation process of organic compounds and rearranges the carbon framework, thereby, possessing FTIR spectra that are nearly ideal for porous activated carbon. Meanwhile, MOL750 showed the lowest absorption band, followed by the removal of some absorbance, especially on stretching vibration of C-O and CH aromatic<sup>40,43</sup>. This indicated that the FTIR spectra obtained are the most ideal compared to the others. The presence of a relatively confirmed -OH functional group provides wettability and hydrophilicity properties for the electrode material<sup>44,45</sup>. This property is used as a heteroatom to increase the effect of extra pseudo-capacitance in electrochemical energy storage devices. Similar results were also shown by EDS and electrochemical properties analyses.

The energy dispersive spectroscopy (EDS) was carried out at a voltage of 15.0kV within the energy range of 0-20.0 keV to analyze the elements of consolidated carbon discs MOLs that were pyrolyzed at high temperature. Meanwhile, the details elemental status of the carbon disc MOLs is summarized in Table 1. It was shown that carbon (C) is the component of the highest consolidated disc with approximately 79-89% and oxygen (O) heteroatoms 8-17%, followed by other elements in very small amounts such as potassium (Ca), chlorine (Cl), and zinc (Zn). These results are in line with the previously discussed XRD and FTIR analyzes. The carbonization process at 600°C in the  $\text{N}_2$  atmosphere significantly obtained high pure carbon of 79.45%. This

also supported the density analysis where volatile, water content, complex organic compounds evaporated and degraded. However, as a by-product, they still leave oxygen in form of an oxide compound of 17.41%. An increase in the pyrolysis temperature on physical activation using  $\text{CO}_2$  increased the elemental carbon by 88.91% at MOL850, while the elemental oxygen is reduced regularly and remains 8.06% at MOLs750. The element Zn appears because the byproduct of chemical impregnation  $\text{ZnCl}_2$  is not completely evaporated. Meanwhile, the elements Ca and Cl are the contributions of the organic components of the precursor MOLs. The high pure carbon element obtained in the consolidated disc MOLs also allows the electrode material to have high conductivity properties to boost the electrochemical behavior of the supercapacitor<sup>46</sup>. The elemental oxygen can also contribute to self-heteroatom and provide additional pseudo-capacitance to the disc carbon-based electrode material of consolidated MOLs.


The morphological structures of the obtained consolidated MOL carbon discs were reviewed by scanning electron microscopy (SEM) as shown in Figure 2. Binder-free carbon discs pyrolyzed using 600-850°C different temperatures exhibited a 3D connected pore-rich surface structure. Precursor MOLs that were impregnated with  $\text{ZnCl}_2$  at 600°C showed a smooth surface with clear micron-scale pore channels. In the selected area, MOL600 maintains the natural pore structure of MOLs at the nano and micro scale. The pores obtained were dominated by mesopores in the 23-46 nm range and rich in micropores. Furthermore, the  $\text{ZnCl}_2$  impregnation maximizes the potential of MOLs precursors to provide rich pores through evaporation and gradation of their organic compounds<sup>47</sup>. Figure 2b confirms the mesoporous rich structure in the range of 24 to 49 nm and macropores in the 100 nm scale.

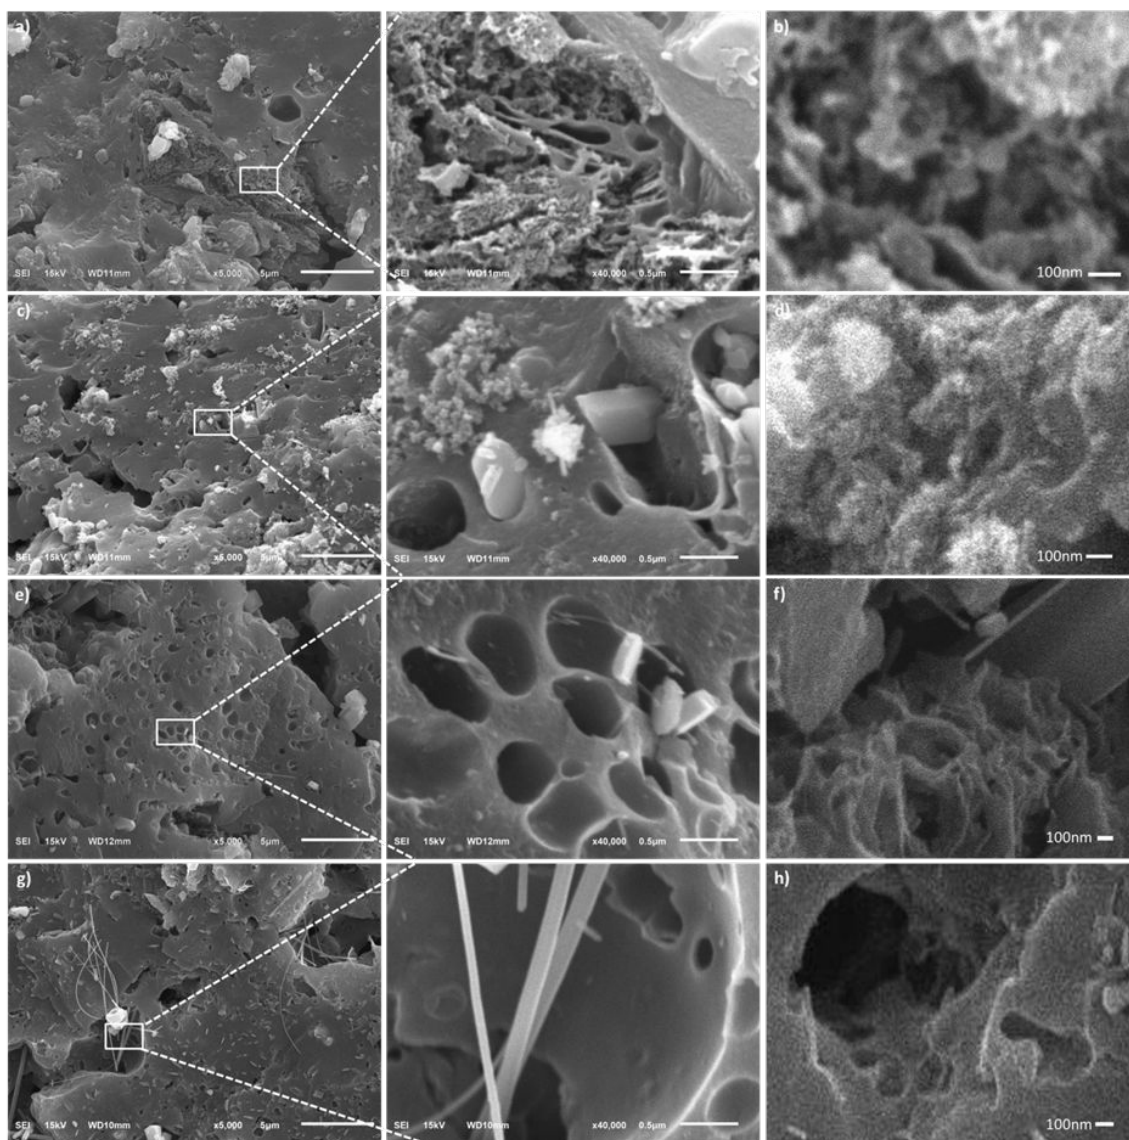

**Figure 2.** SEM image of (a) MOL600, (b) MOL600 at closer zoom, (c) MOL650, (d) MOL650 at closer zoom, (e) MOL7500, (f) MOL600 at closer zoom, (g) MOL850, and (h) MOL850 at closer zoom.

This is useful as an electrolyte reservoir in the electrochemistry of supercapacitors<sup>48</sup>. When the pyrolysis temperature was increased to 650°C in the CO<sub>2</sub> physical activation process, the surface structure was decorated with holes in the diameter which ranged from 65 nm to 1,261 nm as shown in Figure 2c. The physical activation of CO<sub>2</sub> significantly grows the rich macropores by grinding the carbon skeleton, which is released in form of CO, H<sub>2</sub>O, and CO<sub>2</sub><sup>49</sup>. Through a closer zoom, SEM micrographs confirmed the presence of multiple pores connected in 3D hierarchies, where the


macropore walls contain mesopores in small numbers. Figure 2d also shows the expansion of the pores towards a larger direction due to high-temperature carbon skeleton grinding compared to Figure 2b. Meanwhile, increasing the pyrolysis temperature to a higher at 750°C allows MOLs750 to have abundant pores as shown in Figure 2e. The various pore structures obtained range from 500-900 nm. Figure 2f shows morphology 3D carbon foam-like interconnected by thin sheet-like struts and open pores with a diameter of several tens of nanometers.

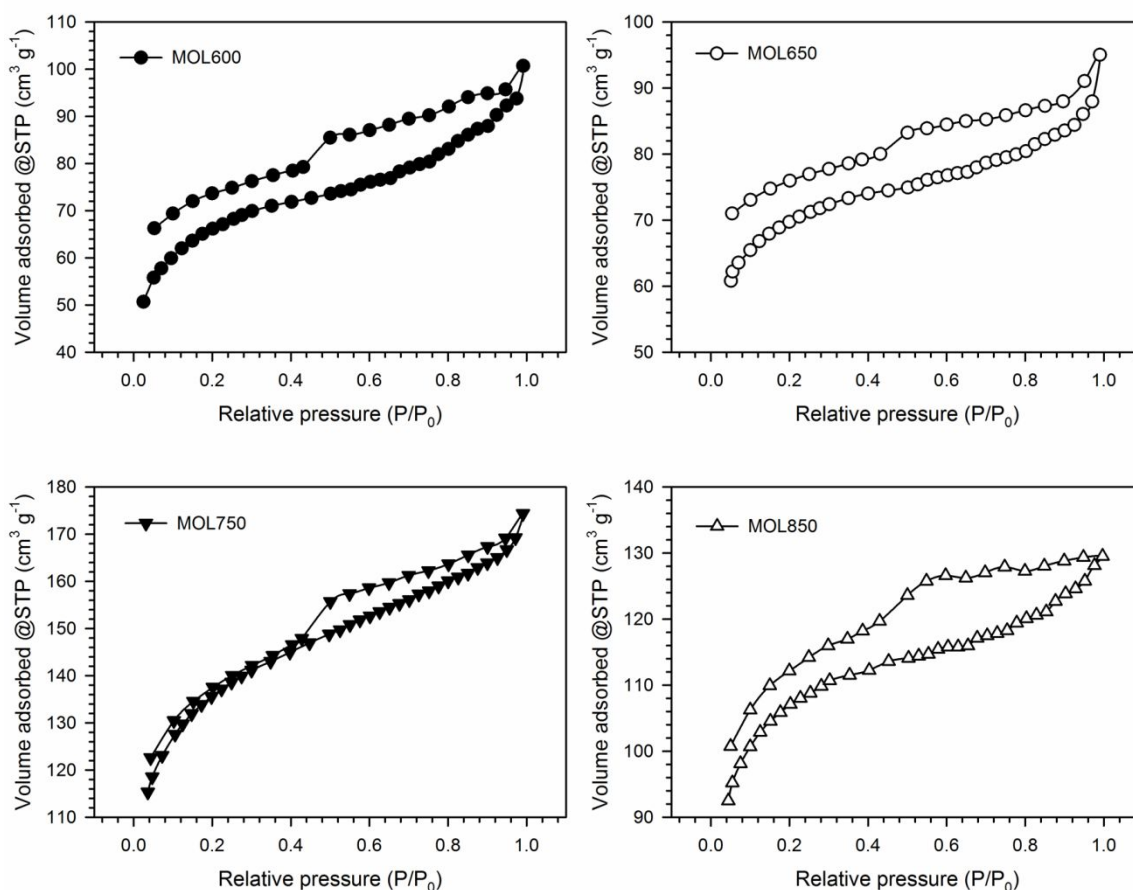

**Figure 3.**  $N_2$  gas absorption profiles of the MOLs carbon disc.

This pore structure significantly contributes to an increase in the amount of ionic charge transfer and electro-active activity in the MOLs of the electrode material<sup>50</sup>. These morphological properties are expected to cause high capacitive properties with greater energy density and power in symmetric supercapacitor devices. Increasing the pyrolysis temperature to 850°C at MOL850 led to a more severe etching of the carbon matrix, causing considerable pore dilation. Subsequently, the 3D hierarchical porous structure becomes visible as shown in Figure 2g and their magnification selected area. Moreover, MOL850 exhibits a 2D nanofiber structure at a diameter of approximately 73-188nm, which can lead to the distribution of micropores on their surface. Figure 4h shows the abundant 3D pore morphology connected hierarchically between mesopores and macropores. The analysis showed that

increasing the pyrolysis temperature etches the carbon framework giving rise to a 3D porous carbon framework connected to nanoscale 2D nanosheets and nanofibers on MOLs carbon discs. These results indicated that the proposed approach can significantly increase the proportion of hierarchically connected mesopores/macropores in carbon MOLs. Therefore, excellent material properties can be achieved to improve the performance of electrode materials in electrochemical energy storage devices. A more detailed analysis of the pore structure was confirmed through the  $N_2$  adsorption-desorption isotherm characterization. The MOLs carbon discs obtained from the integrated single-stage pyrolysis process at different temperatures of 600-850°C have type  $N_2$  gas absorption profiles as shown in Figure 3.

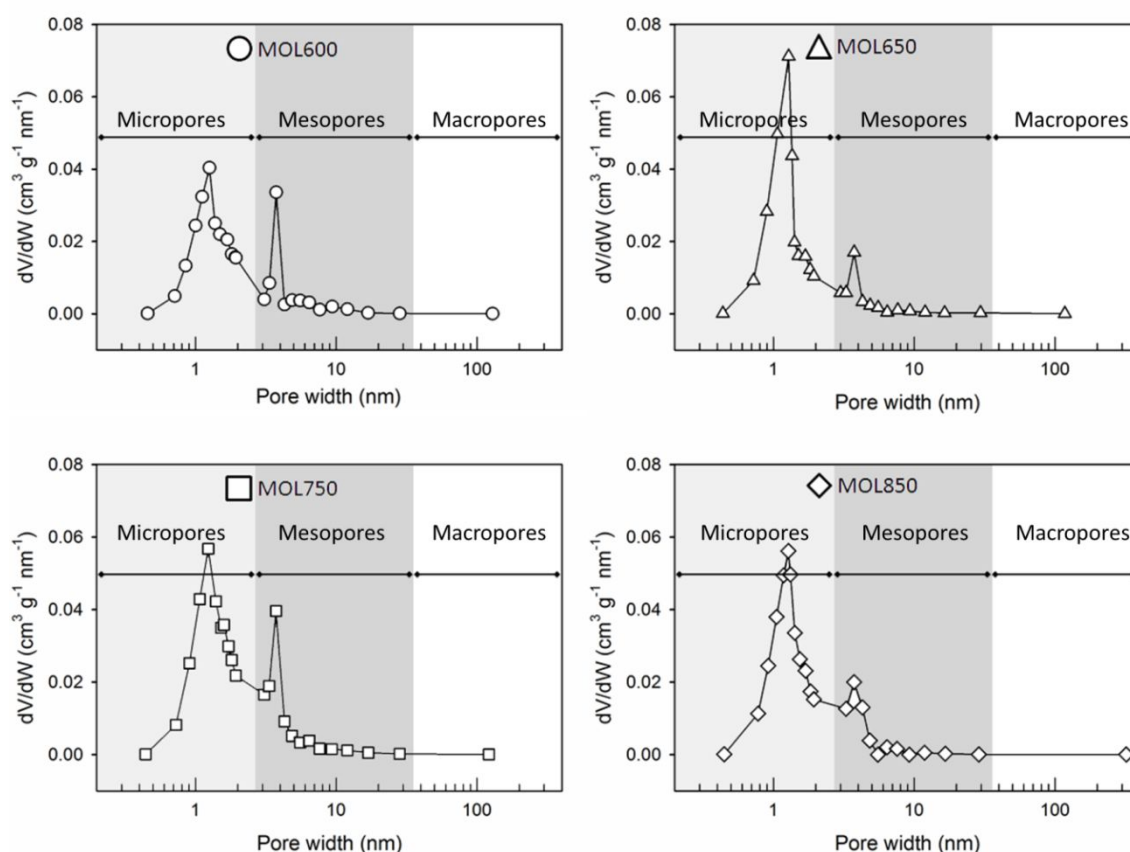


**Figure 4.** Pore size distribution of the MOLs carbon discs.

The MOL600 carbon discs obtained by carbonization at 600 temperatures have the lowest isotherm curve with mixed types I and IV. This confirmed a low specific surface area of  $207 \text{ m}^2 \text{ g}^{-1}$  with micro and mesopore structures at a ratio of 65.30% and 34.70%, respectively. After the physical activation of  $\text{CO}_2$  on MOL650, MOL750, and MOL850 carbon discs, the absorption curve regularly increased. This indicated higher pore properties and specific surface areas that exhibit mixed type I and IV isotherm curves with an H4 type hysteresis loop. It also showed a hierarchical pore combination of micropores and mesopores that are connected<sup>51,52</sup>. Furthermore, the hysteresis loops are open due to the physical structure of the imperfectly developed pores, where their upper surface is smaller than the inner structure and is usually called a bottleneck pore in several studies<sup>36</sup>. Increasing the physical activation temperature from 650 to  $750^\circ\text{C}$  can

significantly increase the specific surface area by approximately 2 times from  $211 \text{ m}^2 \text{ g}^{-1}$  to  $412 \text{ m}^2 \text{ g}^{-1}$ . The distribution of their micro and meso surface areas also changes, which affects the electro-active properties of the electrode material. Abundant micropores promote the material by providing rich channels for ion adsorption, which create an electrical layer, while high mesopores contribute to increased barrier-free charge flow<sup>53,54</sup>. Moreover, MOLs750 indicated the presence of a macropore structure in small amounts as shown by an increase in uptake at a relative pressure of  $0.95 \leq P/P_0 \leq 1.0$ . The macropore structure can also act as a reservoir for electrolyte ions after the confirmation of the electrochemical properties of the supercapacitor<sup>55</sup>, which is in line with the SEM analysis as shown in Figure 2. The complete combination of micro, meso, and macroporous structures in MOL750 is expected to increase the high performance of MOLs precursor-based

supercapacitors. An increase in the physical activation temperature to approximately 850°C in the MOL850 samples exhibited a reduction in N<sub>2</sub> gas uptake with their specific surface area of about 322 m<sup>2</sup> g<sup>-1</sup>. There is a possibility that the overgrowth of

the pores prevents their walls from maintaining the carbon skeleton for the top to collapse and cover the pores below. The pore structure parameters are shown in Table 2, while the pore size distribution of the MOLs carbon discs is shown in Figure 4.

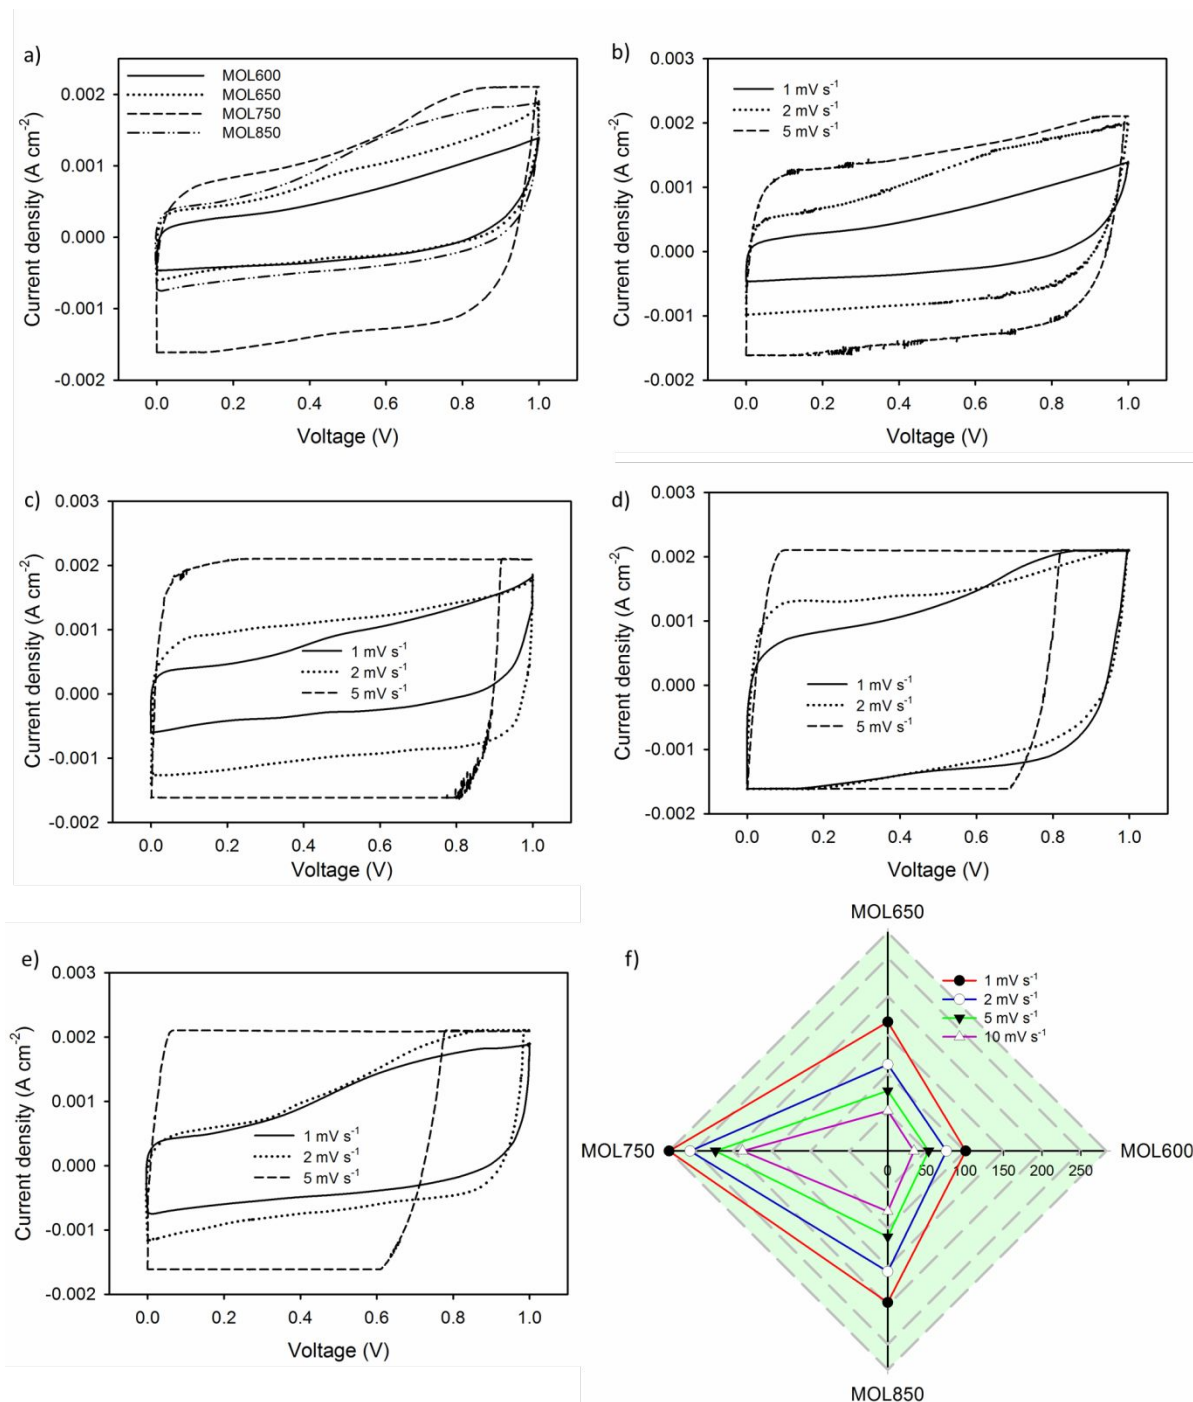

**Figure 5.** a) CV curve of the MOLs carbon disc at a scan rate of 1 mV s<sup>-1</sup>, b)-e) CV curve in different scan rate of MOL600, MOL650, MOL750, and MOL850, and f) capacitive performance of carbon MOLs in different scan rate in 1M H<sub>2</sub>SO<sub>4</sub> electrolyte.

The pyrolyzed carbon disc MOLs at different temperatures showed an abundant pore distribution of micropores ( $x \leq 2$  nm), which is rich in mesopores ( $2 \leq x \leq 18$  nm). Carbonized discs at 600°C temperatures gave a relatively balanced micro-mesopores distribution with an average pore diameter of 3.0 nm. The physical activation treatment of CO<sub>2</sub> at a temperature of 650-850°C also gave abundant micropores, which were dominated by 1.7 nm micropores. In addition, this treatment reduced the mean pore diameter to approximately 2.4 nm as shown in Table 2. These results confirm the formation of a hierarchical pore structure that develops more conducive to charge/ion storage at the electrode/electrolyte interface<sup>56,57</sup>. Furthermore, the physical activation of CO<sub>2</sub> at different temperatures indicated that the hierarchical pore structure varied in the pore ranging from 1.4 to 2.7 nm. The potential for MOLs precursors was also confirmed to obtain 3D hierarchical porous carbon discs.


**Table 2.** Porosity properties of MOLs

Carbon samples	S <sub>BET</sub> (m <sup>2</sup> g <sup>-1</sup> )	S <sub>micro</sub> (m <sup>2</sup> g <sup>-1</sup> )	S <sub>meso</sub> (m <sup>2</sup> g <sup>-1</sup> )	V <sub>tot</sub> (cm <sup>3</sup> g <sup>-1</sup> )	D <sub>aver</sub> (nm)
MOL600	207.482	135.500	71.982	0.1558	3.0
MOL650	211.334	165.167	46.167	0.1470	2.7
MOL750	412.196	313.343	98.853	0.2697	2.6
MOL850	322.008	264.035	57.973	0.2004	2.4

## 2.2. Electrochemical performance analysis

The electro-active interactions of ionic charge and carbon-based MOLs electrodes were reviewed in detail through cyclic voltammetry (CV) and galvanostatic charge-discharge (GCD) in a two-electrode system in 1 M H<sub>2</sub>SO<sub>4</sub> electrolyte. Figure 5a shows the CV curve of the carbon disc MOLs at a scan rate of 1 mV s<sup>-1</sup>, showing a nearly perfect rectangular shape in a potential window of 0 to 1 V. This showed the electro-active properties of the normal electrically double-layered carbon disc MOLs. Furthermore, the spike in current density in the potential window of 0.4 to 0.6 V characterizes the additional pseudocapacitance due to the contribution of the

heteroatoms as self-doping<sup>58</sup>. It was also discovered that the highest specific capacitance was in the MOL750 carbon disc of 283 F g<sup>-1</sup>, characterized by the largest rectangular shape, while the lowest capacitance was in MOL600 of 101 F g<sup>-1</sup>. The CV curve of MOL650 shows a rectangular shape that is larger than MOL600. This indicated that the CO<sub>2</sub> physical activation treatment can significantly increase the capacitive properties of MOL650 discs to approximately 196 F g<sup>-1</sup>. The physical activation of CO<sub>2</sub> can significantly maximize the impurity evaporation process, thereby, initiating the formation of a rich micro-mesopore structure, which allows more ions to diffuse at the electrolyte/electrode interface.

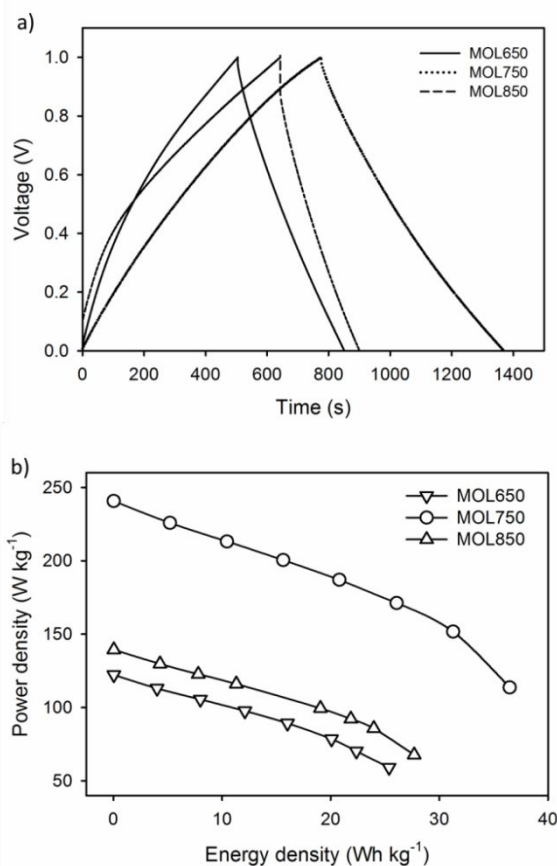


**Figure 6.** a) GCD curves of the disc electrode MOLs in 1M H<sub>2</sub>SO<sub>4</sub> electrolyte, and b) Ragone plot of the disc electrode MOLs in 1 M H<sub>2</sub>SO<sub>4</sub> electrolyte.

The application of a higher activation temperature can maximize the potential of

1  
2  
3 the MOL750 carbon disc also confirmed the  
4 greatest capacitive properties. This is  
5 contributed by their compactly consolidated  
6 material structure with a 3D hierarchical  
7 structure, followed by an increase in specific  
8 surface area. However, the addition of a  
9 higher temperature to 850°C reduces the  
10 specific capacitance to 211 F g<sup>-1</sup>. This is  
11 because the intense pore expansion can  
12 reduce their surface area as shown in Figure  
13 3 and Table 1, which reduced the  
14 electrochemical properties of MOL850. The  
15 carbon discs MOL600, MOLs650,  
16 MOLs750, MOL850 were evaluated at  
17 various scanning levels as shown in Figure  
18 5b-e to confirm the effect of pores on the  
19 performance of the electrode material. It was  
20 also discovered that the curve presents a  
21 wide rectangular distortion at a scanning  
22 speed of 2-5 mV s<sup>-1</sup>, which shows a good  
23 EDLC performance. The pseudo-  
24 capacitance property was not confirmed at  
25 the scanning levels of 2 and 5 mV s<sup>-1</sup>,  
26 therefore, it can be speculated that the  
27 electrode material has a weak heteroatom  
28 self-doping<sup>59</sup>. Furthermore, at 5 mV s<sup>-1</sup>, CV  
29 curves are obviously different with a  
30 significant increase in current followed by  
31 an unusual shape indicated due to their  
32 relatively low pore structure. This is  
33 confirmed similar to the previous study<sup>31,60</sup>.  
34 Moreover, the higher scan rate also confirms  
35 the performance of the capacitive properties  
36 of carbon MOLs as shown in Figure 5f. The  
37 scan rate treatment of 1 to 10 mV s<sup>-1</sup>  
38 significantly reduced the specific  
39 capacitance caused by their pore size  
40 distribution. However, the MOLs750 carbon  
41 disc was able to maintain a specific  
42 capacitance of 78% at a scan rate of 10 mV  
43 s<sup>-1</sup>. Figure 6a shows the GCD curves of the  
44 disc electrode MOLs at higher physical  
45 activation temperatures of 650, 750, and  
46 850°C in a current density of 1 A g<sup>-1</sup>. It also  
47 showed a distorted isosceles triangle shape,  
48 which indicated the nature of the ideal  
49 electric double layer. Furthermore, the iR  
50 drop on the barely visible curve indicates  
51 low ion diffusion resistance<sup>61</sup>. Their charge  
52 times, which were greater than discharge

times indicated ion degradation due to the  
presence of self-doping heteroatoms  
associated with the redox reactions of  
oxygenated surface functions in the aqueous  
electrolyte of 1 M H<sub>2</sub>SO<sub>4</sub><sup>22,62</sup>. This is  
supported by the high level of oxygen in the  
MOLs carbon disc of approximately  
8.06–17.41%. The long charge-discharge  
time of the MOLs disc electrodes  
characterizes the increase in specific  
capacitance after the CO<sub>2</sub> physical activation  
process at temperatures of 650, 750, and  
850°C. The MOLs750 disc electrodes  
exhibited the longest discharge time,  
showing that their highest capacitance was  
307 F g<sup>-1</sup>, followed by MOLs850 and  
MOLs650 221 and 156 F g<sup>-1</sup>, respectively.  
This is directly affected by the increase in  
surface area and accessible pore volume in  
the carbon disc MOLs, which are required  
for electrolytic ion charge accumulation and  
fast unimpeded transport. The physical  
activation at a high temperature can  
significantly increase the specific surface  
area, followed by an increase in the total  
pore volume and their pore size distribution,  
which is rich in 3D micro-mesopores<sup>54,63</sup>.  
The results also showed that MOLs carbon  
discs have the highest specific surface area  
of 433 m<sup>2</sup> g<sup>-1</sup> with a maximum total volume  
of 0.244 cm<sup>3</sup> g<sup>-1</sup>. This allows them to have a  
high accumulation of electrolyte ions,  
thereby, forming more electro-active layers.  
The hierarchically connected 3D rich  
mesopores structure of MOLs750 confirms  
their almost unimpeded access to ion  
transport and the range of diffusion in all  
directions acting as a reservoir for  
electrolyte ions<sup>64</sup>. This can significantly  
improve the capacitive properties of the  
MOLs carbon electrodes as shown in the  
MOLs650 to MOLs750 electrodes. An  
increase in temperature to approximately  
850°C at the MOLs850 carbon disc reduced  
its capacitive properties as shown by  
excessive pore expansion. This can cause  
the pore framework to collapse and cover  
the hierarchical pores below, which reduced  
their surface area and pore volume (Table  
1).



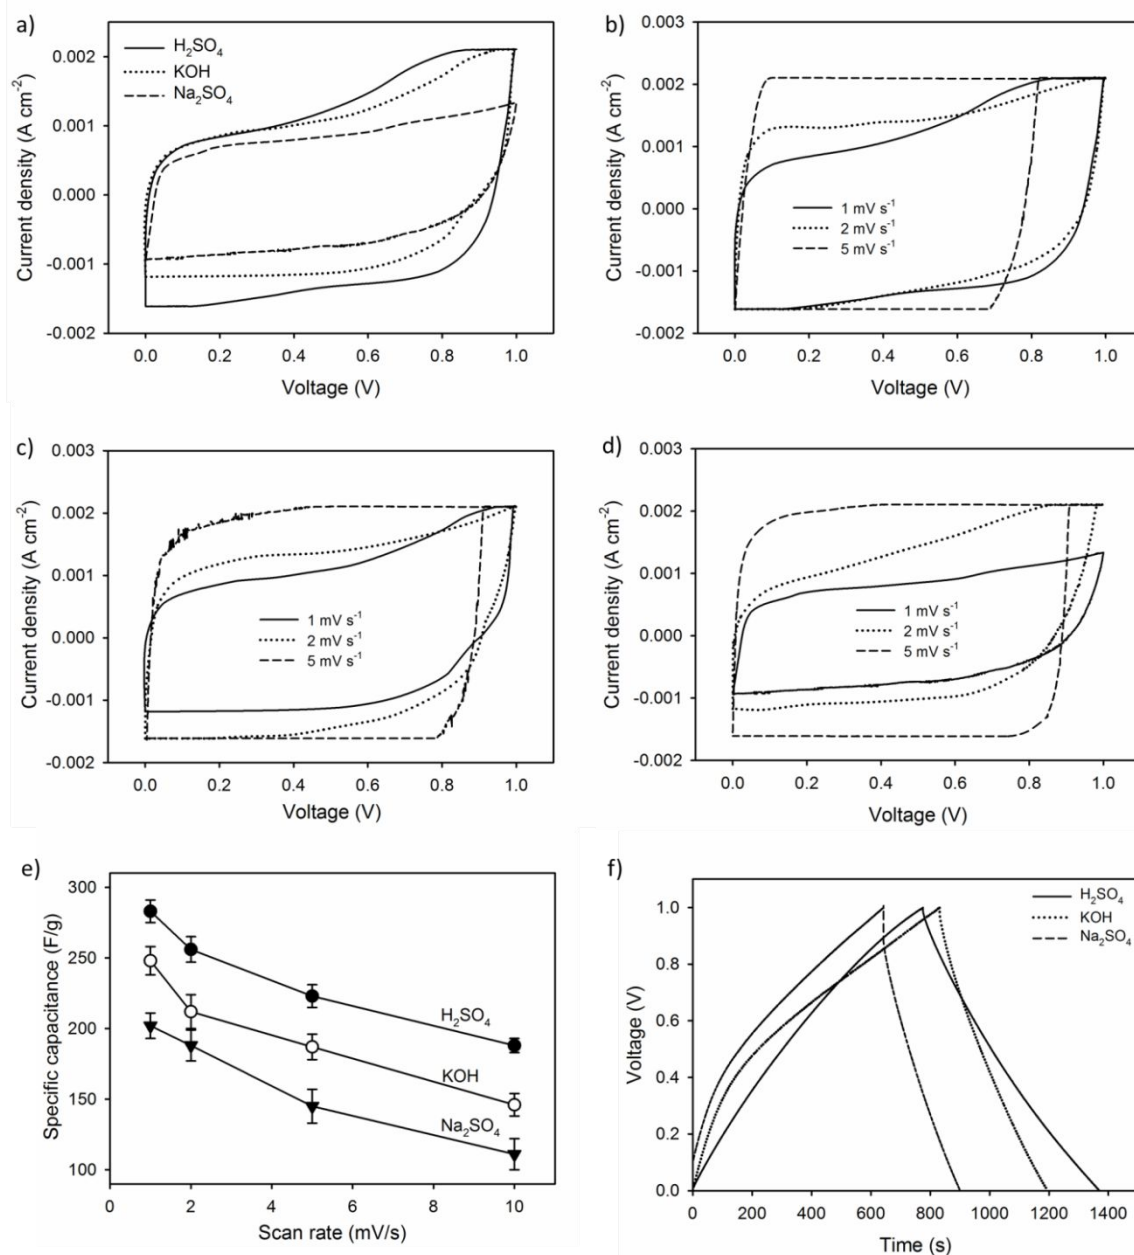

**Figure 7.** a) CV curve of the MOLs750 carbon in different aqueous electrolytes, b)-d) Improved CV scanning was also applied to MOLs750 in different aqueous electrolytes, e) capacitive performance of carbon MOLs in different scan rate in different aqueous electrolytes, and f) GCD curve of the MOLs750 carbon in different aqueous electrolytes.

However, the GCD curve of MOLs750 has the least symmetrical isosceles triangle shape due to the pseudo-capacitance effect of oxygen heteroatoms<sup>17,50</sup>. The results obtained from GCD are very similar to SEM, EDS, N<sub>2</sub> adsorption/desorption, and CV images. The Ragone plots confirm the energy and power densities of the MOL650,

MOL750, and MOL850 disc electrodes as shown in Figure 6b. Meanwhile, the Ragone plot tends to show that the energy density rises as the physical activation temperature increases at high power density. The MOL650 disc electrode produces an energy density of 25.37 Wh kg<sup>-1</sup> at a power density of 122.25 W kg<sup>-1</sup>. An increase in the

physical activation temperature on the MOL750 carbon disc gave the most significant energy density of 36.47 Wh kg<sup>-1</sup> at a power density of 240.73 W kg<sup>-1</sup> due to the contribution of hierarchically connected 3D micro-mesopores, specific surface area, and self-doping heteroatom. The MOLs850 disc electrode shows an energy density of 27.6876 Wh kg<sup>-1</sup> with a power density of almost 139.4286 W kg<sup>-1</sup>. These results indicated that the disc electrode MOLs can produce high properties for electrochemical

energy storage applications. Although the specific surface area of MOL750 is not very high, it can have extraordinary energy density and compete with other studies as summarized in Table 3. This is due to the efficiency of the electrode material designed as solid consolidated carbon discs, which optimized 3D hierarchical pores leading to low internal resistance, high conductivity, and producing high electrochemical performance<sup>26,27</sup>.

**Table 3.** Electrochemical performance of MOLs carbon disc in CV and GCD techniques.

Electrolyte	CV		GCD		
	C <sub>sp</sub> (F g <sup>-1</sup> )	C <sub>sp</sub> (F g <sup>-1</sup> )	E (Wh kg <sup>-1</sup> )	P (W kg <sup>-1</sup> )	R (Ω)
1 M H <sub>2</sub> SO <sub>4</sub>	283	307	36.47	240.73	0.006
6 M KOH	248	254	33.21	220.75	0.012
1 M Na <sub>2</sub> SO <sub>4</sub>	202	201	31.59	144.75	0.031


The MOL750 carbon disc electrode was evaluated through different aqueous electrolytes, namely 1 M H<sub>2</sub>SO<sub>4</sub>, 6 M KOH, and 1 M Na<sub>2</sub>SO<sub>4</sub> to confirm the high electrochemical performance. Figure 7a shows the CV curve of the MOLs750 carbon in different aqueous electrolytes. Generally, all aqueous electrolytes showed a distorted rectangular shape, which indicated good EDLC properties. In H<sub>2</sub>SO<sub>4</sub> and KOH electrolytes, there was a sudden increase in current density in the voltage range of 0.6-0.8 V. This is closely related to the redox reaction of oxygen heteroatoms under acidic and alkaline aqueous electrolytes that confirms the presence of apparent capacitance. However, it was not discovered in the neutral aqueous electrolyte Na<sub>2</sub>SO<sub>4</sub>. Based on the magnitude of the formed CV curve, the performance of MOL750 on different electrolytes can be ordered by H<sub>2</sub>SO<sub>4</sub>>KOH>Na<sub>2</sub>SO<sub>4</sub> with specific capacitances of 283, 248, and 202 F g<sup>-1</sup>. Improved CV scanning was also applied to MOLs750 in different aqueous electrolytes as shown in Figure 7b-d. All three aqueous electrolytes still produced a distorted rectangular shape, although showing widening towards a parallelogram at scan rates of 2 and 5 mV s<sup>-1</sup>. This generally

exhibited good EDLC performance on acidic, alkaline, and neutral electrolytes. Furthermore, it was discovered that higher scan rates reduced their capacitive properties as shown in Figure 7e. Although specific capacitance was decreased at a scan rate of 10 mV s<sup>-1</sup> for all electrolytes, they still maintain their capacitive properties of 61-78% with the order H<sub>2</sub>SO<sub>4</sub>>KOH>Na<sub>2</sub>SO<sub>4</sub>. This was significantly contributed by rich mesoporosity >30%, allowing electrolyte ions to diffuse smoothly when their scan is enhanced. Moreover, the contribution of this aqueous electrolyte modification is also reviewed through the GCD technique. Figure 7f depicts the GCD curves of the MOL750 carbon disc electrodes on different electrolytes. It exhibits a nearly ideal isosceles triangular shape, which indicates the normal EDLC properties of an aqueous electrolyte. However, the KOH electrolyte appeared a GCD curve that contained the greatest ion degradation characterized by a charging time, which is significantly different from the discharging time. This is closely related to oxygen heteroatoms with the potential of the evolution of O<sub>2</sub> and H<sub>2</sub> in aqueous electrolyte systems<sup>65</sup>. It was also discovered that the iR drop was relatively very low, confirming the high conductivity

properties of the MOLs750 precursor as summarized in Table 3.

This phenomenon initiates the high storage capacity of supercapacitors despite their relatively low surface area. Based on the length of the discharge time, the H<sub>2</sub>SO<sub>4</sub> electrolyte exhibited the highest specific capacitance, followed by KOH and Na<sub>2</sub>SO<sub>4</sub> with their capacitive values of 307, 254, and 201 F g<sup>-1</sup>, respectively. This result is in line with the CV analysis, which also revealed almost similar results. To confirm the practical application<sup>66</sup>, the volumetric capacitance was also evaluated as high as 101.61, 684.07, and 66.53 F cm<sup>-3</sup> for different electrolytes H<sub>2</sub>SO<sub>4</sub>, KOH and Na<sub>2</sub>SO<sub>4</sub> respectively. Moreover, modifying the cations and anions in the aqueous electrolyte can affect the electrochemical substance of the supercapacitor, especially at the MOL750 carbon disc electrode. This is due to Ionic mobility, ionic hydrated radius, conductivity, and impact on charge/ion exchange as well as diffusion<sup>67</sup>. The small dehydrated sphere of H<sup>+</sup> cations compared to K<sup>+</sup> and Na<sup>+</sup> allows the charge on the cations to produce the greatest molar ionic conductivity and ionic mobility<sup>68</sup>. These characteristics are needed to obtain fast charge transfer and high ion adsorption at the electrolyte/electrode interface. Similarly, the specification of the cationic radius is also closely related to long-term cycle stability for the MOL750 electrode material, as shown in Figure 10e, where the H<sub>2</sub>SO<sub>4</sub> electrolyte maintained a specific capacitance of 78%. Anion specifications were also studied in their interactions with the MOL750 disc electrode. The results showed that the OH<sup>-</sup> has a narrower hydration ball radius, initiating better conductivity and ionic mobility. Meanwhile, the SO<sub>4</sub><sup>2-</sup> exhibited a larger hydration ball radius, leading to a decrease in the number of ions accessing the pores and lower electrical double sheet formation<sup>69</sup>. Relative to other anions, SO<sub>4</sub><sup>2-</sup> ion has poor conductivity and ion mobility, which makes Na<sub>2</sub>SO<sub>4</sub> electrolytes show the lowest capacitive

properties compared to H<sub>2</sub>SO<sub>4</sub> and KOH electrolytes.

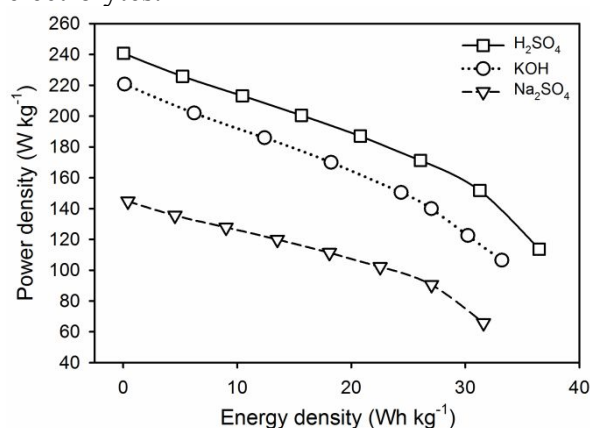

**Figure 8.** Ragone plot of the disc electrode MOLs in different aqueous electrolytes.

For detailed confirmation, the potential of the MOL750 disc electrode in different aqueous electrolytes was reviewed through the Ragone plot as shown in Figure 8. The H<sub>2</sub>SO<sub>4</sub> electrolyte demonstrated the highest performance with an energy density of 36.47 Wh kg<sup>-1</sup> at a power density of 240.73 W kg<sup>-1</sup>. Furthermore, 3D hierarchical pore properties with micro and meso ratio of approximately 3:1 perfectly match the criteria for H<sup>+</sup> anions and SO<sub>4</sub><sup>2-</sup> cations in aqueous electrolyte H<sub>2</sub>SO<sub>4</sub> to possess high energy density in supercapacitor energy storage devices. The alkaline electrolyte KOH also displays an energy density of 33.2047 Wh kg<sup>-1</sup> at a power density of 220.750 W kg<sup>-1</sup>, while the neutral electrolyte Na<sub>2</sub>SO<sub>4</sub> exhibits an energy density of 31.5964 Wh kg<sup>-1</sup> at a power density of 144.7541 W kg<sup>-1</sup>. Moreover, the volumetric energy density is summarized in detail covering 12.07, 10.99, and 10.45 Wh L<sup>-1</sup> for the different electrolytes H<sub>2</sub>SO<sub>4</sub>, KOH and Na<sub>2</sub>SO<sub>4</sub>, which indicated the great potential of MOL750 electrode as practical applications in electrochemical energy storage devices<sup>66,70</sup>. This result is relatively high compared to previous reports, which are summarized in Table 4

**Table 4.** Comparison of electrochemical performance in different carbon sources.

Sources	$S_{\text{BET}}$ ( $\text{m}^2 \text{g}^{-1}$ )	Electrolyte	Electrode design	$C_{\text{sp}}$ ( $\text{F g}^{-1}$ )	E ( $\text{Wh kg}^{-1}$ )	R ( $\Omega$ )	Ref
Wood powders	282.4	6 M KOH	Powder with PTFE	150.1	-	-	25
Feather finger grass flower	637.1	6 M KOH	Powder with PTFE	315	18.75	-	26
Camellia pollen	852	6 M KOH	Powder with PTFE	300	14.3	0.68	27
Sword bean shell	2282	6 M KOH	Powder with PVDF	264	12.5	1.38	44
foxtail grasses	819	6 M KOH	Powder with PTFE	358	18.2	0.8	53
Calcium D-gluconate	539	1 M $\text{H}_2\text{SO}_4$	Powder with PTFE	355	40.5	-	71
Rubber wood sawdust	2820	1 M $\text{H}_2\text{SO}_4$	Powder with PTFE	185	6.93	1.32	72
Kapok flower	1904.1	6 M KOH	Powder with PTFE	286.8	-	0.79	73
Banana leaves	1459	[BMIM][PF6]	Powder with PVP	190	59	-	74
Shallot peel	1182.2	1 M $\text{H}_2\text{SO}_4$	Solid coin without binder	170.12	16.67	0.031	60
MOLs	412.196	1 M $\text{Na}_2\text{SO}_4$	Concolidate disc binder-free	201	31.59	0.031	This work
MOLs	412.196	6 M KOH	Concolidate disc binder-free	254	33.21	0.012	This work
MOLs	412.196	1 M $\text{H}_2\text{SO}_4$	Concolidate disc binder-free	307	36.47	0.006	This work

### 3. CONCLUSION

The green *Moringa oleifera* leaves (MOLs) were converted into a novel consolidated carbon disc-based electrode material through a facile, simple, and environmental approach. The MOLs carbon discs obtained showed a rich 3D hierarchical micro-mesopore structure decorated nanofibers. Furthermore, oxygen heteroatoms (8.06–17.41%) were confirmed with a high carbon content of 88.91%. Furthermore, the electrochemical properties of the carbon disc electrodes of MOLs were evaluated in a symmetric supercapacitor system on different aqueous electrolytes. The MOL750 disc electrode showed the best electrochemical properties with a specific capacitance of  $307 \text{ F g}^{-1}$  on aqueous

electrolyte  $\text{H}_2\text{SO}_4$ . Moreover, the MOLs750 discs can maintain their high performance on aqueous electrolytes KOH and  $\text{Na}_2\text{SO}_4$  with specific capacitances of 254 and  $201 \text{ F g}^{-1}$  in a current density of  $1 \text{ A g}^{-1}$ . The design of binder-free consolidated carbon disc MOLs showed their great potential in producing high capacitive properties, lower internal resistance, high conductivity, despite the relatively low surface area of  $412.196 \text{ m}^2 \text{g}^{-1}$ . Therefore, the MOLs can be developed as a novel approach for producing excellent biomass-based electrode material to enhance the performance of energy storage devices in symmetric supercapacitors.

## 4. EXPERIMENTAL SECTION

### 4.1. Synthesis of porous consolidated carbon disc from MOLs

Green *Moringa oleifera* leaves, hereinafter referred to MOLs, were obtained from a vegetable supplier of Pekanbaru grand-market, separated from the stalks, and cleaned. After the soil and sand elements are removed, the leaves were sundried for 2 days and further oven-dried at 110°C (Oven food warmer 10-110C type FW-35) for 35 hours until the green precursors turned wilted and brittle. The precursor was converted into powder form through pre-carbonization, crusher, and sieving. Pre-carbonization was carried out by preparing 30 g of dried leaves sample in a closed container and placing it in an oven with a temperature of 250°C (KIRIN Oven 10L KBO 100 M) for 2 hours 30 minutes. The sample obtained from the pre-carbonization was inserted into the crusher instrument for 24 hours. The precursor powder from the crusher was sieved using a 250 mesh (CBN test sieve analysis, Cat No. KB-31) to obtain a homogeneous powder, which was chemically activated by zinc chloride impregnated in solution 0.5 mol/L solution. Zinc chloride for analysis was purchased from EMSURE ACS, ISO, Reag. Ph Eur. CAS No. 7646-85-7, EC Number 231-592-0. Subsequently, the dried powder precursor was mixed with ZnCl<sub>2</sub> solution on a Digital Lab Thermostatic Hot-Plate instrument (WiseStir Wisd MSH30D) with a rotation rate of 300 rpm at a temperature of 80°C for 2 hours, while the impregnated samples were dried in an oven at 110°C for 2 days. As a novelty in this study, the carbon powder was converted into a consolidated disc without a binder. For one solid disc sample, 0.7 g of sample powder was pressed through a hydraulic press (Hydraulic Press Bench Type 10T Krisbow KW0500135) at a pressure equal to a mass of 8 tons. 0.7 gr powder samples put in an iron mold resembling a tube with a diameter of 19mm. The iron mold is pressed using a hydraulic press freely equivalent to ±8.0 tons. A total of 15 monolith solid discs were further put

into a vertical furnace (Box Furnace NDT-LB 5, Payun Tech) for high-temperature pyrolysis. The pyrolysis process including carbonization and physical activation was carried out in a single-stage integrated system. This process starts with carbonization in the N<sub>2</sub> gas environment from a temperature of 30 to 600°C with a gas increase rate of 3°C/min. The gas environment is replaced with CO<sub>2</sub> as a physical activation stage to a high different temperature of 650, 750, and 850°C, with an increased rate of 10°C/min. For comparison, a sample was further prepared at 600°C without physical activation. Meanwhile, the 3D porous carbon samples obtained were neutralized by soaking in distilled water and HCl in 1 m/L solution. The immersion water was confirmed to be neutral (pH=7) using a universal pH strip indicator, which was purchased from Merck KGaA, 64271 Darmstadt, Germany. Several labels were made to facilitate the analysis and comparison of materials, as well as electrochemical properties of 3D porous activated carbon-based MOLs. It includes MOL600 as a precursor as well as MOLs650, MOLs750, and MOLs850 from ZnCl<sub>2</sub> impregnation and physical activation with different temperatures of 650, 750, and 850°C.

### 4.2. Material characterizations

The initial porosity properties of solid consolidated disc carbon samples were evaluated through density reduction in high temperatures before and after the pyrolysis process. The density was calculated based on measurements of mass using a Labtronics GM-303 analytical balance, thickness, and diameter of the solid carbon monolith pellets using a QRC5 digital caliper<sup>75</sup>. The porosity properties of carbon MOLs were further evaluated through the N<sub>2</sub> gas adsorption/desorption using Quantachrome version 10.01 at a temperature of 77 K in the P/P<sub>0</sub> relative pressure range of 0.00-0.985. The specific surface area was determined with the Breunauer-Emmet-Teller (BET) technique and the pore size distribution was

calculated using the density functional theory (DFT) approach. Furthermore, the structure and morphology of activated carbon were reviewed through X-ray diffraction (XRD) and scanning electron microscopy (SEM) methods. X-ray diffraction (XRD) was examined in CuK $\alpha$  source ( $\lambda = 1.54051$ ) at an angle range of 10-60° (Malvern Panalytical's X-ray diffractometers), while interlayer spacing was calculated using Bragg's law and lattice parameters ( $L_c$  and  $L_a$ ), which were determined by equation debye-scheerer<sup>36,37</sup>. Similarly, scanning electron microscopy (SEM) was reviewed at a voltage of 15 kV in the energy range 0-20 KeV using JEOL-JSM6510LA instrument. The elemental status of MOLs was also reviewed through the energy dispersive spectroscopy method (JEOL-JSM-6510-LA instrument).

### 4.3. Measurement of electrochemical properties

The working electrodes were prepared in a two-system configuration similar to a binder-free two solid disc carbon MOLs with a loading mass of approximately  $\pm 10.0$  mg. The carbon disc obtained from pyrolysis was polished using P1200 polishing paper to obtain carbon discs with diameters and thicknesses of  $\pm 8$  mm and 0.19 mm, respectively. Here, two carbon disc as electrodes binder-free were prepared in diameter of  $\pm 8.0$  mm with a thickness of 0.19 mm. They were separated by an organic separator made from eggshell membranes. As a support for the electrode, the cell body was made in a rectangular geometry with a hole of  $\pm 9.0$  mm diameter in the middle. The current collector was prepared from 0.2 mm stainless steel and an aqueous electrolyte consisting of 1 M H<sub>2</sub>SO<sub>4</sub>, 6 M KOH, and 1 M Na<sub>2</sub>SO<sub>4</sub> was selected. Subsequently, the electrochemical properties were reviewed using cyclic voltammetry technique with CV, RAD-ER 5841, calibrated error  $\pm 6.0\%$  in a potential window range of 0.0-1.0V at different scanning rates of 1, 2, 5, and 10 mV s<sup>-1</sup>.

Specific capacitance, energy and power densities, and internal resistance were further evaluated through the galvanostatic charge-discharge technique using GCD, RAD-ER 2018 at a constant current density of 1.0 A g<sup>-1</sup> based on the standard equation<sup>76</sup>.

$$C_{sp} = \frac{I \cdot \Delta t}{m \cdot \Delta V}$$

$$E_{sp} = \int IV dt$$

$$P_{sp} = \frac{E_{sp}}{t}$$

Where  $C_{sp}$  (F g<sup>-1</sup>) is specific capacitance,  $I$  (A) is current,  $\Delta t$  (s) is discharge time,  $m$  (g) is mass working electrode,  $\Delta V$  (V) is voltage discharge,  $E_{sp}$  (Wh kg<sup>-1</sup>) is energy density, and  $P_{sp}$  is power density (W kg<sup>-1</sup>).

### ACKNOWLEDGEMENTS

The research was financially supported by second years Project of Word Class Research (WCR) in *Kementerian Pendidikan, Kebudayaan, Riset, dan Teknologi*, Republic of Indonesia with the title "High energy and power densities of supercapacitor for the optimization of electrode supply process".

### AUTHOR INFORMATION

#### Corresponding Author

Rika Taslim – *Department of Industrial Engineering, State Islamic University of Sultan Syarif Kasim, Riau, Simpang Baru-Tampan Pekanbaru, 28293 Indonesia*; <https://orcid.org/0000-0003-1946-1299>; Email: [rikataslim@gmail.com](mailto:rikataslim@gmail.com).

#### Authors

Apriwandi Apriwandi – *Department of Physics, Faculty of Mathematics and Natural Sciences, University of Riau, Panam, Pekanbaru, 28293 Indonesia*: Email: [apriwandi95@gmail.com](mailto:apriwandi95@gmail.com).

Erman Taer – *Department of Physics, Faculty of Mathematics and Natural Sciences, University of Riau, Panam, Pekanbaru, 28293 Indonesia*: Email: [erman.taer@lecturer.unri.ac.id](mailto:erman.taer@lecturer.unri.ac.id).

## REFERENCES

(1) International Energy Agency. *Global Energy Review 2021*; 2021.

(2) BP. *Statistical Review of World Energy*; 2021; Vol. 70.

(3) BPSTATS. *Review of World Energy Statistical Review of World, 68th Edition*; 2019.

(4) REN21. *Renewables 2021 Global Status Report*; 2021.

(5) Burke, A. Ultracapacitors: Why, How, and Where Is the Technology. *J. Power Sources* **2000**, *91* (1), 37–50.

(6) Li, X.; Zhang, J.; Liu, B.; Su, Z. A Critical Review on the Application and Recent Developments of Post-Modified Biochar in Supercapacitors. *J. Clean. Prod.* **2021**, *310* (April), 127428. <https://doi.org/10.1016/j.jclepro.2021.127428>.

(7) Zhang, W.; Cheng, R. R.; Bi, H. H.; Lu, Y. H.; Ma, L. B.; He, X. J. A Review of Porous Carbons Produced by Template Methods for Supercapacitor Applications. *Xinxing Tan Cailiao/New Carbon Mater.* **2021**, *36* (1), 69–81. [https://doi.org/10.1016/S1872-5805\(21\)60005-7](https://doi.org/10.1016/S1872-5805(21)60005-7).

(8) Miller, E. E.; Hua, Y.; Tezel, F. H. Materials for Energy Storage: Review of Electrode Materials and Methods of Increasing Capacitance for Supercapacitors. *J. Energy Storage* **2018**, *20* (February), 30–40. <https://doi.org/10.1016/j.est.2018.08.009>.

(9) Taer, E.; Taslim, R. Brief Review: Preparation Techniques of Biomass Based Activated Carbon Monolith Electrode for Supercapacitor Applications. In *AIP Conference Proceedings*; 2018; Vol. 1927, pp 020004-1-020004-4. <https://doi.org/https://doi.org/10.1063/1.5021192>.

(10) González, A.; Goikolea, E.; Barrena, J. A.; Mysyk, R. Review on Supercapacitors: Technologies and Materials. *Renew. Sustain. Energy Rev.* **2016**, *58*, 1189–1206. <https://doi.org/10.1016/j.rser.2015.12.249>.

(11) Wang, G.; Zhang, L.; Zhang, J. A Review of Electrode Materials for Electrochemical Supercapacitors. *Chem. Soc. Rev.* **2012**, *41* (2), 797–828. <https://doi.org/10.1039/c1cs15060j>.

(12) Dessie, Y.; Tadesse, S.; Eswaramoorthy, R.; Abebe, B. Recent Developments in Manganese Oxide Based Nanomaterials with Oxygen Reduction Reaction Functionalities for Energy Conversion and Storage Applications: A Review. *J. Sci. Adv. Mater. Devices* **2019**, *4* (3), 353–369. <https://doi.org/10.1016/j.jsamd.2019.07.001>.

(13) Soltani, S.; Khanian, N.; Choong, T. S. Y.; Rashid, U. Recent Progress in the Design and Synthesis of Nanofibers with Diverse Synthetic Methodologies: Characterization and Potential Applications. *New J. Chem.* **2020**, *44* (23), 9581–9606. <https://doi.org/10.1039/d0nj01071e>.

(14) Zhang, Q. Z.; Zhang, D.; Miao, Z. C.; Zhang, X. L.; Chou, S. L. Research Progress in MnO<sub>2</sub>-Carbon Based Supercapacitor Electrode Materials. *Small* **2018**, *14* (24), 1–15. <https://doi.org/10.1002/smll.201702883>.

(15) Arunachalam, R.; Prataap, R. K. V.; Pavul Raj, R.; Mohan, S.; Vijayakumar, J.; Péter, L.; Al Ahmad, M. Pulse Electrodeposited RuO<sub>2</sub> Electrodes for High-Performance Supercapacitor Applications. *Surf. Eng.* **2019**, *35* (2), 103–109. <https://doi.org/10.1080/02670844.2018.1426408>.

(16) Li, J.; Hu, H.; Li, H.; Yao, C. Recent Developments in Electrochemical Sensors Based on Nanomaterials for Determining Glucose and Its Byproduct H<sub>2</sub>O<sub>2</sub>. *J. Mater. Sci.* **2017**, *52* (17), 10455–10469. <https://doi.org/10.1007/s10853-017-1221-4>.

(17) Wang, J.; Zheng, F.; Yu, Y.; Hu, P.; Li, M.; Wang, J.; Fu, J.; Zhen, Q.; Bashir, S.; Liu, J. L. Symmetric Supercapacitors

- Composed of Ternary Metal Oxides (NiO/V<sub>2</sub>O<sub>5</sub>/MnO<sub>2</sub>) Nanoribbon Electrodes with High Energy Storage Performance. *Chem. Eng. J.* **2021**, *426* (August). <https://doi.org/10.1016/j.cej.2021.131804>.
- (18) Zang, S.; Jiang, J.; An, Y.; Li, Z.; Guo, H.; Sun, Y.; Dou, H.; Zhang, X. A Novel Porous Organic Polymer-Derived Hierarchical Carbon for Supercapacitors with Ultrahigh Energy Density and Durability. *J. Electroanal. Chem.* **2020**, *876*, 114723. <https://doi.org/10.1016/j.jelechem.2020.114723>.
- (19) Majid, S.; Ali, A. S. G.; Cao, W. Q.; Reza, R.; Ge, Q. Biomass-Derived Porous Carbons as Supercapacitor Electrodes-A Review. *New Carbon Mater.* **2021**, *36* (3), 546–572. [https://doi.org/10.1016/S1872-5805\(21\)60038-0](https://doi.org/10.1016/S1872-5805(21)60038-0).
- (20) Saini, S.; Chand, P.; Joshi, A. Biomass Derived Carbon for Supercapacitor Applications: Review. *J. Energy Storage* **2021**, *39* (April), 102646. <https://doi.org/10.1016/j.est.2021.102646>.
- (21) Li, Z.; Guo, D.; Liu, Y.; Wang, H.; Wang, L. Recent Advances and Challenges in Biomass-Derived Porous Carbon Nanomaterials for Supercapacitors. *Chem. Eng. J.* **2020**, *397* (October 2019), 125418. <https://doi.org/10.1016/j.cej.2020.125418>.
- (22) Gopalakrishnan, A.; Badhulika, S. Effect of Self-Doped Heteroatoms on the Performance of Biomass-Derived Carbon for Supercapacitor Applications. *J. Power Sources* **2020**, *480* (August), 228830. <https://doi.org/10.1016/j.jpowsour.2020.228830>.
- (23) Aruchamy, K.; Dharmalingam, K.; Lee, C. W.; Mondal, D.; Sanna Kotrappanavar, N. Creating Ultrahigh Surface Area Functional Carbon from Biomass for High Performance Supercapacitor and Facile Removal of Emerging Pollutants. *Chem. Eng. J.* **2022**, *427* (April 2021), 131477. <https://doi.org/10.1016/j.cej.2021.131477>.
- (24) Zhang, Y.; Wu, C.; Dai, S.; Liu, L.; Zhang, H.; Shen, W.; Sun, W.; Ming Li, C. Rationally Tuning Ratio of Micro- to Meso-Pores of Biomass-Derived Ultrathin Carbon Sheets toward Supercapacitors with High Energy and High Power Density. *J. Colloid Interface Sci.* **2022**, *606*, 817–825. <https://doi.org/10.1016/j.jcis.2021.08.042>.
- (25) Wang, C.; Wang, H.; Dang, B.; Wang, Z.; Shen, X.; Li, C.; Sun, Q. Ultrahigh Yield of Nitrogen Doped Porous Carbon from Biomass Waste for Supercapacitor. *Renew. Energy* **2020**, *156*, 370–376. <https://doi.org/10.1016/j.renene.2020.04.092>.
- (26) Senthil, R. A.; Yang, V.; Pan, J.; Sun, Y. A Green and Economical Approach to Derive Biomass Porous Carbon from Freely Available Feather Finger Grass Flower for Advanced Symmetric Supercapacitors. *J. Energy Storage* **2021**, *35* (January), 102287. <https://doi.org/10.1016/j.est.2021.102287>.
- (27) Cao, L.; Li, H.; Xu, Z.; Zhang, H.; Ding, L.; Wang, S.; Zhang, G.; Hou, H.; Xu, W.; Yang, F.; Jiang, S. Comparison of the Heteroatoms-Doped Biomass-Derived Carbon Prepared by One-Step Nitrogen-Containing Activator for High Performance Supercapacitor. *Diam. Relat. Mater.* **2021**, *114* (November 2020), 108316. <https://doi.org/10.1016/j.diamond.2021.108316>.
- (28) Wang, L.; Li, X.; Huang, X.; Han, S.; Jiang, J. Activated Green Resources to Synthesize N, P Co-Doped O-Rich Hierarchical Interconnected Porous Carbon for High-Performance Supercapacitors. *J. Alloys Compd.* **2021**, *891*, 161908. <https://doi.org/10.1016/j.jallcom.2021.161908>.
- (29) Apriwandi, A.; Taer, E.; Farma, R.; Setiadi, R. N.; Amiruddin, E. A Facile Approach of Micro-Mesopores Structure Binder-Free Coin/Monolith Solid Design Activated Carbon for Electrode Supercapacitor. *J. Energy Storage* **2021**, *40* (June), 102823. <https://doi.org/10.1016/j.est.2021.102823>.
- (30) Farma, R.; Deraman, M.; Omar, R.; Awitdrus; Ishak, M. M.; Taer, E.; Talib, I. A. Binderless Composite Electrode



Monolith from Carbon Nanotube and Biomass Carbon Activated by KOH and CO<sub>2</sub> Gas for Supercapacitor. *AIP Conf. Proc.* **2011**, *1415*, 180–184. <https://doi.org/10.1063/1.3667251>.

(31) Taer, E.; Apriwandi; Dalimunthe, B. K. L.; Taslim, R. A Rod-like Mesoporous Carbon Derived from Agro-Industrial Cassava Petiole Waste for Supercapacitor Application. *J. Chem. Technol. Biotechnol.* **2021**, *96* (3), 662–671. <https://doi.org/10.1002/jctb.6579>.

(32) Martínez-Casillas, D. C.; Mascorro-Gutiérrez, I.; Arreola-Ramos, C. E.; Villafán-Vidales, H. I.; Arancibia-Bulnes, C. A.; Ramos-Sánchez, V. H.; Cuentas-Gallegos, A. K. A Sustainable Approach to Produce Activated Carbons from Pecan Nutshell Waste for Environmentally Friendly Supercapacitors. *Carbon N. Y.* **2019**, *148*, 403–412. <https://doi.org/10.1016/j.carbon.2019.04.017>.

(33) Wei, H.; Wang, H.; Li, A.; Li, H.; Cui, D.; Dong, M.; Lin, J.; Fan, J.; Zhang, J.; Hou, H.; Shi, Y.; Zhou, D.; Guo, Z. Advanced Porous Hierarchical Activated Carbon Derived from Agricultural Wastes toward High Performance Supercapacitors. *J. Alloys Compd.* **2020**, *820*, 153111. <https://doi.org/10.1016/j.jallcom.2019.153111>.

(34) Achour, A.; Arman, A.; Islam, M.; Zavarian, A. A.; Al-zubaidi, A. B.; Szade, J. Synthesis and Characterization of Porous CaCO<sub>3</sub> Micro/Nano-Particles. *Eur. Phys. J. PLUS* **2017**, *132*, 267. <https://doi.org/10.1140/epjp/i2017-11531-8>.

(35) Jose, A.; Devi, K. R. S.; Pinheiro, D.; Lakshmi, S. Electrochemical Synthesis, Photodegradation and Antibacterial Properties of PEG Capped Zinc Oxide Nanoparticles. *J. Photochem. Photobiol. B Biol.* **2018**, *187*, 25–34. <https://doi.org/10.1016/j.jphotobiol.2018.07.022>.

(36) Ayinla, R. T.; Dennis, J. O.; Zaid, H. M.; Sanusi, Y. K.; Usman, F.; Adebayo, L. L. A Review of Technical Advances of Recent Palm Bio-Waste Conversion to

Activated Carbon for Energy Storage. *J. Clean. Prod.* **2019**, *229*, 1427–1442. <https://doi.org/10.1016/j.jclepro.2019.04.116>.

(37) Yaya, A.; Agyei-Tuffour, B.; Dodoo-Arhin, D.; Nyankson, E.; Annan, E.; Konadu, D. S.; Sinayobye, E.; Baryeh, E. a.; Ewels, C. P. Layered Nanomaterials- A Review. *Glob. J. Eng. Des. Technol.* **2012**, *1* (2), 32–41.

(38) Deraman, M.; Daik, R.; Soltaninejad, S.; Nor, N. S. M.; Awitdrus; Farma, R.; Mamat, N. F.; Basri, N. H.; Othman, M. A. R. A New Empirical Equation for Estimating Specific Surface Area of Supercapacitor Carbon Electrode from X-Ray Diffraction. *Adv. Mater. Res.* **2015**, *1108*, 1–7. <https://doi.org/10.4028/www.scientific.net/AMR.1108.1>.

(39) Kumar, K.; Saxena, R. K.; Kothari, R.; Suri, D. K.; Kaushik, N. K.; Bohra, J. N. Correlation between Adsorption and X-Ray Diffraction Studies on Viscose Rayon Based Activated Carbon Cloth. *Carbon N. Y.* **1997**, *35* (12), 1842–1844. [https://doi.org/10.1016/S0008-6223\(97\)87258-2](https://doi.org/10.1016/S0008-6223(97)87258-2).

(40) Riyanto, C.; Kristen, U.; Wacana, S.; Ampri, M. S.; Martono, Y.; Kristen, U.; Wacana, S. Synthesis and Characterization of Nano Activated Carbon from Annatto Peels (Bixa Orellana L.) Viewed from Temperature Activation and Impregnation Ratio of H<sub>3</sub>PO<sub>4</sub>. *J. Sci. data Anal.* **2020**, *1* (1), 44–50. <https://doi.org/10.20885/EKSAKTA.vol1.iss1.art>.

(41) Salakhum, S.; Yutthalekha, T.; Chareonpanich, M.; Limtrakul, J.; Wattanakit, C. Synthesis of Hierarchical Faujasite Nanosheets from Corn Cob Ash-Derived Nanosilica as Efficient Catalysts for Hydrogenation of Lignin-Derived Alkylphenols. *Microporous Mesoporous Mater.* **2018**, *258*, 141–150. <https://doi.org/10.1016/j.micromeso.2017.09.009>.

(42) Pourhosseini, S. E. M.; Norouzi, O.; Naderi, H. R. Study of Micro/Macro

1  
2  
3  
4  
5  
6  
7  
8  
9  
10  
11  
12  
13  
14  
15  
16  
17  
18  
19  
20  
21  
22  
23  
24  
25  
26  
27  
28  
29  
30  
31  
32  
33  
34  
35  
36  
37  
38  
39  
40  
41  
42  
43  
44  
45  
46  
47  
48  
49  
50  
51  
52  
53  
54  
55  
56  
57  
58  
59  
60

Ordered Porous Carbon with Olive-Shaped Structure Derived from *Cladophora Glomerata* Macroalgae as Efficient Working Electrodes of Supercapacitors. *Biomass and Bioenergy* **2017**, *107* (October), 287–298. <https://doi.org/10.1016/j.biombioe.2017.10.025>.

(43) Li, J.; Zou, Y.; Xiang, C.; Xu, F.; Sun, L.; Li, B.; Zhang, J. Osmanthus Fragrans-Derived N-Doped Porous Carbon for Supercapacitor Applications. *J. Energy Storage* **2021**, *42*, 103017. <https://doi.org/10.1016/j.est.2021.103017>.

(44) Chen, T.; Luo, L.; Luo, L.; Deng, J.; Wu, X.; Fan, M.; Du, G.; Weigang Zhao. High Energy Density Supercapacitors with Hierarchical Nitrogen-Doped Porous Carbon as Active Material Obtained from Bio-Waste. *Renew. Energy* **2021**, *175*, 760–769. <https://doi.org/10.1016/j.renene.2021.05.006>.

(45) Liang, Y.; Lu, Y.; Xiao, G.; Zhang, J.; Chi, H.; Dong, Y. Hierarchical Porous Nitrogen-Doped Carbon Microspheres after Thermal Rearrangement as High Performance Electrode Materials for Supercapacitors. *Appl. Surf. Sci.* **2020**, *529*, 147141. <https://doi.org/10.1016/j.apsusc.2020.147141>.

(46) Bhat, V. S.; Kanagavalli, P.; Sriram, G.; B, R. P.; John, N. S.; Veerapandian, M.; Kurkuri, M.; Hegde, G. Low Cost, Catalyst Free, High Performance Supercapacitors Based on Porous Nano Carbon Derived from Agriculture Waste. *J. Energy Storage* **2020**, *32* (August), 101829. <https://doi.org/10.1016/j.est.2020.101829>.

(47) Márquez-Montesino, F.; Torres-Figueroa, N.; Lemus-Santana, A.; Trejo, F. Activated Carbon by Potassium Carbonate Activation from Pine Sawdust (*Pinus Montezumae* Lamb.). *Chem. Eng. Technol.* **2020**, *43* (9), 1716–1725. <https://doi.org/10.1002/ceat.202000051>.

(48) Zhang, Y.; Yu, S.; Lou, G.; Shen, Y.; Chen, H.; Shen, Z.; Zhao, S.; Zhang, J.; Chai, S.; Zou, Q. Review of Macroporous Materials as Electrochemical Supercapacitor Electrodes. *J. Mater. Sci.* **2017**, *52* (19),

11201–11228.

<https://doi.org/10.1007/s10853-017-0955-3>.

(49) Boujibar, O.; Ghamouss, F.; Ghosh, A.; Achak, O.; Chafik, T. Efficient CO<sub>2</sub> Capture by Ultra-High Microporous Activated Carbon Made from Natural Coal. *Chem. Eng. Technol.* **2021**, *44* (1), 148–155. <https://doi.org/10.1002/ceat.202000138>.

(50) Yakaboylu, G. A.; Jiang, C.; Yumak, T.; Zondlo, J. W.; Wang, J.; Sabolsky, E. M. Engineered Hierarchical Porous Carbons for Supercapacitor Applications through Chemical Pretreatment and Activation of Biomass Precursors. *Renew. Energy* **2021**, *163*, 276–287. <https://doi.org/10.1016/j.renene.2020.08.092>.

(51) Sing, K. S. W. Reporting Physisorption Data for Gas/Solid Systems with Special Reference to the Determination of Surface Area and Porosity. *Pure Appl. Chem.* **1982**, *54* (11), 2201–2218. <https://doi.org/10.1351/pac198254112201>.

(52) Zheng, G.; Huang, Z.; Liu, Z. Cooperative Utilization of Beet Pulp and Industrial Waste Fly Ash to Produce N/P/O Self-Co-Doped Hierarchically Porous Carbons for High-Performance Supercapacitors. *J. Power Sources* **2021**, *482* (September 2020), 228935. <https://doi.org/10.1016/j.jpowsour.2020.228935>.

(53) Liang, X.; Liu, R.; Wu, X. Biomass Waste Derived Functionalized Hierarchical Porous Carbon with High Gravimetric and Volumetric Capacitances for Supercapacitors. *Microporous Mesoporous Mater.* **2021**, *310* (September 2020), 110659. <https://doi.org/10.1016/j.micromeso.2020.110659>.

(54) Zhang, X.; Liu, B.; Yan, X.; Zhao, X.; Zhang, Y.; Wei, Y.; Cao, Q. Design and Structure Optimization of 3D Porous Graphitic Carbon Nanosheets for High-Performance Supercapacitor. *Microporous Mesoporous Mater.* **2020**, *309* (August), 110580. <https://doi.org/10.1016/j.micromeso.2020.110580>.

<https://doi.org/10.1016/j.micromeso.2020.110580>.

- (55) Wang, Y.; Qiao, M.; Mamat, X. Nitrogen-Doped Macro-Meso-Micro Hierarchical Ordered Porous Carbon Derived from ZIF-8 for Boosting Supercapacitor Performance. *Appl. Surf. Sci.* **2021**, *540* (P1), 148352. <https://doi.org/10.1016/j.apsusc.2020.148352>.
- (56) Wu, J.; Xia, M.; Zhang, X.; Chen, Y.; Sun, F.; Wang, X.; Yang, H.; Chen, H. Hierarchical Porous Carbon Derived from Wood Tar Using Crab as the Template: Performance on Supercapacitor. *J. Power Sources* **2020**, *455* (February), 227982. <https://doi.org/10.1016/j.jpowsour.2020.227982>.
- (57) Yang, V.; Senthil, R. A.; Pan, J.; Kumar, T. R.; Sun, Y.; Liu, X. Hierarchical Porous Carbon Derived from Jujube Fruits as Sustainable and Ultrahigh Capacitance Material for Advanced Supercapacitors. *J. Colloid Interface Sci.* **2020**, *579*, 347–356. <https://doi.org/10.1016/j.jcis.2020.06.080>.
- (58) Huo, S.; Zhang, X.; Liang, B.; Zhao, Y.; Li, K. Synthesis of Interconnected Hierarchically Porous Carbon Networks with Excellent Diffusion Ability Based on NaNO<sub>3</sub> Crystal-Assisted Strategy for High Performance Supercapacitors. *J. Power Sources* **2020**, *450* (December 2019), 227612. <https://doi.org/10.1016/j.jpowsour.2019.227612>.
- (59) Sekhon, S. S.; Park, J. S. Biomass-Derived N-Doped Porous Carbon Nanosheets for Energy Technologies. *Chem. Eng. J.* **2021**, *425* (December 2020), 129017. <https://doi.org/10.1016/j.cej.2021.129017>.
- (60) Taer, E.; Apriwandi, A.; Rama, D. Solid Coin-like Design Activated Carbon Nanospheres Derived from Shallot Peel Precursor for Boosting Supercapacitor Performance. *J. Mater. Res. Technol.* **2021**, *15*, 1732–1741. <https://doi.org/10.1016/j.jmrt.2021.09.025>.
- (61) Hor, A. A.; Hashmi, S. A. Optimization of Hierarchical Porous Carbon Derived from a Biomass Pollen-Cone as High-Performance Electrodes for Supercapacitors. *Electrochim. Acta* **2020**, *356*, 136826. <https://doi.org/10.1016/j.electacta.2020.136826>.
- (62) Liu, H.; Liu, R.; Xu, C.; Ren, Y.; Tang, D.; Zhang, C.; Li, F.; Wei, X.; Zhang, R. Oxygen–Nitrogen–Sulfur Self-Doping Hierarchical Porous Carbon Derived from Lotus Leaves for High-Performance Supercapacitor Electrodes. *J. Power Sources* **2020**, *479*, 228799. <https://doi.org/10.1016/j.jpowsour.2020.228799>.
- (63) Zhang, Q.; Han, K.; Li, S.; Li, M.; Li, J.; Ren, K. Synthesis of Garlic Skin-Derived 3D Hierarchical Porous Carbon for High-Performance Supercapacitors. *Nanoscale* **2018**, *10* (5), 2427–2437. <https://doi.org/10.1039/c7nr07158b>.
- (64) Liu, H.; Gao, F.; Fan, Q.; Wei, C.; Ma, C.; Shi, J. Preparation of Novel 3D Hierarchical Porous Carbon Membrane as Flexible Free-Standing Electrode for Supercapacitors. *J. Electroanal. Chem.* **2020**, *873*, 114409. <https://doi.org/10.1016/j.jelechem.2020.114409>.
- (65) Taer, E.; Taslim, R.; Apriwandi, A. Ultrahigh Capacitive Supercapacitor Derived from Self-Oxygen Doped Biomass-Based 3D Porous Carbon Sources. *ChemNanoMat* **2022**, *8* (2), e202100388. <https://doi.org/10.1002/cnma.202100388>.
- (66) Wang, Q.; Yan, J.; Fan, Z. Carbon Materials for High Volumetric Performance Supercapacitors: Design, Progress, Challenges and Opportunities. *Energy Environ. Sci.* **2016**, *9*, 729–762. <https://doi.org/10.1039/C5EE03109E>.
- (67) Sajjad, M.; Khan, M. I.; Cheng, F.; Lu, W. A Review on Selection Criteria of Aqueous Electrolytes Performance Evaluation for Advanced Asymmetric Supercapacitors. *J. Energy Storage* **2021**, *40*, 102729. <https://doi.org/10.1016/j.est.2021.102729>.
- (68) Aldama, I.; Barranco, V.; Kunowsky, M.; Ibañez, J.; Rojo, J. M. Contribution of Cations and Anions of Aqueous Electrolytes to the Charge Stored

1  
2  
3  
4  
5  
6  
7  
8  
9  
10  
11  
12  
13  
14  
15  
16  
17  
18  
19  
20  
21  
22  
23  
24  
25  
26  
27  
28  
29  
30  
31  
32  
33  
34  
35  
36  
37  
38  
39  
40  
41  
42  
43  
44  
45  
46  
47  
48  
49  
50  
51  
52  
53  
54  
55  
56  
57  
58  
59  
60

at the Electric Electrolyte/Electrode Interface of Carbon-Based Supercapacitors. *J. Phys. Chem. C* **2017**, *121* (22), 12053–12062.

<https://doi.org/10.1021/acs.jpcc.7b03003>.

(69) Selvaraj, A. R.; Muthusamy, A.; Inho-Cho; Kim, H. J.; Senthil, K.; Prabakar, K. Ultrahigh Surface Area Biomass Derived 3D Hierarchical Porous Carbon Nanosheet Electrodes for High Energy Density Supercapacitors. *Carbon N. Y.* **2021**, *174*, 463–474.

<https://doi.org/10.1016/j.carbon.2020.12.052>

(70) Gogotsi, Y.; Simon, P. True Performance Metrics in Electrochemical Energy Storage. *Science (80-. )*. **2011**, *334* (November), 917–918.

<https://doi.org/10.1126/science.1213003>.

(71) Chen, C.; Zhao, M.; Cai, Y.; Zhao, G.; Xie, Y.; Zhang, L.; Zhu, G.; Pan, L. Scalable Synthesis of Strutted Nitrogen Doped Hierarchical Porous Carbon Nanosheets for Supercapacitors with Both High Gravimetric and Volumetric Performances. *Carbon N. Y.* **2021**, *179*, 458–468.

<https://doi.org/10.1016/j.carbon.2021.04.062>

(72) Sangtong, N.; Chaisuwan, T.; Wongkasemjit, S.; Ishida, H.; Redpradit, W.; Seneesrisakul, K.; Thubsuang, U. Ultrahigh-Surface-Area Activated Biocarbon Based on Biomass Residue as a Supercapacitor Electrode Material: Tuning Pore Structure Using Alkalis with Different Atom Sizes. *Microporous Mesoporous Mater.* **2021**, *326* (June), 111383.

<https://doi.org/10.1016/j.micromeso.2021.111383>.

(73) Zheng, L. H.; Chen, M. H.; Liang, S. X.; Lü, Q. F. Oxygen-Rich Hierarchical Porous Carbon Derived from Biomass Waste-Kapok Flower for Supercapacitor Electrode. *Diam. Relat. Mater.* **2021**, *113* (January), 108267.

<https://doi.org/10.1016/j.diamond.2021.108267>.

(74) Roy, C. K.; Shah, S. S.; Reaz, A. H.; Sultana, S.; Chowdhury, A. N.; Firoz, S. H.;

Zahir, M. H.; Ahmed Qasem, M. A.; Aziz, M. A. Preparation of Hierarchical Porous Activated Carbon from Banana Leaves for High-Performance Supercapacitor: Effect of Type of Electrolytes on Performance. *Chem. - An Asian J.* **2021**, *16* (4), 296–308.

<https://doi.org/10.1002/asia.202001342>.

(75) Taer, E.; Natalia, K.; Apriwandi, A.; Taslim, R.; Agustino, A.; Farma, R. The Synthesis of Activated Carbon Nano Fiber Electrode Made from Acacia Leaves (Acacia Mangium Wild) as Supercapacitors. *Adv. Nat. Sci. Nanosci. Nanotechnol.* **2020**, *11* (2), 25007. <https://doi.org/10.1088/2043-6254/ab8b60>.

(76) Yao, Y.; Chen, X.; Yu, N.; Wei, F.; Feng, H. Preparation and Supercapacitive Performance of Lead Dioxide Electrodes with Three-Dimensional Porous Structure. *Russ. J. Electrochem.* **2018**, *54* (7), 585–591.

<https://doi.org/10.1134/S1023193518070078>.

8.

---

**Taslim, Rika ao-2022-04301k.R1 - Manuscript Revision Request - Formatting Changes 22-Sep-2022**

1 message

ACS Omega &lt;onbehalf@manuscriptcentral.com&gt;

Thu, Sep 22, 2022 at 5:17 PM

Reply-To: guo-office@omega.acs.org

To: rikataslim@gmail.com

22-Sep-2022

Journal: ACS Omega

Manuscript ID: ao-2022-04301k.R1

Title: "Novel &lt;i&gt;Moringa oleifera&lt;/i&gt; leaves 3D porous carbon-based electrode material as high performance EDLC supercapacitor"

Author(s): Taslim, Rika; Apriwandi, Apriwandi; Taer, Erman

COVID-19 Support: Please visit the following website to access important information for ACS authors and reviewers during the COVID-19 crisis: <https://axial.acs.org/2020/03/25/chemists-covid-19-coronavirus/>

We are flexible in these unprecedented times affecting the global research community. If you need more time to complete authoring or reviewing tasks, please contact the editorial office and request an extension.

Dear Dr. Taslim:

Thank you for submitting your manuscript to ACS Omega.

We are pleased to inform you that your manuscript ao-2022-04301k.R1 is about to be accepted for publication in ACS Omega. Prior to formal acceptance please perform the following formatting changes:

\* In case your current addresses differ from the research affiliations they should be included as footnotes. (affiliations in the system and manuscript must match)

\* Please update Abstract in the system upon submission of your revision if applicable.

- Please remove ORCID IDs from the manuscript file. ORCID IDs should not be typed into the manuscript. ACS publishes only those ORCID IDs that have been properly verified and linked before the manuscript is accepted. After your ORCID ID is linked, it will be displayed automatically in all subsequently accepted manuscripts for any/all ACS journals. We do not publish ORCID IDs provided during proof review or via other communications after a manuscript is accepted for publication. For more information see Authors Guidelines at [https://publish.acs.org/publish/author\\_guidelines?coden=acsodf#orcid](https://publish.acs.org/publish/author_guidelines?coden=acsodf#orcid)

- Kindly confirm in your Author's Response whether the photos in Figure 1 were taken by one of the authors. In case they were not, please add a credit line to the caption (e.g., "Photograph courtesy of 'Author's Name'. Copyright 2022.") and clarify if the image [in figure or TOC graphic] is free domain or if permission is required. If permission is required, provide a document that shows a granted permission, and add a credit line accordingly. More information is available at [http://pubs.acs.org/page/copyright/permissions\\_otherpub.html](http://pubs.acs.org/page/copyright/permissions_otherpub.html).

- We have noticed that Figure 10e was mentioned in the text (Page 14), but was not supplied. Please supply the missing graphic or correct the manuscript text. Please note that all figures, tables, schemes and equations must be numbered consecutively with Arabic numbers starting from Figure 1/ Table 1/ Scheme 1 / Eq. 1.

- TOC graphic should be labeled as 'For Table of Contents Only'

- Kindly reconsider elements used for TOC and whether they are appropriate. It should be in accordance with guidelines: [http://pubsapp.acs.org/paragonplus/submission/toc\\_abstract\\_graphics\\_guidelines.pdf](http://pubsapp.acs.org/paragonplus/submission/toc_abstract_graphics_guidelines.pdf)

To revise your manuscript, log into ACS Paragon Plus with your ACS ID at <http://acsparagonplus.acs.org/> and select "My Authoring Activity". There you will find your manuscript title listed under "Revisions Requested by Editorial Office." Your original files are available to you when you upload your revised manuscript. If you are replacing files, please remove the old version of the file from the manuscript before uploading the new file. Please upload manuscript file that is free of any annotations or highlights.

Funding Sources: Authors are required to report ALL funding sources and grant/award numbers relevant to this manuscript. Enter all sources of funding for ALL authors relevant to this manuscript in BOTH the Open Funder Registry tool in ACS Paragon Plus and in the manuscript to meet this requirement. See [http://pubs.acs.org/page/4authors/funder\\_options.html](http://pubs.acs.org/page/4authors/funder_options.html) for complete instructions.

ORCID: Authors submitting manuscript revisions are required to provide their own validated ORCID iDs before completing the submission, if an ORCID iD is not already associated with their ACS Paragon Plus user profiles. This iD may be provided during original manuscript submission or when submitting the manuscript revision. You can provide only your own ORCID iD, a unique researcher identifier. If your ORCID iD is not already validated and associated with your ACS Paragon Plus user profile, you may do so by following the ORCID-related links in the Email/Name section of your ACS Paragon Plus account. All authors are encouraged to register for and associate their own ORCID iDs with their ACS Paragon Plus profiles. The ORCID iD will be displayed in the published article for any author on a manuscript who has a validated ORCID iD associated with ACS Paragon Plus when the manuscript is accepted. Learn more at <http://www.orcid.org>.

In publishing only original research, ACS is committed to deterring plagiarism, including self-plagiarism. ACS Publications uses Crossref Similarity Check Powered by iThenticate to screen submitted manuscripts for similarity to published material, and other software to screen previous submissions to ACS journals. Note that your manuscript may be screened during the submission process.

We look forward to seeing your paper in ACS Omega.

Sincerely,

Prof. Shaojun Guo  
Associate Editor  
ACS Omega  
Email: [guo-office@omega.acs.org](mailto:guo-office@omega.acs.org)

-----  
PLEASE NOTE: This email message, including any attachments, contains confidential information related to peer review and is intended solely for the personal use of the recipient(s) named above. No part of this communication or any related attachments may be shared with or disclosed to any third party or organization without the explicit prior written consent of the journal Editor and ACS. If the reader of this message is not the intended recipient or is not responsible for delivering it to the intended recipient, you have received this communication in error. Please notify the sender immediately by e-mail, and delete the original message.

As an author or reviewer for ACS Publications, we may send you communications about related journals, topics or products and services from the American Chemical Society. Please email us at [pubs-comms-unsub@acs.org](mailto:pubs-comms-unsub@acs.org) if you do not want to receive these. Note, you will still receive updates about your manuscripts, reviews, or future invitations to review.

Thank you.


This document is confidential and is proprietary to the American Chemical Society and its authors. Do not copy or disclose without written permission. If you have received this item in error, notify the sender and delete all copies.

**Novel *Moringa oleifera* leaves 3D porous carbon-based electrode material as high performance EDLC supercapacitor**

Journal:	ACS Omega
Manuscript ID	ao-2022-04301k.R2
Manuscript Type:	Article
Date Submitted by the Author:	n/a
Complete List of Authors:	Taslim, Rika; State Islamic University Sultan Syarif Kasim, Department of Industrial Engineering Apriwandi, Apriwandi; University of Riau - Bina Widya Campus, Department of Physics Taer, Erman; Universitas Riau - Kampus Binawidja, Department of physics

SCHOLARONE™  
Manuscripts

1  
2  
3  
4  
5  
6  
7  
8  
9  
10  
11  
12  
13  
14  
15  
16  
17  
18  
19  
20  
21  
22  
23  
24  
25  
26  
27  
28  
29  
30  
31  
32  
33  
34  
35  
36  
37  
38  
39  
40  
41  
42  
43  
44  
45  
46  
47

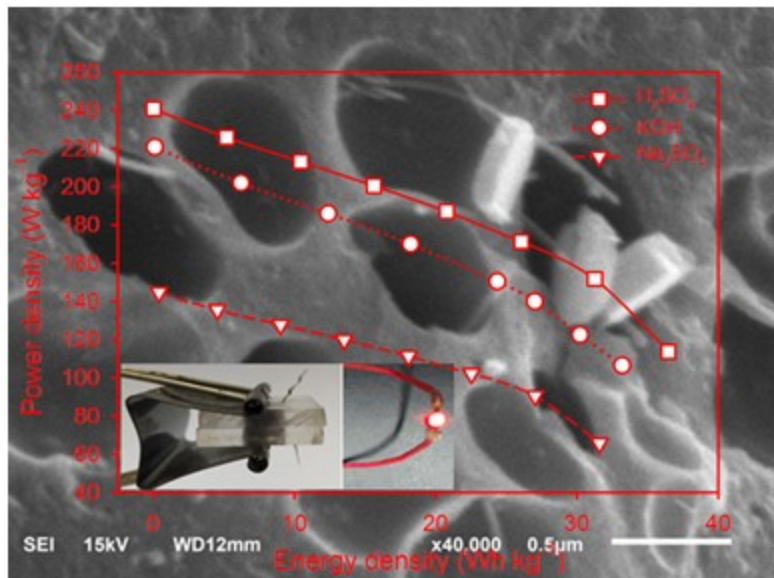

*Moringa oleifera* leaves





# Novel *Moringa oleifera* leaves 3D porous carbon-based electrode material as high performance EDLC supercapacitor

Rika Taslim,<sup>\*[a]</sup> Apriwandi Apriwandi,<sup>[b]</sup> and Erman Taer,<sup>[b]</sup>

<sup>[a]</sup> Department of Industrial Engineering, State Islamic University of Sultan Syarif Kasim, Riau, Simpang Baru-Tampan Pekanbaru, 28293 Indonesia

<sup>[b]</sup> Department of Physics, Faculty of Mathematics and Natural Sciences, University of Riau, Panam, Pekanbaru, 28293 Indonesia

E-mail: [rikataslim@gmail.com](mailto:rikataslim@gmail.com)

**Abstract.** Biomass-based activated carbon has great potential of versatile 3D porous structures as excellent electrode material in presenting high conductivity, large porosity, and outstanding stability for electrochemical energy storage devices. In this study, the electrode material develops through a novel consolidated carbon disc binder-free design, which derived from *Moringa oleifera* leaves (MOLs) for electrochemical double-layer capacitor applications. The carbon discs prepare in a series of treatments of pre-carbonized, chemical impregnation of zinc chloride, and integrated pyrolysis of N<sub>2</sub> carbonization and CO<sub>2</sub> physical activation. The physical activation temperatures apply at 650, 750, and 850°C to optimize the precursor potential. By optimizing the 3D hierarchical pore properties of the MOL750, the carbon disc binder-free design demonstrate optimal symmetric supercapacitor performance with a high specific capacitance of 307 F g<sup>-1</sup> at a current density of 1 A g<sup>-1</sup> in an aqueous electrolyte solution of 1 M H<sub>2</sub>SO<sub>4</sub>. Furthermore, the extremely low internal resistance (0.006Ω) of the carbon disc initiated excellent electrical conductivity. The supercapacitors also maintain their high capacitive properties in aqueous electrolyte solutions of 6 M KOH, and 1 M Na<sub>2</sub>SO<sub>4</sub>, respectively. The results show that a novel consolidate carbon discs binder-free design can be obtained from biomass MOLs through a reasonable approach to develop superior electrode materials to enhance high-performance electrochemical energy storage devices.

## 1. INTRODUCTION

The rapid growth of the world's population with the demands for prosperous life management has made the energy crisis the main global challenge. At the end of 2021, the energy consumption was 4.5% higher than the previous year <sup>1</sup> and is estimated to increase by more than half in the next 4 years <sup>2</sup>. Moreover, approximately 90% of the total energy demand is obtained from coal, which is non-renewable. Studies have shown that the use of coal energy sources causes significant problems in the production of CO<sub>2</sub> emissions and greenhouse gas effects, which leads to global warming and climate change <sup>3</sup>. This makes it necessary to develop effective, efficient, and pollution-free green energy technology and renewable energy conversion

systems. In the past decade, people have focused on abundant, low-cost, safe, and environmentally friendly renewable energy sources such as wind, ocean waves, solar, and biomass. However, their use was limited due to a relatively low supply of technology and complex supporting components. Several developed countries such as China and the United States have implemented renewable energy technologies as alternative sources of energy <sup>4</sup>. This situation led to the development of energy storage systems and devices with high specifications, good stability, low cost, effectiveness, and efficiency to perfect green energy technologies <sup>5,6</sup>. Among the various energy storage technologies investigated, supercapacitors received much attention due to their outstanding power transmission specifications, fast energy storage, infinite cycle stability, high

conductivity, and eco-friendly nature<sup>7-9</sup>. The main key to the superior characteristics of supercapacitor devices is their electrode-based material<sup>10,11</sup>. Various electrode-based materials can produce high and low characteristics of electronic and ionic conductivity. This significantly affects the ability of the electric charge transfusion rate and cyclic resistance of the supercapacitor<sup>12,13</sup>. Therefore, there is a need to design and develop excellent electrode materials for high-performance supercapacitors. In recent years, electrode materials have shown high specifications such as metal oxides, conducting polymers, and carbon materials. The metal oxide materials such as MnO<sub>2</sub>, TiO<sub>2</sub>, and RuO<sub>2</sub> offer high oxidation states for efficient charge transfer during redox reactions, which generate Faradic currents and ion intercalation that favor charge storage, high capacity and conductivity, as well as low toxicity<sup>14-16</sup>. According to Wang *et al.* (2021), the mixed metal oxide material has produced a specific capacitance of 788 F g<sup>-1</sup> with an energy density of 138 Wh kg<sup>-1</sup><sup>17</sup>. Similar results were also confirmed in polymeric materials that produce high energy density<sup>18</sup>. The polymeric materials allow flexible design, which is considered to be more practical, modern, and generally acceptable. The excessive consumption of metal and high-cost polymeric materials with their complicated production methods, low porosity, and corrosive properties significantly increased the risk of mass production and limit their wider application.

Similarly, carbon materials, especially activated carbon, are of greater concern due to their lower production costs, abundant availability, suitable pore structure, and very high porosity properties<sup>7,19</sup>. The biomass-based activated carbon provides a 3D hierarchical pore structure of a combination of micro, meso, and macropores that enable the electrode material to produce high energy and power densities simultaneously<sup>20,21</sup>. Moreover, the self-doping of N/O/P on carbon-based biomass also confirmed their high advantage<sup>22</sup>. Activated carbon from the leaves of *Parthenium hysterophorus* (biomass) has shown a 3D porous structure with a high surface area of 4014 m<sup>2</sup> g<sup>-1</sup> recently, followed by oxygen self-doping<sup>23</sup>. This characteristic has increased the storage capacity of a symmetric supercapacitor to 270 F g<sup>-1</sup>. The adjustable micro:macropores ratio of activated carbon from pecan shells can also produce an extraordinary specific capacitance of 447 F g<sup>-1</sup><sup>24</sup> and display high electrochemical properties with a surface area of 1,785 m<sup>2</sup> g<sup>-1</sup>. This showed that the high surface area does not guarantee the high electrochemical

properties of the supercapacitor. Some suspicions of tuning micro-mesopores, heteroatom self-doping, and the natural conductivity of the materials also contribute to the improvement of their electrochemical properties. Similar results were also obtained from other organic-based activated carbon sources such as wood powders<sup>25</sup>, feather finger grass flower<sup>26</sup>, camellia pollen<sup>27</sup>, and peach gum<sup>28</sup>. Meanwhile, the electrode materials of biomass-based activated carbon possessed energy density disproportionately with their power density and electrical/ionic conductivity far from metal oxide materials and conducting polymer due to high porosity, which hinders their practical application. Therefore, it is necessary to design a biomass-based porous carbon with a novel, easy, inexpensive, and approach for environmentally friendly, pollution-free, and high-performance supercapacitors.


Therefore, this study aims to develop a novel electrode material design from *Moringa oleifera* leaves biomass-based consolidated solid carbon discs to increase the storage capacity of symmetric supercapacitor devices. The proposed carbon discs are prepared binder-free, whose treatment consists of pre-carbonization, chemical impregnation (ZnCl<sub>2</sub>), and integrated pyrolysis of N<sub>2</sub> carbonization and physical activation of CO<sub>2</sub>. The potential for activated carbon precursors was also maximized through different pyrolysis temperatures 650, 750, and 850°C. Moreover, the carbon discs of MOLs exhibit 3D hierarchical pore properties with oxygen heteroatoms as their additional oxidative property. The optimized carbon disc exhibits a high specific capacitance of 307 F g<sup>-1</sup> in the 1 M H<sub>2</sub>SO<sub>4</sub> electrolyte. This showed that the proposed design is a reasonable approach to increase the symmetric storage capacity of pollution-free, low-cost, and high-performance supercapacitors.

## 2. RESULTS AND DISCUSSION

### 2.1. Material analysis

Density analysis is an important aspect for the evaluation of carbon MOLs in form of binder-free consolidated discs. This section shows the analysis of changes in the density of the carbon discs of MOLs at different temperatures of pyrolysis treatments. The precursor powder pressed at a predetermined load was properly compacted at a diameter of ±19.00 mm, a thickness of ±2.00 mm, and a mass of ±0.70 gr (see Figure 1a). The potential precursors of the confirmed MOLs formed a strong/resistant and a fracture-free consolidated disc with a smooth surface. Their biological composition and complex compounds can act as

self-adhesives to enable the formation of binder-free strong discs.

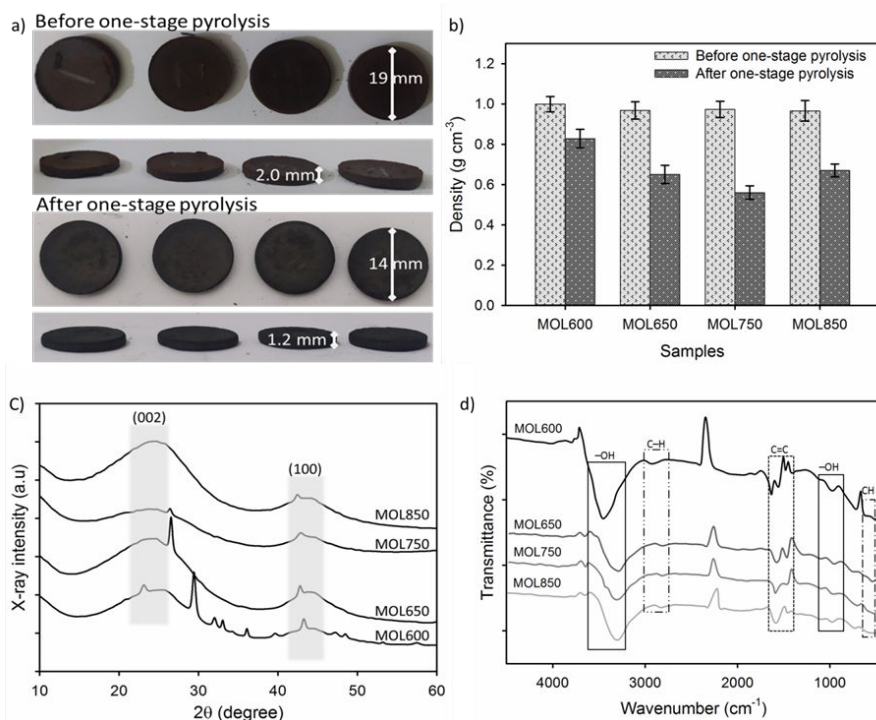

**Figure 1.** a) Dimensions of binder-free consolidated discs before and after pyrolysis (Photograph courtesy of Apriwandi Apriwandi. Copyright 2022.), b) Changes in the density of the carbon discs of MOLs at different temperatures of pyrolysis treatments, c) XRD pattern of MOLs disc at different pyrolysis temperatures, and d) FTIR spectrum of the MOLs carbon disc at a wavenumber of 4500-450  $\text{cm}^{-1}$ .

A similar case was also stated in a previous study using banana leaves as a precursor<sup>29</sup>. In this study, the average densities of the samples MOL600, MOL650, MOL750, and MOL850 were 0.9990, 0.9680, 0.9730, and 0.9660  $\text{g cm}^{-3}$ , respectively. The discs of consolidated MOLs were pyrolyzed at high temperatures, including carbonization in an  $\text{N}_2$  gas environment and physical activation in a  $\text{CO}_2$  gas environment and their final process was evaluated for overall dimensional changes<sup>30</sup>. As shown in Figure 1b, the disc density of the consolidated MOLs degraded significantly after the high-temperature pyrolysis process due to a significantly large mass loss. Pyrolysis initiated from 30°C to 850°C for over 10 hours significantly degraded the disc dimensions, where their diameter, thickness, and average mass were reduced to  $\pm 14.00$ - $13.00$ mm,  $\pm 1.2$ - $1.0$ mm, and 0.2-0.1 gr, respectively. After the pyrolysis process, the MOLs disc density decreased to 0.8280, 0.6500, 0.5600, and 0.6700  $\text{g cm}^{-3}$  for samples MOL600, MOL650, MOL750, and MOL850, respectively.

The evaporation of volatile compounds, water content, and decomposition of the biological composition of the precursor during the chemical reaction of  $\text{ZnCl}_2$  at high-pyrolysis temperature caused the reduction of the density of MOLs discs. Furthermore, the physical appearance of the disc

sample is relatively solid black, which indicated a high fixed carbon content. The 42.44% density degradation initiated the formation of a diverse pore framework which is needed as a good electrode material for electrochemical energy storage devices. The different pyrolysis temperatures from 600°C to 750°C affect their respective densities by degrading the MOLs disc density to 32.36%. This is due to the erosion of the carbon framework which causes the expansion of larger pores and initiates the formation of macropores within the micron scale. From the pyrolysis temperature of 750°C to 850°C, the density of the disc increased by 16.41% due to excessive erosion of the carbon pore walls. This makes the carbon skeleton unable to maintain the structure above, thereby, it collapsed and covered the pores below. However, these results are relatively normal for solid carbon samples.

The material structure of the carbon disc MOLs was evaluated through X-ray diffraction (XRD) and Fourier transforms infrared (FTIR) techniques. Figure 1c shows the XRD pattern of disc MOLs at different pyrolysis temperatures of 600, 650, 750, and 850°C. The carbon discs showed strong broad peaks at angles 24° and 44° correlated with the (002) and (100) scattering planes, which confirmed the turbostratic carbon structure (JCPDS No. 29-1126, 29-1127)<sup>31</sup>. The high-temperature pyrolysis

of the precursor MOLs allows the decomposition and rearrangement of the carbon structure to initiate good amorphous behavior<sup>32</sup>.

**Table 1.** Microcrystalline parameters and elemental status of MOLs carbon disc at different physical activation temperature.

Carbon disc MOLs	Microcrystalline parameters				Elemental status				
	$d_{002}$ (Å)	$d_{100}$ (Å)	$L_c$ (Å)	$L_a$ (Å)	C (%)	O (%)	Ca (%)	Cl (%)	Zn (%)
MOL600	3.524	2.077	13.391	22.159	79.45	17.41	2.28	0.87	0.00
MOL650	3.616	2.051	12.297	16.903	85.97	10.49	0.63	0.68	2.24
MOL750	3.698	1.994	7.481	23.866	88.54	8.06	1.11	0.64	1.65
MOL750	3.689	1.993	10.323	18.144	88.91	8.45	1.38	0.60	0.66

Furthermore, the properties of the carbon disc structure of MOLs changed during the high-temperature pyrolysis process including carbonization and physical activation. The hkl (002) plane possesses broad peak attenuation from 600 to 850°C, which significantly reduced the crystalline properties and initiate the formation of abundant micro-mesoporosity<sup>33</sup>. This property improves the electro-active site of the electrode material in energy storage systems. Meanwhile, the sharp peaks in the sample were significantly reduced from 600 to 850°C, indicating the presence of a small amount of crystal structure of the compound CaCO<sub>3</sub> and ZnO at angles of 23°, 26°, 29°, 32°, 36°, and 43°.

These compounds are the contribution of organic precursor components and by-products of their chemical impregnation. The CaCO<sub>3</sub> compound is located at an angle of 23.165°, 29.255°, 32.050°, 36.095° (JCPDS No. 06-0230) and the ZnO compound in very small amounts at 26.05°-26.395° (JCPDF No. 36-1451)<sup>34,35</sup>. The MOLs600 sample that was carbonized at 600°C produced an XRD pattern, containing several CaCO<sub>3</sub> crystalline compounds. The application of physical activation in the CO<sub>2</sub> gas environment reduced the CaCO<sub>3</sub> compounds as shown in MOLs650, MOLs750, and MOLs850, as described EDS technique in Table 1. Moreover, high-temperature pyrolysis obtains carbon discs with a well amorphous structure. Table 1 summarizes the interlayer spacing and microcrystalline dimensions of the MOLs carbon discs at pyrolysis temperatures ranging from 600 to 850°C. The value of  $d_{(002)}$  of MOLs is slightly higher than  $d_{(002)}$  of graphite by approximately 3.46%, while  $d_{(100)}$  indicates a relatively ideal for

amorphous carbon-based biomass as stated in previous studies<sup>36,37</sup>. Furthermore, the microcrystalline dimension ( $L_c$ ) is closely related to the specific surface area and the active channel on the electrode material, which is often related through empirical equations<sup>38,39</sup>. Based on this empirical equation,  $L_c$  showed that the specific surface area inversely, where a low  $L_c$  allows the electrode disc to obtain a high surface area. From Table 1, the carbon discs pyrolyzed at 750°C temperature showed higher surface area than others.


Figure 1d shows the FTIR spectrum of the carbon disc MOLs at a wavenumber of 4500-450 cm<sup>-1</sup>. Generally, different pyrolysis temperatures, namely 600, 650, 750, and 850°C of the MOLs precursors exhibited stretching vibrations of -OH, C-H, C=C, C-O, CH<sub>2</sub>, and C-H aromatics<sup>40,41</sup>. This functional group is considered normal for porous activated carbon based on organic waste. The carbon discs pyrolyzed at 600°C (carbonization only) showed significant absorption at several wavenumbers compared to higher temperatures. Furthermore, the highest absorption was discovered in the band 3,463-3,309 cm<sup>-1</sup> due to stretching vibration of -OH<sup>42</sup>, which was also discovered in wavenumber 1,491-1,422 cm<sup>-1</sup>. Stretching vibration of C-H was indicated at wavenumbers 2,926 cm<sup>-1</sup> and 978 cm<sup>-1</sup>, while 1,652 cm<sup>-1</sup> and 1,553 cm<sup>-1</sup> were the stretching vibrations of C=C. Meanwhile, the absorption band in the range 1,300-1,010 cm<sup>-1</sup> represents the C-O functional group, while CH aromatic is were in the 770-709 cm<sup>-1</sup> and 540-518 cm<sup>-1</sup><sup>43</sup>. The abundance of C and O in this functional group indicates their relatively high content in carbon disc MOLs as shown in Table 1. At higher temperatures, the pyrolysis of

MOL650, MOLs750, and MOL850 integrated with the one-stage carbonization and physical activation process showed relatively different absorption patterns. The stretching vibrations of C-O and -OH decreased significantly at MOL650, MOL750, and MOL850, as shown in the absorption bands of 3,400-3,300  $\text{cm}^{-1}$  and 1,300-1,010  $\text{cm}^{-1}$ . This is due to the physical activation in the  $\text{CO}_2$  gas environment treatment, maximizing the evaporation process of organic compounds and rearranges the carbon framework, thereby, possessing FTIR spectra that are nearly ideal for porous activated carbon. Meanwhile, MOL750 showed the lowest absorption band, followed by the removal of some absorbance, especially on stretching vibration of C-O and CH aromatic<sup>40,43</sup>. This indicated that the FTIR spectra obtained are the most ideal compared to the others. The presence of a relatively confirmed -OH functional group provides wettability and hydrophilicity properties for the electrode material<sup>44,45</sup>. This property is used as a heteroatom to increase the effect of extra pseudo-capacitance in electrochemical energy storage devices. Similar results were also shown by EDS and electrochemical properties analyses.

The energy dispersive spectroscopy (EDS) was carried out at a voltage of 15.0kV within the energy range of 0-20.0 keV to analyze the elements of consolidated carbon discs MOLs that were pyrolyzed at high temperature. Meanwhile, the details elemental status of the carbon disc MOLs is summarized in Table 1. It was shown that carbon (C) is the component of the highest consolidated disc with approximately 79-89% and oxygen (O) heteroatoms 8-17%, followed by other elements in very small amounts such as potassium (Ca), chlorine (Cl), and zinc (Zn). These results are in line with the previously discussed XRD and FTIR analyzes. The carbonization process at 600°C in the  $\text{N}_2$  atmosphere significantly obtained high pure carbon of 79.45%. This

also supported the density analysis where volatile, water content, complex organic compounds evaporated and degraded. However, as a by-product, they still leave oxygen in form of an oxide compound of 17.41%. An increase in the pyrolysis temperature on physical activation using  $\text{CO}_2$  increased the elemental carbon by 88.91% at MOL850, while the elemental oxygen is reduced regularly and remains 8.06% at MOLs750. The element Zn appears because the byproduct of chemical impregnation  $\text{ZnCl}_2$  is not completely evaporated. Meanwhile, the elements Ca and Cl are the contributions of the organic components of the precursor MOLs. The high pure carbon element obtained in the consolidated disc MOLs also allows the electrode material to have high conductivity properties to boost the electrochemical behavior of the supercapacitor<sup>46</sup>. The elemental oxygen can also contribute to self-heteroatom and provide additional pseudo-capacitance to the disc carbon-based electrode material of consolidated MOLs.


The morphological structures of the obtained consolidated MOL carbon discs were reviewed by scanning electron microscopy (SEM) as shown in Figure 2. Binder-free carbon discs pyrolyzed using 600-850°C different temperatures exhibited a 3D connected pore-rich surface structure. Precursor MOLs that were impregnated with  $\text{ZnCl}_2$  at 600°C showed a smooth surface with clear micron-scale pore channels. In the selected area, MOL600 maintains the natural pore structure of MOLs at the nano and micro scale. The pores obtained were dominated by mesopores in the 23-46 nm range and rich in micropores. Furthermore, the  $\text{ZnCl}_2$  impregnation maximizes the potential of MOLs precursors to provide rich pores through evaporation and gradation of their organic compounds<sup>47</sup>. Figure 2b confirms the mesoporous rich structure in the range of 24 to 49 nm and macropores in the 100 nm scale.

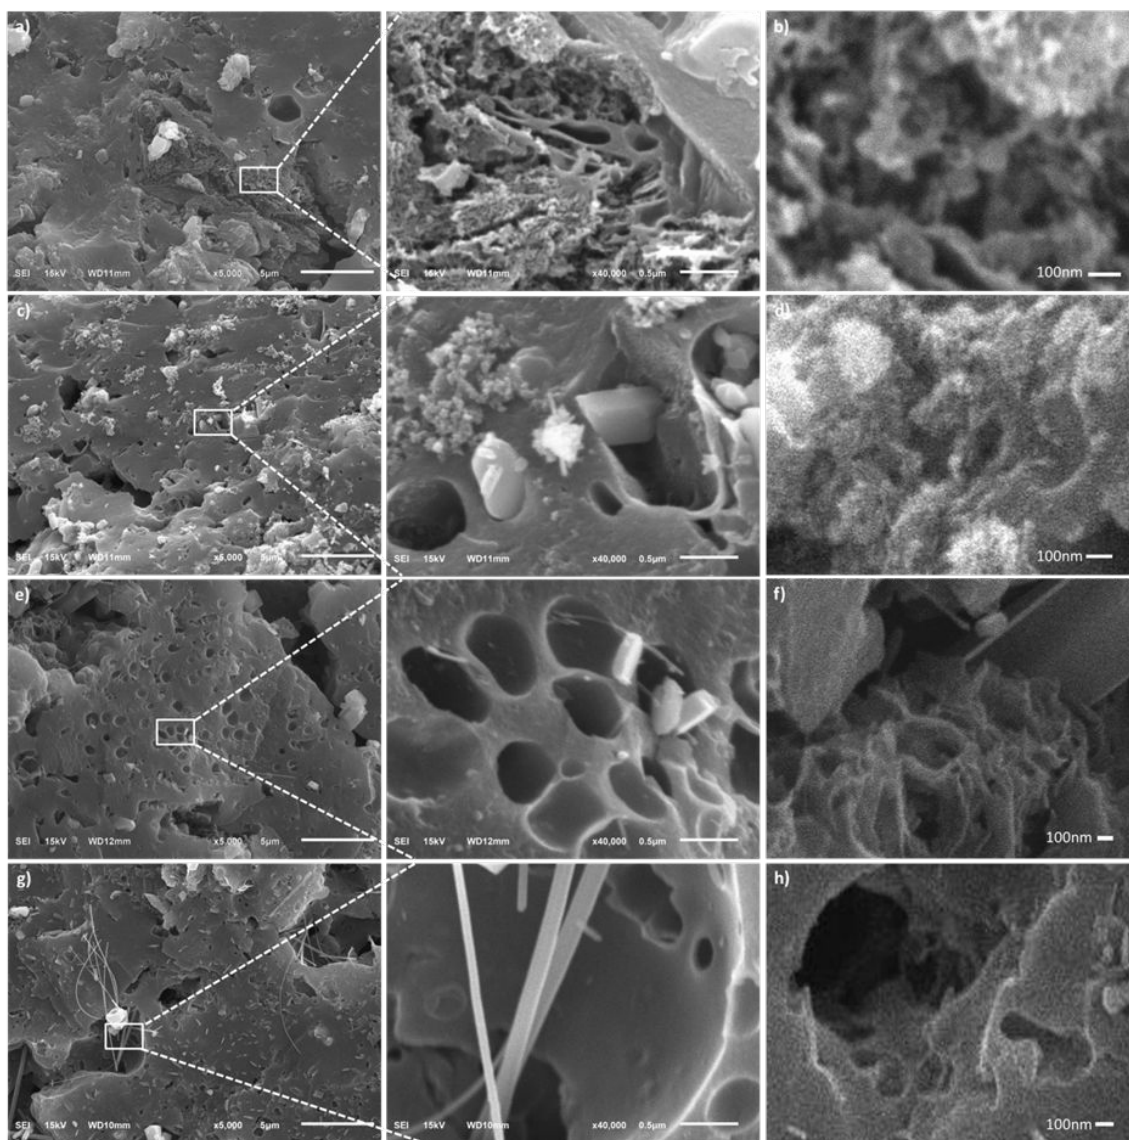

**Figure 2.** SEM image of (a) MOL600, (b) MOL600 at closer zoom, (c) MOL650, (d) MOL650 at closer zoom, (e) MOL750, (f) MOL600 at closer zoom, (g) MOL850, and (h) MOL850 at closer zoom.

This is useful as an electrolyte reservoir in the electrochemistry of supercapacitors<sup>48</sup>. When the pyrolysis temperature was increased to 650°C in the CO<sub>2</sub> physical activation process, the surface structure was decorated with holes in the diameter which ranged from 65 nm to 1,261 nm as shown in Figure 2c. The physical activation of CO<sub>2</sub> significantly grows the rich macropores by grinding the carbon skeleton, which is released in form of CO, H<sub>2</sub>O, and CO<sub>2</sub><sup>49</sup>. Through a closer zoom, SEM micrographs confirmed the presence of multiple pores connected in 3D hierarchies, where the


macropore walls contain mesopores in small numbers. Figure 2d also shows the expansion of the pores towards a larger direction due to high-temperature carbon skeleton grinding compared to Figure 2b. Meanwhile, increasing the pyrolysis temperature to a higher at 750°C allows MOLs750 to have abundant pores as shown in Figure 2e. The various pore structures obtained range from 500-900 nm. Figure 2f shows morphology 3D carbon foam-like interconnected by thin sheet-like struts and open pores with a diameter of several tens of nanometers.

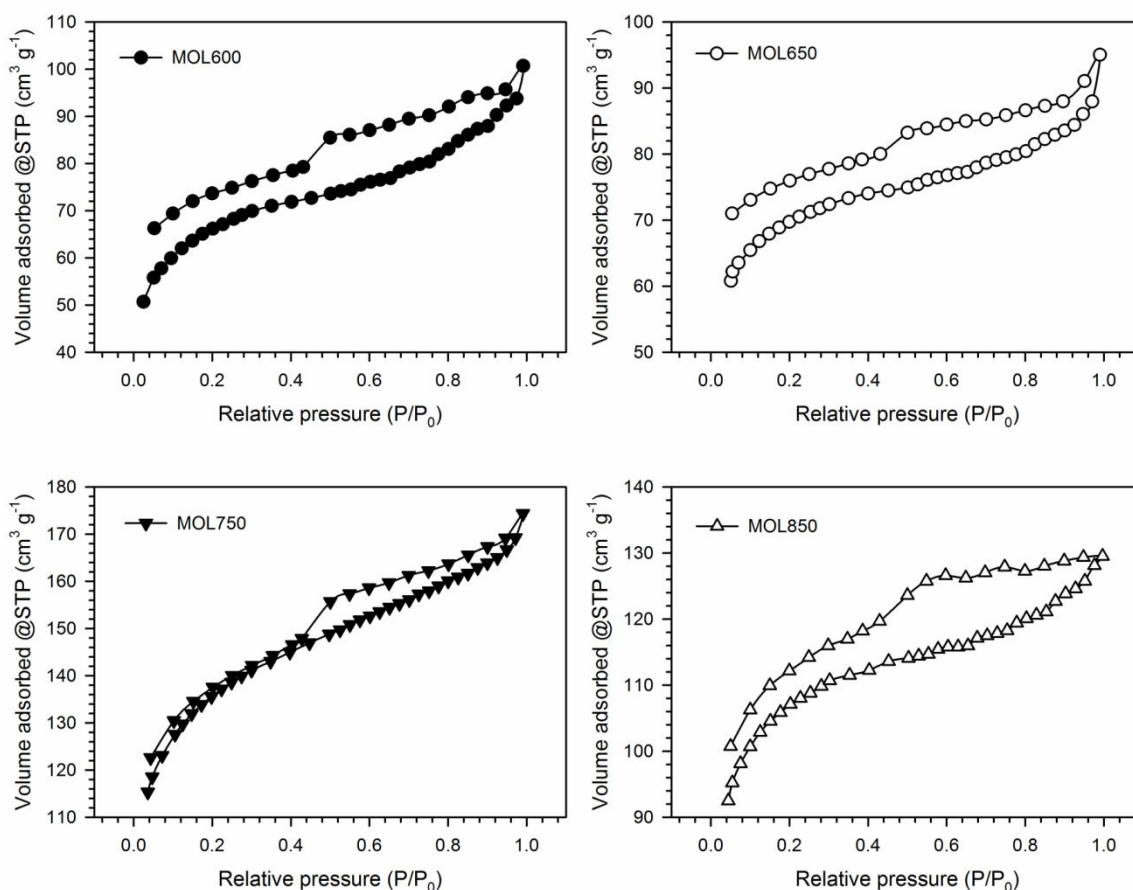

**Figure 3.**  $N_2$  gas absorption profiles of the MOLs carbon disc.

This pore structure significantly contributes to an increase in the amount of ionic charge transfer and electro-active activity in the MOLs of the electrode material<sup>50</sup>. These morphological properties are expected to cause high capacitive properties with greater energy density and power in symmetric supercapacitor devices. Increasing the pyrolysis temperature to 850°C at MOL850 led to a more severe etching of the carbon matrix, causing considerable pore dilation. Subsequently, the 3D hierarchical porous structure becomes visible as shown in Figure 2g and their magnification selected area. Moreover, MOL850 exhibits a 2D nanofiber structure at a diameter of approximately 73-188nm, which can lead to the distribution of micropores on their surface. Figure 4h shows the abundant 3D pore morphology connected hierarchically between mesopores and macropores. The analysis showed that

increasing the pyrolysis temperature etches the carbon framework giving rise to a 3D porous carbon framework connected to nanoscale 2D nanosheets and nanofibers on MOLs carbon discs. These results indicated that the proposed approach can significantly increase the proportion of hierarchically connected mesopores/macropores in carbon MOLs. Therefore, excellent material properties can be achieved to improve the performance of electrode materials in electrochemical energy storage devices. A more detailed analysis of the pore structure was confirmed through the  $N_2$  adsorption-desorption isotherm characterization. The MOLs carbon discs obtained from the integrated single-stage pyrolysis process at different temperatures of 600-850°C have type  $N_2$  gas absorption profiles as shown in Figure 3.

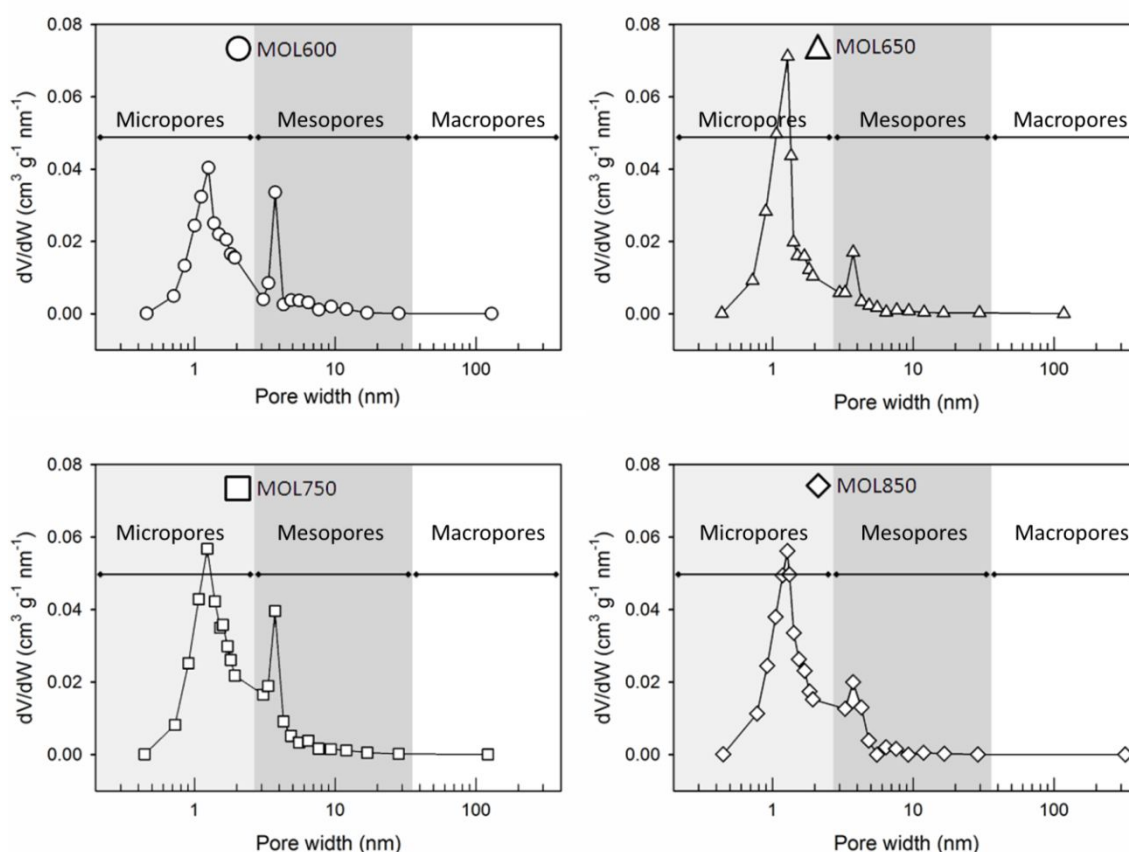

**Figure 4.** Pore size distribution of the MOLs carbon discs.


The MOL600 carbon discs obtained by carbonization at 600 temperatures have the lowest isotherm curve with mixed types I and IV. This confirmed a low specific surface area of  $207 \text{ m}^2 \text{ g}^{-1}$  with micro and mesopore structures at a ratio of 65.30% and 34.70%, respectively. After the physical activation of  $\text{CO}_2$  on MOL650, MOL750, and MOL850 carbon discs, the absorption curve regularly increased. This indicated higher pore properties and specific surface areas that exhibit mixed type I and IV isotherm curves with an H4 type hysteresis loop. It also showed a hierarchical pore combination of micropores and mesopores that are connected<sup>51,52</sup>. Furthermore, the hysteresis loops are open due to the physical structure of the imperfectly developed pores, where their upper surface is smaller than the inner structure and is usually called a bottleneck pore in several studies<sup>36</sup>. Increasing the physical activation temperature from 650 to  $750^\circ\text{C}$  can

significantly increase the specific surface area by approximately 2 times from  $211 \text{ m}^2 \text{ g}^{-1}$  to  $412 \text{ m}^2 \text{ g}^{-1}$ . The distribution of their micro and meso surface areas also changes, which affects the electro-active properties of the electrode material. Abundant micropores promote the material by providing rich channels for ion adsorption, which create an electrical layer, while high mesopores contribute to increased barrier-free charge flow<sup>53,54</sup>. Moreover, MOLs750 indicated the presence of a macropore structure in small amounts as shown by an increase in uptake at a relative pressure of  $0.95 \leq P/P_0 \leq 1.0$ . The macropore structure can also act as a reservoir for electrolyte ions after the confirmation of the electrochemical properties of the supercapacitor<sup>55</sup>, which is in line with the SEM analysis as shown in Figure 2. The complete combination of micro, meso, and macroporous structures in MOL750 is expected to increase the high performance of MOLs precursor-based



supercapacitors. An increase in the physical activation temperature to approximately 850°C in the MOL850 samples exhibited a reduction in N<sub>2</sub> gas uptake with their specific surface area of about 322 m<sup>2</sup> g<sup>-1</sup>. There is a possibility that the overgrowth of

the pores prevents their walls from maintaining the carbon skeleton for the top to collapse and cover the pores below. The pore structure parameters are shown in Table 2, while the pore size distribution of the MOLs carbon discs is shown in Figure 4.

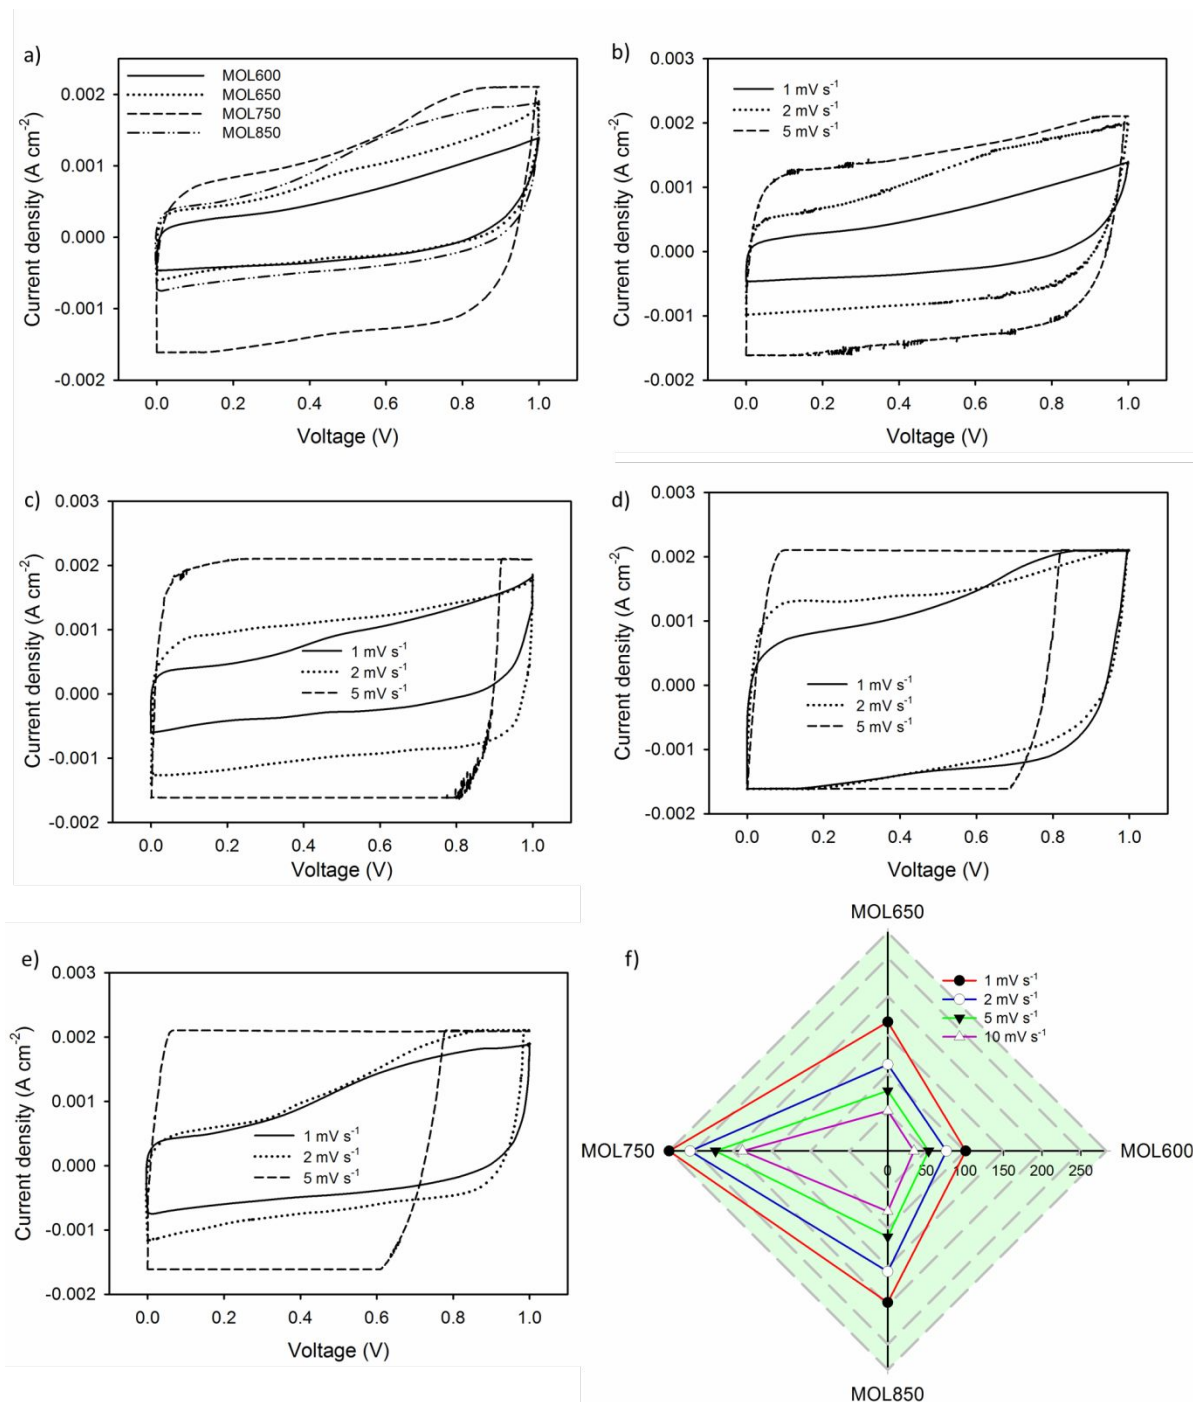

**Figure 5.** a) CV curve of the MOLs carbon disc at a scan rate of 1 mV s<sup>-1</sup>, b)-e) CV curve in different scan rate of MOL600, MOL650, MOL750, and MOL850, and f) capacitive performance of carbon MOLs in different scan rate in 1M H<sub>2</sub>SO<sub>4</sub> electrolyte.

The pyrolyzed carbon disc MOLs at different temperatures showed an abundant pore distribution of micropores ( $x \leq 2$  nm), which is rich in mesopores ( $2 \leq x \leq 18$  nm). Carbonized discs at  $600^\circ\text{C}$  temperatures gave a relatively balanced micro-mesopores distribution with an average pore diameter of 3.0 nm. The physical activation treatment of  $\text{CO}_2$  at a temperature of  $650\text{--}850^\circ\text{C}$  also gave abundant micropores, which were dominated by 1.7 nm micropores. In addition, this treatment reduced the mean pore diameter to approximately 2.4 nm as shown in Table 2. These results confirm the formation of a hierarchical pore structure that develops more conducive to charge/ion storage at the electrode/electrolyte interface<sup>56,57</sup>. Furthermore, the physical activation of  $\text{CO}_2$  at different temperatures indicated that the hierarchical pore structure varied in the pore ranging from 1.4 to 2.7 nm. The potential for MOLs precursors was also confirmed to obtain 3D hierarchical porous carbon discs.


**Table 2.** Porosity properties of MOLs

Carbon samples	$S_{\text{BET}}$ ( $\text{m}^2 \text{g}^{-1}$ )	$S_{\text{micro}}$ ( $\text{m}^2 \text{g}^{-1}$ )	$S_{\text{meso}}$ ( $\text{m}^2 \text{g}^{-1}$ )	$V_{\text{tot}}$ ( $\text{cm}^3 \text{g}^{-1}$ )	$D_{\text{aver}}$ (nm)
MOL600	207.482	135.500	71.982	0.1558	3.0
MOL650	211.334	165.167	46.167	0.1470	2.7
MOL750	412.196	313.343	98.853	0.2697	2.6
MOL850	322.008	264.035	57.973	0.2004	2.4

## 2.2. Electrochemical performance analysis

The electro-active interactions of ionic charge and carbon-based MOLs electrodes were reviewed in detail through cyclic voltammetry (CV) and galvanostatic charge-discharge (GCD) in a two-electrode system in 1 M  $\text{H}_2\text{SO}_4$  electrolyte. Figure 5a shows the CV curve of the carbon disc MOLs at a scan rate of  $1 \text{ mV s}^{-1}$ , showing a nearly perfect rectangular shape in a potential window of 0 to 1 V. This showed the electro-active properties of the normal electrically double-layered carbon disc MOLs. Furthermore, the spike in current density in the potential window of 0.4 to 0.6 V characterizes the additional pseudocapacitance due to the contribution of the

heteroatoms as self-doping<sup>58</sup>. It was also discovered that the highest specific capacitance was in the MOL750 carbon disc of  $283 \text{ F g}^{-1}$ , characterized by the largest rectangular shape, while the lowest capacitance was in MOL600 of  $101 \text{ F g}^{-1}$ . The CV curve of MOL650 shows a rectangular shape that is larger than MOL600. This indicated that the  $\text{CO}_2$  physical activation treatment can significantly increase the capacitive properties of MOL650 discs to approximately  $196 \text{ F g}^{-1}$ . The physical activation of  $\text{CO}_2$  can significantly maximize the impurity evaporation process, thereby, initiating the formation of a rich micro-mesopore structure, which allows more ions to diffuse at the electrolyte/electrode interface.

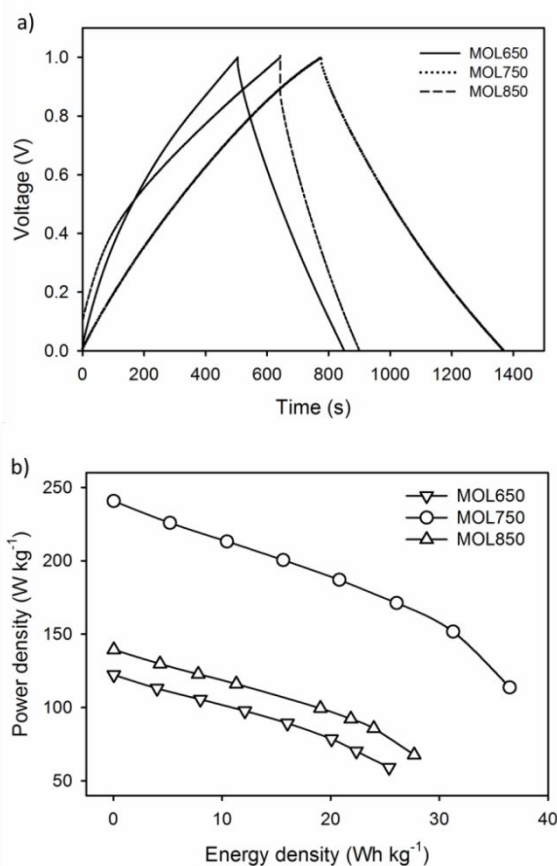


**Figure 6.** a) GCD curves of the disc electrode MOLs in 1M  $\text{H}_2\text{SO}_4$  electrolyte, and b) Ragone plot of the disc electrode MOLs in 1 M  $\text{H}_2\text{SO}_4$  electrolyte.

The application of a higher activation temperature can maximize the potential of

1  
2  
3 the MOL750 carbon disc also confirmed the  
4 greatest capacitive properties. This is  
5 contributed by their compactly consolidated  
6 material structure with a 3D hierarchical  
7 structure, followed by an increase in specific  
8 surface area. However, the addition of a  
9 higher temperature to 850°C reduces the  
10 specific capacitance to 211 F g<sup>-1</sup>. This is  
11 because the intense pore expansion can  
12 reduce their surface area as shown in Figure  
13 3 and Table 1, which reduced the  
14 electrochemical properties of MOL850. The  
15 carbon discs MOL600, MOLs650,  
16 MOLs750, MOL850 were evaluated at  
17 various scanning levels as shown in Figure  
18 5b-e to confirm the effect of pores on the  
19 performance of the electrode material. It was  
20 also discovered that the curve presents a  
21 wide rectangular distortion at a scanning  
22 speed of 2-5 mV s<sup>-1</sup>, which shows a good  
23 EDLC performance. The pseudo-  
24 capacitance property was not confirmed at  
25 the scanning levels of 2 and 5 mV s<sup>-1</sup>,  
26 therefore, it can be speculated that the  
27 electrode material has a weak heteroatom  
28 self-doping<sup>59</sup>. Furthermore, at 5 mV s<sup>-1</sup>, CV  
29 curves are obviously different with a  
30 significant increase in current followed by  
31 an unusual shape indicated due to their  
32 relatively low pore structure. This is  
33 confirmed similar to the previous study<sup>31,60</sup>.  
34 Moreover, the higher scan rate also confirms  
35 the performance of the capacitive properties  
36 of carbon MOLs as shown in Figure 5f. The  
37 scan rate treatment of 1 to 10 mV s<sup>-1</sup>  
38 significantly reduced the specific  
39 capacitance caused by their pore size  
40 distribution. However, the MOLs750 carbon  
41 disc was able to maintain a specific  
42 capacitance of 78% at a scan rate of 10 mV  
43 s<sup>-1</sup>. Figure 6a shows the GCD curves of the  
44 disc electrode MOLs at higher physical  
45 activation temperatures of 650, 750, and  
46 850°C in a current density of 1 A g<sup>-1</sup>. It  
47 also showed a distorted isosceles triangle  
48 shape, which indicated the nature of the  
49 ideal electric double layer. Furthermore,  
50 the iR drop on the barely visible curve  
51 indicates low ion diffusion resistance<sup>61</sup>.  
52 Their charge times, which were greater than  
53 discharge

times indicated ion degradation due to the  
presence of self-doping heteroatoms  
associated with the redox reactions of  
oxygenated surface functions in the aqueous  
electrolyte of 1 M H<sub>2</sub>SO<sub>4</sub><sup>22,62</sup>. This is  
supported by the high level of oxygen in the  
MOLs carbon disc of approximately  
8.06–17.41%. The long charge-discharge  
time of the MOLs disc electrodes  
characterizes the increase in specific  
capacitance after the CO<sub>2</sub> physical activation  
process at temperatures of 650, 750, and  
850°C. The MOLs750 disc electrodes  
exhibited the longest discharge time,  
showing that their highest capacitance was  
307 F g<sup>-1</sup>, followed by MOLs850 and  
MOLs650 221 and 156 F g<sup>-1</sup>, respectively.  
This is directly affected by the increase in  
surface area and accessible pore volume in  
the carbon disc MOLs, which are required  
for electrolytic ion charge accumulation and  
fast unimpeded transport. The physical  
activation at a high temperature can  
significantly increase the specific surface  
area, followed by an increase in the total  
pore volume and their pore size distribution,  
which is rich in 3D micro-mesopores<sup>54,63</sup>.  
The results also showed that MOLs carbon  
discs have the highest specific surface area  
of 433 m<sup>2</sup> g<sup>-1</sup> with a maximum total volume  
of 0.244 cm<sup>3</sup> g<sup>-1</sup>. This allows them to have a  
high accumulation of electrolyte ions,  
thereby, forming more electro-active layers.  
The hierarchically connected 3D rich  
mesopores structure of MOLs750 confirms  
their almost unimpeded access to ion  
transport and the range of diffusion in all  
directions acting as a reservoir for  
electrolyte ions<sup>64</sup>. This can significantly  
improve the capacitive properties of the  
MOLs carbon electrodes as shown in the  
MOLs650 to MOLs750 electrodes. An  
increase in temperature to approximately  
850°C at the MOLs850 carbon disc reduced  
its capacitive properties as shown by  
excessive pore expansion. This can cause  
the pore framework to collapse and cover  
the hierarchical pores below, which reduced  
their surface area and pore volume (Table  
1).

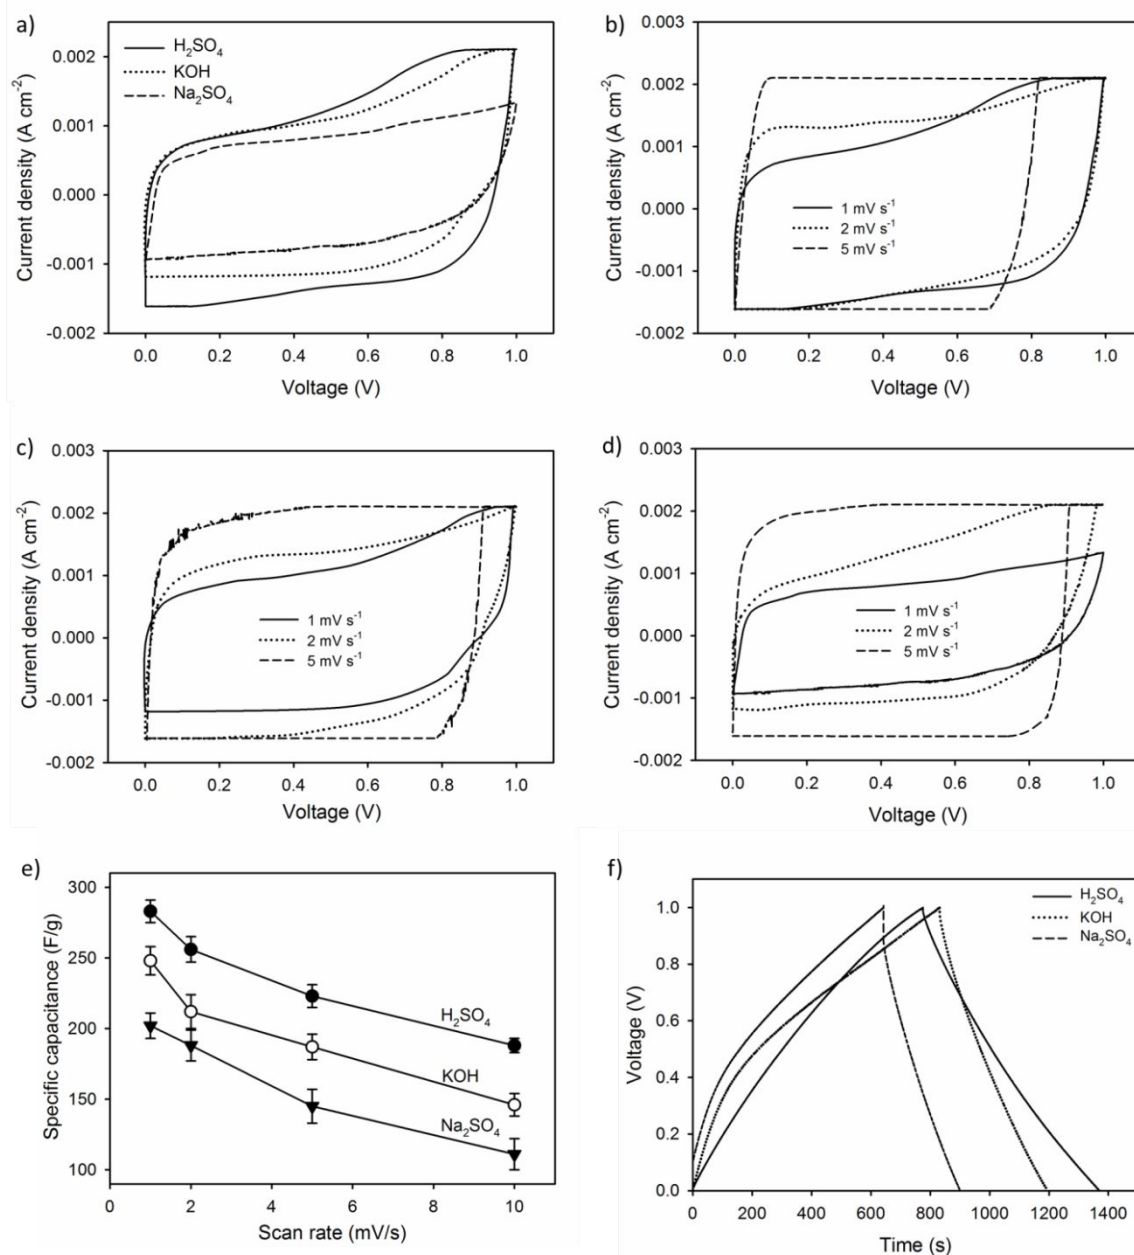

**Figure 7.** a) CV curve of the MOLs750 carbon in different aqueous electrolytes, b)-d) Improved CV scanning was also applied to MOLs750 in different aqueous electrolytes, e) capacitive performance of carbon MOLs in different scan rate in different aqueous electrolytes, and f) GCD curve of the MOLs750 carbon in different aqueous electrolytes.

However, the GCD curve of MOLs750 has the least symmetrical isosceles triangle shape due to the pseudo-capacitance effect of oxygen heteroatoms<sup>17,50</sup>. The results obtained from GCD are very similar to SEM, EDS, N<sub>2</sub> adsorption/desorption, and CV images. The Ragone plots confirm the energy and power densities of the MOL650,

MOL750, and MOL850 disc electrodes as shown in Figure 6b. Meanwhile, the Ragone plot tends to show that the energy density rises as the physical activation temperature increases at high power density. The MOL650 disc electrode produces an energy density of 25.37 Wh kg<sup>-1</sup> at a power density of 122.25 W kg<sup>-1</sup>. An increase in the

physical activation temperature on the MOL750 carbon disc gave the most significant energy density of 36.47 Wh kg<sup>-1</sup> at a power density of 240.73 W kg<sup>-1</sup> due to the contribution of hierarchically connected 3D micro-mesopores, specific surface area, and self-doping heteroatom. The MOLs850 disc electrode shows an energy density of 27.6876 Wh kg<sup>-1</sup> with a power density of almost 139.4286 W kg<sup>-1</sup>. These results indicated that the disc electrode MOLs can produce high properties for electrochemical

energy storage applications. Although the specific surface area of MOL750 is not very high, it can have extraordinary energy density and compete with other studies as summarized in Table 3. This is due to the efficiency of the electrode material designed as solid consolidated carbon discs, which optimized 3D hierarchical pores leading to low internal resistance, high conductivity, and producing high electrochemical performance<sup>26,27</sup>.

**Table 3.** Electrochemical performance of MOLs carbon disc in CV and GCD techniques.

Electrolyte	CV		GCD		
	C <sub>sp</sub> (F g <sup>-1</sup> )	C <sub>sp</sub> (F g <sup>-1</sup> )	E (Wh kg <sup>-1</sup> )	P (W kg <sup>-1</sup> )	R (Ω)
1 M H <sub>2</sub> SO <sub>4</sub>	283	307	36.47	240.73	0.006
6 M KOH	248	254	33.21	220.75	0.012
1 M Na <sub>2</sub> SO <sub>4</sub>	202	201	31.59	144.75	0.031


The MOL750 carbon disc electrode was evaluated through different aqueous electrolytes, namely 1 M H<sub>2</sub>SO<sub>4</sub>, 6 M KOH, and 1 M Na<sub>2</sub>SO<sub>4</sub> to confirm the high electrochemical performance. Figure 7a shows the CV curve of the MOLs750 carbon in different aqueous electrolytes. Generally, all aqueous electrolytes showed a distorted rectangular shape, which indicated good EDLC properties. In H<sub>2</sub>SO<sub>4</sub> and KOH electrolytes, there was a sudden increase in current density in the voltage range of 0.6-0.8 V. This is closely related to the redox reaction of oxygen heteroatoms under acidic and alkaline aqueous electrolytes that confirms the presence of apparent capacitance. However, it was not discovered in the neutral aqueous electrolyte Na<sub>2</sub>SO<sub>4</sub>. Based on the magnitude of the formed CV curve, the performance of MOL750 on different electrolytes can be ordered by H<sub>2</sub>SO<sub>4</sub>>KOH>Na<sub>2</sub>SO<sub>4</sub> with specific capacitances of 283, 248, and 202 F g<sup>-1</sup>. Improved CV scanning was also applied to MOLs750 in different aqueous electrolytes as shown in Figure 7b-d. All three aqueous electrolytes still produced a distorted rectangular shape, although showing widening towards a parallelogram at scan rates of 2 and 5 mV s<sup>-1</sup>. This generally

exhibited good EDLC performance on acidic, alkaline, and neutral electrolytes. Furthermore, it was discovered that higher scan rates reduced their capacitive properties as shown in Figure 7e. Although specific capacitance was decreased at a scan rate of 10 mV s<sup>-1</sup> for all electrolytes, they still maintain their capacitive properties of 61-78% with the order H<sub>2</sub>SO<sub>4</sub>>KOH>Na<sub>2</sub>SO<sub>4</sub>. This was significantly contributed by rich mesoporosity >30%, allowing electrolyte ions to diffuse smoothly when their scan is enhanced. Moreover, the contribution of this aqueous electrolyte modification is also reviewed through the GCD technique. Figure 7f depicts the GCD curves of the MOL750 carbon disc electrodes on different electrolytes. It exhibits a nearly ideal isosceles triangular shape, which indicates the normal EDLC properties of an aqueous electrolyte. However, the KOH electrolyte appeared a GCD curve that contained the greatest ion degradation characterized by a charging time, which is significantly different from the discharging time. This is closely related to oxygen heteroatoms with the potential of the evolution of O<sub>2</sub> and H<sub>2</sub> in aqueous electrolyte systems<sup>65</sup>. It was also discovered that the iR drop was relatively very low, confirming the high conductivity

properties of the MOLs750 precursor as summarized in Table 3.

This phenomenon initiates the high storage capacity of supercapacitors despite their relatively low surface area. Based on the length of the discharge time, the H<sub>2</sub>SO<sub>4</sub> electrolyte exhibited the highest specific capacitance, followed by KOH and Na<sub>2</sub>SO<sub>4</sub> with their capacitive values of 307, 254, and 201 F g<sup>-1</sup>, respectively. This result is in line with the CV analysis, which also revealed almost similar results. To confirm the practical application<sup>66</sup>, the volumetric capacitance was also evaluated as high as 101.61, 684.07, and 66.53 F cm<sup>-3</sup> for different electrolytes H<sub>2</sub>SO<sub>4</sub>, KOH and Na<sub>2</sub>SO<sub>4</sub> respectively. Moreover, modifying the cations and anions in the aqueous electrolyte can affect the electrochemical substance of the supercapacitor, especially at the MOL750 carbon disc electrode. This is due to Ionic mobility, ionic hydrated radius, conductivity, and impact on charge/ion exchange as well as diffusion<sup>67</sup>. The small dehydrated sphere of H<sup>+</sup> cations compared to K<sup>+</sup> and Na<sup>+</sup> allows the charge on the cations to produce the greatest molar ionic conductivity and ionic mobility<sup>68</sup>. These characteristics are needed to obtain fast charge transfer and high ion adsorption at the electrolyte/electrode interface. Similarly, the specification of the cationic radius is also closely related to long-term cycle stability for the MOL750 electrode material, as shown in Figure 7e, where the H<sub>2</sub>SO<sub>4</sub> electrolyte maintained a specific capacitance of 78%. Anion specifications were also studied in their interactions with the MOL750 disc electrode. The results showed that the OH<sup>-</sup> has a narrower hydration ball radius, initiating better conductivity and ionic mobility. Meanwhile, the SO<sub>4</sub><sup>2-</sup> exhibited a larger hydration ball radius, leading to a decrease in the number of ions accessing the pores and lower electrical double sheet formation<sup>69</sup>. Relative to other anions, SO<sub>4</sub><sup>2-</sup> ion has poor conductivity and ion mobility, which makes Na<sub>2</sub>SO<sub>4</sub> electrolytes show the lowest capacitive

properties compared to H<sub>2</sub>SO<sub>4</sub> and KOH electrolytes.

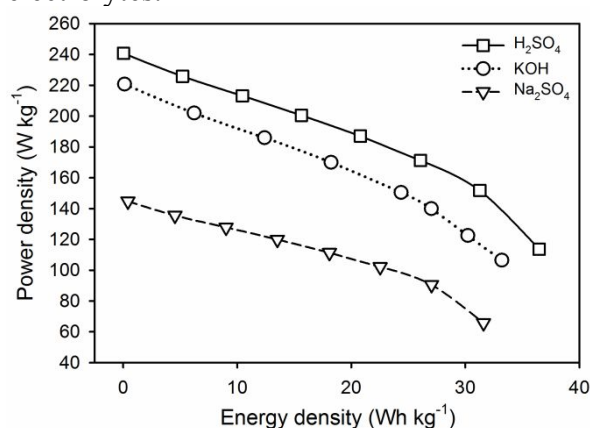

**Figure 8.** Ragone plot of the disc electrode MOLs in different aqueous electrolytes.

For detailed confirmation, the potential of the MOL750 disc electrode in different aqueous electrolytes was reviewed through the Ragone plot as shown in Figure 8. The H<sub>2</sub>SO<sub>4</sub> electrolyte demonstrated the highest performance with an energy density of 36.47 Wh kg<sup>-1</sup> at a power density of 240.73 W kg<sup>-1</sup>. Furthermore, 3D hierarchical pore properties with micro and meso ratio of approximately 3:1 perfectly match the criteria for H<sup>+</sup> anions and SO<sub>4</sub><sup>2-</sup> cations in aqueous electrolyte H<sub>2</sub>SO<sub>4</sub> to possess high energy density in supercapacitor energy storage devices. The alkaline electrolyte KOH also displays an energy density of 33.2047 Wh kg<sup>-1</sup> at a power density of 220.750 W kg<sup>-1</sup>, while the neutral electrolyte Na<sub>2</sub>SO<sub>4</sub> exhibits an energy density of 31.5964 Wh kg<sup>-1</sup> at a power density of 144.7541 W kg<sup>-1</sup>. Moreover, the volumetric energy density is summarized in detail covering 12.07, 10.99, and 10.45 Wh L<sup>-1</sup> for the different electrolytes H<sub>2</sub>SO<sub>4</sub>, KOH and Na<sub>2</sub>SO<sub>4</sub>, which indicated the great potential of MOL750 electrode as practical applications in electrochemical energy storage devices<sup>66,70</sup>. This result is relatively high compared to previous reports, which are summarized in Table 4

**Table 4.** Comparison of electrochemical performance in different carbon sources.

Sources	$S_{\text{BET}}$ ( $\text{m}^2 \text{g}^{-1}$ )	Electrolyte	Electrode design	$C_{\text{sp}}$ ( $\text{F g}^{-1}$ )	E ( $\text{Wh kg}^{-1}$ )	R ( $\Omega$ )	Ref
Wood powders	282.4	6 M KOH	Powder with PTFE	150.1	-	-	25
Feather finger grass flower	637.1	6 M KOH	Powder with PTFE	315	18.75	-	26
Camellia pollen	852	6 M KOH	Powder with PTFE	300	14.3	0.68	27
Sword bean shell	2282	6 M KOH	Powder with PVDF	264	12.5	1.38	44
foxtail grasses	819	6 M KOH	Powder with PTFE	358	18.2	0.8	53
Calcium D-gluconate	539	1 M $\text{H}_2\text{SO}_4$	Powder with PTFE	355	40.5	-	71
Rubber wood sawdust	2820	1 M $\text{H}_2\text{SO}_4$	Powder with PTFE	185	6.93	1.32	72
Kapok flower	1904.1	6 M KOH	Powder with PTFE	286.8	-	0.79	73
Banana leaves	1459	[BMIM][PF6]	Powder with PVP	190	59	-	74
Shallot peel	1182.2	1 M $\text{H}_2\text{SO}_4$	Solid coin without binder	170.12	16.67	0.031	60
MOLs	412.196	1 M $\text{Na}_2\text{SO}_4$	Concolidate disc binder-free	201	31.59	0.031	This work
MOLs	412.196	6 M KOH	Concolidate disc binder-free	254	33.21	0.012	This work
MOLs	412.196	1 M $\text{H}_2\text{SO}_4$	Concolidate disc binder-free	307	36.47	0.006	This work

### 3. CONCLUSION

The green *Moringa oleifera* leaves (MOLs) were converted into a novel consolidated carbon disc-based electrode material through a facile, simple, and environmental approach. The MOLs carbon discs obtained showed a rich 3D hierarchical micro-mesopore structure decorated nanofibers. Furthermore, oxygen heteroatoms (8.06–17.41%) were confirmed with a high carbon content of 88.91%. Furthermore, the electrochemical properties of the carbon disc electrodes of MOLs were evaluated in a symmetric supercapacitor system on different aqueous electrolytes. The MOL750 disc electrode showed the best electrochemical properties with a specific capacitance of  $307 \text{ F g}^{-1}$  on aqueous

electrolyte  $\text{H}_2\text{SO}_4$ . Moreover, the MOLs750 discs can maintain their high performance on aqueous electrolytes KOH and  $\text{Na}_2\text{SO}_4$  with specific capacitances of 254 and  $201 \text{ F g}^{-1}$  in a current density of  $1 \text{ A g}^{-1}$ . The design of binder-free consolidated carbon disc MOLs showed their great potential in producing high capacitive properties, lower internal resistance, high conductivity, despite the relatively low surface area of  $412.196 \text{ m}^2 \text{g}^{-1}$ . Therefore, the MOLs can be developed as a novel approach for producing excellent biomass-based electrode material to enhance the performance of energy storage devices in symmetric supercapacitors.

## 4. EXPERIMENTAL SECTION

### 4.1. Synthesis of porous consolidated carbon disc from MOLs

Green *Moringa oleifera* leaves, hereinafter referred to MOLs, were obtained from a vegetable supplier of Pekanbaru grand-market, separated from the stalks, and cleaned. After the soil and sand elements are removed, the leaves were sundried for 2 days and further oven-dried at 110°C (Oven food warmer 10-110C type FW-35) for 35 hours until the green precursors turned wilted and brittle. The precursor was converted into powder form through pre-carbonization, crusher, and sieving. Pre-carbonization was carried out by preparing 30 g of dried leaves sample in a closed container and placing it in an oven with a temperature of 250°C (KIRIN Oven 10L KBO 100 M) for 2 hours 30 minutes. The sample obtained from the pre-carbonization was inserted into the crusher instrument for 24 hours. The precursor powder from the crusher was sieved using a 250 mesh (CBN test sieve analysis, Cat No. KB-31) to obtain a homogeneous powder, which was chemically activated by zinc chloride impregnated in solution 0.5 mol/L solution. Zinc chloride for analysis was purchased from EMSURE ACS, ISO, Reag. Ph Eur. CAS No. 7646-85-7, EC Number 231-592-0. Subsequently, the dried powder precursor was mixed with ZnCl<sub>2</sub> solution on a Digital Lab Thermostatic Hot-Plate instrument (WiseStir Wisd MSH30D) with a rotation rate of 300 rpm at a temperature of 80°C for 2 hours, while the impregnated samples were dried in an oven at 110°C for 2 days. As a novelty in this study, the carbon powder was converted into a consolidated disc without a binder. For one solid disc sample, 0.7 g of sample powder was pressed through a hydraulic press (Hydraulic Press Bench Type 10T Krisbow KW0500135) at a pressure equal to a mass of 8 tons. 0.7 gr powder samples put in an iron mold resembling a tube with a diameter of 19mm. The iron mold is pressed using a hydraulic press freely equivalent to ±8.0 tons. A total of 15 monolith solid discs were further put

into a vertical furnace (Box Furnace NDT-LB 5, Payun Tech) for high-temperature pyrolysis. The pyrolysis process including carbonization and physical activation was carried out in a single-stage integrated system. This process starts with carbonization in the N<sub>2</sub> gas environment from a temperature of 30 to 600°C with a gas increase rate of 3°C/min. The gas environment is replaced with CO<sub>2</sub> as a physical activation stage to a high different temperature of 650, 750, and 850°C, with an increased rate of 10°C/min. For comparison, a sample was further prepared at 600°C without physical activation. Meanwhile, the 3D porous carbon samples obtained were neutralized by soaking in distilled water and HCl in 1 m/L solution. The immersion water was confirmed to be neutral (pH=7) using a universal pH strip indicator, which was purchased from Merck KGaA, 64271 Darmstadt, Germany. Several labels were made to facilitate the analysis and comparison of materials, as well as electrochemical properties of 3D porous activated carbon-based MOLs. It includes MOL600 as a precursor as well as MOLs650, MOLs750, and MOLs850 from ZnCl<sub>2</sub> impregnation and physical activation with different temperatures of 650, 750, and 850°C.

### 4.2. Material characterizations

The initial porosity properties of solid consolidated disc carbon samples were evaluated through density reduction in high temperatures before and after the pyrolysis process. The density was calculated based on measurements of mass using a Labtronics GM-303 analytical balance, thickness, and diameter of the solid carbon monolith pellets using a QRC5 digital caliper<sup>75</sup>. The porosity properties of carbon MOLs were further evaluated through the N<sub>2</sub> gas adsorption/desorption using Quantachrome version 10.01 at a temperature of 77 K in the P/P<sub>0</sub> relative pressure range of 0.00-0.985. The specific surface area was determined with the Breunauer-Emmet-Teller (BET) technique and the pore size distribution was



calculated using the density functional theory (DFT) approach. Furthermore, the structure and morphology of activated carbon were reviewed through X-ray diffraction (XRD) and scanning electron microscopy (SEM) methods. X-ray diffraction (XRD) was examined in CuK $\alpha$  source ( $\lambda = 1.54051$ ) at an angle range of 10-60° (Malvern Panalytical's X-ray diffractometers), while interlayer spacing was calculated using Bragg's law and lattice parameters ( $L_c$  and  $L_a$ ), which were determined by equation debye-scheerer<sup>36,37</sup>. Similarly, scanning electron microscopy (SEM) was reviewed at a voltage of 15 kV in the energy range 0-20 KeV using JEOL-JSM6510LA instrument. The elemental status of MOLs was also reviewed through the energy dispersive spectroscopy method (JEOL-JSM-6510-LA instrument).

### 4.3. Measurement of electrochemical properties

The working electrodes were prepared in a two-system configuration similar to a binder-free two solid disc carbon MOLs with a loading mass of approximately  $\pm 10.0$  mg. The carbon disc obtained from pyrolysis was polished using P1200 polishing paper to obtain carbon discs with diameters and thicknesses of  $\pm 8$  mm and 0.19 mm, respectively. Here, two carbon disc as electrodes binder-free were prepared in diameter of  $\pm 8.0$  mm with a thickness of 0.19 mm. They were separated by an organic separator made from eggshell membranes. As a support for the electrode, the cell body was made in a rectangular geometry with a hole of  $\pm 9.0$  mm diameter in the middle. The current collector was prepared from 0.2 mm stainless steel and an aqueous electrolyte consisting of 1 M H<sub>2</sub>SO<sub>4</sub>, 6 M KOH, and 1 M Na<sub>2</sub>SO<sub>4</sub> was selected. Subsequently, the electrochemical properties were reviewed using cyclic voltammetry technique with CV, RAD-ER 5841, calibrated error  $\pm 6.0\%$  in a potential window range of 0.0-1.0V at different scanning rates of 1, 2, 5, and 10 mV s<sup>-1</sup>.

Specific capacitance, energy and power densities, and internal resistance were further evaluated through the galvanostatic charge-discharge technique using GCD, RAD-ER 2018 at a constant current density of 1.0 A g<sup>-1</sup> based on the standard equation<sup>76</sup>.

$$C_{sp} = \frac{I \cdot \Delta t}{m \cdot \Delta V}$$

$$E_{sp} = \int IV dt$$

$$P_{sp} = \frac{E_{sp}}{t}$$

Where  $C_{sp}$  (F g<sup>-1</sup>) is specific capacitance,  $I$  (A) is current,  $\Delta t$  (s) is discharge time,  $m$  (g) is mass working electrode,  $\Delta V$  (V) is voltage discharge,  $E_{sp}$  (Wh kg<sup>-1</sup>) is energy density, and  $P_{sp}$  is power density (W kg<sup>-1</sup>).

### ACKNOWLEDGEMENTS

The research was financially supported by second years Project of Word Class Research (WCR) in *Kementerian Pendidikan, Kebudayaan, Riset, dan Teknologi*, Republic of Indonesia with the title "High energy and power densities of supercapacitor for the optimization of electrode supply process". This study also was funded by the collaborative grants between universities, State Islamic University of Sultan Syarif Kasim Riau with contract No. 873/Un.04/L. 1/TL.01/03/2022

### AUTHOR INFORMATION

#### Corresponding Author

Rika Taslim – *Department of Industrial Engineering, State Islamic University of Sultan Syarif Kasim, Riau, Simpang Baru-Tampan Pekanbaru, 28293 Indonesia*; Email: [rikataslim@gmail.com](mailto:rikataslim@gmail.com).

#### Authors

Apriwandi Apriwandi – *Department of Physics, Faculty of Mathematics and Natural Sciences, University of Riau,*

Panam, Pekanbaru, 28293 Indonesia:  
Email: [apriwandi95@gmail.com](mailto:apriwandi95@gmail.com).  
Erman Taer – Department of Physics,  
Faculty of Mathematics and Natural  
Sciences, University of Riau, Panam,  
Pekanbaru, 28293 Indonesia: Email:  
[erman.taer@lecturer.unri.ac.id](mailto:erman.taer@lecturer.unri.ac.id).

## REFERENCES

- (1) International Energy Agency. *Global Energy Review 2021*; 2021.
- (2) BP. *Statistical Review of World Energy*; 2021; Vol. 70.
- (3) BPSTATS. *Review of World Energy Statistical Review of World, 68th Edition*; 2019.
- (4) REN21. *Renewables 2021 Global Status Report*; 2021.
- (5) Burke, A. Ultracapacitors: Why, How, and Where Is the Technology. *J. Power Sources* **2000**, *91* (1), 37–50.
- (6) Li, X.; Zhang, J.; Liu, B.; Su, Z. A Critical Review on the Application and Recent Developments of Post-Modified Biochar in Supercapacitors. *J. Clean. Prod.* **2021**, *310* (April), 127428. <https://doi.org/10.1016/j.jclepro.2021.127428>.
- (7) Zhang, W.; Cheng, R. R.; Bi, H. H.; Lu, Y. H.; Ma, L. B.; He, X. J. A Review of Porous Carbons Produced by Template Methods for Supercapacitor Applications. *Xinxing Tan Cailiao/New Carbon Mater.* **2021**, *36* (1), 69–81. [https://doi.org/10.1016/S1872-5805\(21\)60005-7](https://doi.org/10.1016/S1872-5805(21)60005-7).
- (8) Miller, E. E.; Hua, Y.; Tezel, F. H. Materials for Energy Storage: Review of Electrode Materials and Methods of Increasing Capacitance for Supercapacitors. *J. Energy Storage* **2018**, *20* (February), 30–40. <https://doi.org/10.1016/j.est.2018.08.009>.
- (9) Taer, E.; Taslim, R. Brief Review: Preparation Techniques of Biomass Based Activated Carbon Monolith Electrode for Supercapacitor Applications. In *AIP Conference Proceedings*; 2018; Vol. 1927, pp 020004-1-020004-4.

<https://doi.org/https://doi.org/10.1063/1.5021192>.

- (10) González, A.; Goikolea, E.; Barrena, J. A.; Mysyk, R. Review on Supercapacitors: Technologies and Materials. *Renew. Sustain. Energy Rev.* **2016**, *58*, 1189–1206. <https://doi.org/10.1016/j.rser.2015.12.249>.
- (11) Wang, G.; Zhang, L.; Zhang, J. A Review of Electrode Materials for Electrochemical Supercapacitors. *Chem. Soc. Rev.* **2012**, *41* (2), 797–828. <https://doi.org/10.1039/c1cs15060j>.
- (12) Dessie, Y.; Tadesse, S.; Eswaramoorthy, R.; Abebe, B. Recent Developments in Manganese Oxide Based Nanomaterials with Oxygen Reduction Reaction Functionalities for Energy Conversion and Storage Applications: A Review. *J. Sci. Adv. Mater. Devices* **2019**, *4* (3), 353–369. <https://doi.org/10.1016/j.jsamd.2019.07.001>.
- (13) Soltani, S.; Khanian, N.; Choong, T. S. Y.; Rashid, U. Recent Progress in the Design and Synthesis of Nanofibers with Diverse Synthetic Methodologies: Characterization and Potential Applications. *New J. Chem.* **2020**, *44* (23), 9581–9606. <https://doi.org/10.1039/d0nj01071e>.
- (14) Zhang, Q. Z.; Zhang, D.; Miao, Z. C.; Zhang, X. L.; Chou, S. L. Research Progress in MnO<sub>2</sub>–Carbon Based Supercapacitor Electrode Materials. *Small* **2018**, *14* (24), 1–15. <https://doi.org/10.1002/sml.201702883>.
- (15) Arunachalam, R.; Prataap, R. K. V.; Pavul Raj, R.; Mohan, S.; Vijayakumar, J.; Péter, L.; Al Ahmad, M. Pulse Electrodeposited RuO<sub>2</sub> Electrodes for High-Performance Supercapacitor Applications. *Surf. Eng.* **2019**, *35* (2), 103–109. <https://doi.org/10.1080/02670844.2018.1426408>.
- (16) Li, J.; Hu, H.; Li, H.; Yao, C. Recent Developments in Electrochemical Sensors Based on Nanomaterials for Determining Glucose and Its Byproduct H<sub>2</sub>O<sub>2</sub>. *J. Mater. Sci.* **2017**, *52* (17), 10455–10469. <https://doi.org/10.1007/s10853-017-1221-4>.
- (17) Wang, J.; Zheng, F.; Yu, Y.; Hu, P.;

- 1  
2  
3  
4  
5  
6  
7  
8  
9  
10  
11  
12  
13  
14  
15  
16  
17  
18  
19  
20  
21  
22  
23  
24  
25  
26  
27  
28  
29  
30  
31  
32  
33  
34  
35  
36  
37  
38  
39  
40  
41  
42  
43  
44  
45  
46  
47  
48  
49  
50  
51  
52  
53  
54  
55  
56  
57  
58  
59  
60
- Li, M.; Wang, J.; Fu, J.; Zhen, Q.; Bashir, S.; Liu, J. L. Symmetric Supercapacitors Composed of Ternary Metal Oxides (NiO/V<sub>2</sub>O<sub>5</sub>/MnO<sub>2</sub>) Nanoribbon Electrodes with High Energy Storage Performance. *Chem. Eng. J.* **2021**, *426* (August). <https://doi.org/10.1016/j.cej.2021.131804>.
- (18) Zang, S.; Jiang, J.; An, Y.; Li, Z.; Guo, H.; Sun, Y.; Dou, H.; Zhang, X. A Novel Porous Organic Polymer-Derived Hierarchical Carbon for Supercapacitors with Ultrahigh Energy Density and Durability. *J. Electroanal. Chem.* **2020**, *876*, 114723. <https://doi.org/10.1016/j.jelechem.2020.114723>.
- (19) Majid, S.; Ali, A. S. G.; Cao, W. Q.; Reza, R.; Ge, Q. Biomass-Derived Porous Carbons as Supercapacitor Electrodes-A Review. *New Carbon Mater.* **2021**, *36* (3), 546–572. [https://doi.org/10.1016/S1872-5805\(21\)60038-0](https://doi.org/10.1016/S1872-5805(21)60038-0).
- (20) Saini, S.; Chand, P.; Joshi, A. Biomass Derived Carbon for Supercapacitor Applications: Review. *J. Energy Storage* **2021**, *39* (April), 102646. <https://doi.org/10.1016/j.est.2021.102646>.
- (21) Li, Z.; Guo, D.; Liu, Y.; Wang, H.; Wang, L. Recent Advances and Challenges in Biomass-Derived Porous Carbon Nanomaterials for Supercapacitors. *Chem. Eng. J.* **2020**, *397* (October 2019), 125418. <https://doi.org/10.1016/j.cej.2020.125418>.
- (22) Gopalakrishnan, A.; Badhulika, S. Effect of Self-Doped Heteroatoms on the Performance of Biomass-Derived Carbon for Supercapacitor Applications. *J. Power Sources* **2020**, *480* (August), 228830. <https://doi.org/10.1016/j.jpowsour.2020.228830>.
- (23) Aruchamy, K.; Dharmalingam, K.; Lee, C. W.; Mondal, D.; Sanna Kotrappanavar, N. Creating Ultrahigh Surface Area Functional Carbon from Biomass for High Performance Supercapacitor and Facile Removal of Emerging Pollutants. *Chem. Eng. J.* **2022**, *427* (April 2021), 131477. <https://doi.org/10.1016/j.cej.2021.131477>.
- (24) Zhang, Y.; Wu, C.; Dai, S.; Liu, L.; Zhang, H.; Shen, W.; Sun, W.; Ming Li, C. Rationally Tuning Ratio of Micro- to Mesopores of Biomass-Derived Ultrathin Carbon Sheets toward Supercapacitors with High Energy and High Power Density. *J. Colloid Interface Sci.* **2022**, *606*, 817–825. <https://doi.org/10.1016/j.jcis.2021.08.042>.
- (25) Wang, C.; Wang, H.; Dang, B.; Wang, Z.; Shen, X.; Li, C.; Sun, Q. Ultrahigh Yield of Nitrogen Doped Porous Carbon from Biomass Waste for Supercapacitor. *Renew. Energy* **2020**, *156*, 370–376. <https://doi.org/10.1016/j.renene.2020.04.092>.
- (26) Senthil, R. A.; Yang, V.; Pan, J.; Sun, Y. A Green and Economical Approach to Derive Biomass Porous Carbon from Freely Available Feather Finger Grass Flower for Advanced Symmetric Supercapacitors. *J. Energy Storage* **2021**, *35* (January), 102287. <https://doi.org/10.1016/j.est.2021.102287>.
- (27) Cao, L.; Li, H.; Xu, Z.; Zhang, H.; Ding, L.; Wang, S.; Zhang, G.; Hou, H.; Xu, W.; Yang, F.; Jiang, S. Comparison of the Heteroatoms-Doped Biomass-Derived Carbon Prepared by One-Step Nitrogen-Containing Activator for High Performance Supercapacitor. *Diam. Relat. Mater.* **2021**, *114* (November 2020), 108316. <https://doi.org/10.1016/j.diamond.2021.108316>.
- (28) Wang, L.; Li, X.; Huang, X.; Han, S.; Jiang, J. Activated Green Resources to Synthesize N, P Co-Doped O-Rich Hierarchical Interconnected Porous Carbon for High-Performance Supercapacitors. *J. Alloys Compd.* **2021**, *891*, 161908. <https://doi.org/10.1016/j.jallcom.2021.161908>.
- (29) Apriwandi, A.; Taer, E.; Farma, R.; Setiadi, R. N.; Amiruddin, E. A Facile Approach of Micro-Mesopores Structure Binder-Free Coin/Monolith Solid Design Activated Carbon for Electrode Supercapacitor. *J. Energy Storage* **2021**, *40* (June), 102823. <https://doi.org/10.1016/j.est.2021.102823>.
- (30) Farma, R.; Deraman, M.; Omar, R.;

- 1  
2  
3  
4  
5  
6  
7  
8  
9  
10  
11  
12  
13  
14  
15  
16  
17  
18  
19  
20  
21  
22  
23  
24  
25  
26  
27  
28  
29  
30  
31  
32  
33  
34  
35  
36  
37  
38  
39  
40  
41  
42  
43  
44  
45  
46  
47  
48  
49  
50  
51  
52  
53  
54  
55  
56  
57  
58  
59  
60
- Awitdrus; Ishak, M. M.; Taer, E.; Talib, I. A. Binderless Composite Electrode Monolith from Carbon Nanotube and Biomass Carbon Activated by KOH and CO<sub>2</sub> Gas for Supercapacitor. *AIP Conf. Proc.* **2011**, *1415*, 180–184. <https://doi.org/10.1063/1.3667251>.
- (31) Taer, E.; Apriwandi; Dalimunthe, B. K. L.; Taslim, R. A Rod-like Mesoporous Carbon Derived from Agro-Industrial Cassava Petiole Waste for Supercapacitor Application. *J. Chem. Technol. Biotechnol.* **2021**, *96* (3), 662–671. <https://doi.org/10.1002/jctb.6579>.
- (32) Martínez-Casillas, D. C.; Mascorro-Gutiérrez, I.; Arreola-Ramos, C. E.; Villafán-Vidales, H. I.; Arancibia-Bulnes, C. A.; Ramos-Sánchez, V. H.; Cuentas-Gallegos, A. K. A Sustainable Approach to Produce Activated Carbons from Pecan Nutshell Waste for Environmentally Friendly Supercapacitors. *Carbon N. Y.* **2019**, *148*, 403–412. <https://doi.org/10.1016/j.carbon.2019.04.017>.
- (33) Wei, H.; Wang, H.; Li, A.; Li, H.; Cui, D.; Dong, M.; Lin, J.; Fan, J.; Zhang, J.; Hou, H.; Shi, Y.; Zhou, D.; Guo, Z. Advanced Porous Hierarchical Activated Carbon Derived from Agricultural Wastes toward High Performance Supercapacitors. *J. Alloys Compd.* **2020**, *820*, 153111. <https://doi.org/10.1016/j.jallcom.2019.153111>.
- (34) Achour, A.; Arman, A.; Islam, M.; Zavarian, A. A.; Al-zubaidi, A. B.; Szade, J. Synthesis and Characterization of Porous CaCO<sub>3</sub> Micro/Nano-Particles. *Eur. Phys. J. PLUS* **2017**, *132*, 267. <https://doi.org/10.1140/epjp/i2017-11531-8>.
- (35) Jose, A.; Devi, K. R. S.; Pinheiro, D.; Lakshmi, S. Electrochemical Synthesis, Photodegradation and Antibacterial Properties of PEG Capped Zinc Oxide Nanoparticles. *J. Photochem. Photobiol. B Biol.* **2018**, *187*, 25–34. <https://doi.org/10.1016/j.jphotobiol.2018.07.022>.
- (36) Ayinla, R. T.; Dennis, J. O.; Zaid, H. M.; Sanusi, Y. K.; Usman, F.; Adebayo, L. L. A Review of Technical Advances of Recent Palm Bio-Waste Conversion to Activated Carbon for Energy Storage. *J. Clean. Prod.* **2019**, *229*, 1427–1442. <https://doi.org/10.1016/j.jclepro.2019.04.116>.
- (37) Yaya, A.; Agyei-Tuffour, B.; Dodoo-Arhin, D.; Nyankson, E.; Annan, E.; Konadu, D. S.; Sinayobye, E.; Baryeh, E. a.; Ewels, C. P. Layered Nanomaterials- A Review. *Glob. J. Eng. Des. Technol.* **2012**, *1* (2), 32–41.
- (38) Deraman, M.; Daik, R.; Soltaninejad, S.; Nor, N. S. M.; Awitdrus; Farma, R.; Mamat, N. F.; Basri, N. H.; Othman, M. A. R. A New Empirical Equation for Estimating Specific Surface Area of Supercapacitor Carbon Electrode from X-Ray Diffraction. *Adv. Mater. Res.* **2015**, *1108*, 1–7. <https://doi.org/10.4028/www.scientific.net/AMR.1108.1>.
- (39) Kumar, K.; Saxena, R. K.; Kothari, R.; Suri, D. K.; Kaushik, N. K.; Bohra, J. N. Correlation between Adsorption and X-Ray Diffraction Studies on Viscose Rayon Based Activated Carbon Cloth. *Carbon N. Y.* **1997**, *35* (12), 1842–1844. [https://doi.org/10.1016/S0008-6223\(97\)87258-2](https://doi.org/10.1016/S0008-6223(97)87258-2).
- (40) Riyanto, C.; Kristen, U.; Wacana, S.; Ampri, M. S.; Martono, Y.; Kristen, U.; Wacana, S. Synthesis and Characterization of Nano Activated Carbon from Annatto Peels (Bixa Orellana L.) Viewed from Temperature Activation and Impregnation Ratio of H<sub>3</sub>PO<sub>4</sub>. *J. Sci. data Anal.* **2020**, *1* (1), 44–50. <https://doi.org/10.20885/EKSAKTA.vol1.iss1.art>.
- (41) Salakhum, S.; Yutthalekha, T.; Chareonpanich, M.; Limtrakul, J.; Wattanakit, C. Synthesis of Hierarchical Faujasite Nanosheets from Corn Cob Ash-Derived Nanosilica as Efficient Catalysts for Hydrogenation of Lignin-Derived Alkylphenols. *Microporous Mesoporous Mater.* **2018**, *258*, 141–150. <https://doi.org/10.1016/j.micromeso.2017.09.009>.

- (42) Pourhosseini, S. E. M.; Norouzi, O.; Naderi, H. R. Study of Micro/Macro Ordered Porous Carbon with Olive-Shaped Structure Derived from Cladophora Glomerata Macroalgae as Efficient Working Electrodes of Supercapacitors. *Biomass and Bioenergy* **2017**, *107* (October), 287–298. <https://doi.org/10.1016/j.biombioe.2017.10.025>.
- (43) Li, J.; Zou, Y.; Xiang, C.; Xu, F.; Sun, L.; Li, B.; Zhang, J. Osmanthus Fragrans-Derived N-Doped Porous Carbon for Supercapacitor Applications. *J. Energy Storage* **2021**, *42*, 103017. <https://doi.org/10.1016/j.est.2021.103017>.
- (44) Chen, T.; Luo, L.; Luo, L.; Deng, J.; Wu, X.; Fan, M.; Du, G.; Weigang Zhao. High Energy Density Supercapacitors with Hierarchical Nitrogen-Doped Porous Carbon as Active Material Obtained from Bio-Waste. *Renew. Energy* **2021**, *175*, 760–769. <https://doi.org/10.1016/j.renene.2021.05.006>.
- (45) Liang, Y.; Lu, Y.; Xiao, G.; Zhang, J.; Chi, H.; Dong, Y. Hierarchical Porous Nitrogen-Doped Carbon Microspheres after Thermal Rearrangement as High Performance Electrode Materials for Supercapacitors. *Appl. Surf. Sci.* **2020**, *529*, 147141. <https://doi.org/10.1016/j.apsusc.2020.147141>.
- (46) Bhat, V. S.; Kanagavalli, P.; Sriram, G.; B, R. P.; John, N. S.; Veerapandian, M.; Kurkuri, M.; Hegde, G. Low Cost, Catalyst Free, High Performance Supercapacitors Based on Porous Nano Carbon Derived from Agriculture Waste. *J. Energy Storage* **2020**, *32* (August), 101829. <https://doi.org/10.1016/j.est.2020.101829>.
- (47) Márquez-Montesino, F.; Torres-Figueroa, N.; Lemus-Santana, A.; Trejo, F. Activated Carbon by Potassium Carbonate Activation from Pine Sawdust (*Pinus Montezumae* Lamb.). *Chem. Eng. Technol.* **2020**, *43* (9), 1716–1725. <https://doi.org/10.1002/ceat.202000051>.
- (48) Zhang, Y.; Yu, S.; Lou, G.; Shen, Y.; Chen, H.; Shen, Z.; Zhao, S.; Zhang, J.; Chai, S.; Zou, Q. Review of Macroporous Materials as Electrochemical Supercapacitor Electrodes. *J. Mater. Sci.* **2017**, *52* (19), 11201–11228. <https://doi.org/10.1007/s10853-017-0955-3>.
- (49) Boujibar, O.; Ghamouss, F.; Ghosh, A.; Achak, O.; Chafik, T. Efficient CO<sub>2</sub> Capture by Ultra-High Microporous Activated Carbon Made from Natural Coal. *Chem. Eng. Technol.* **2021**, *44* (1), 148–155. <https://doi.org/10.1002/ceat.202000138>.
- (50) Yakaboylu, G. A.; Jiang, C.; Yumak, T.; Zondlo, J. W.; Wang, J.; Sabolsky, E. M. Engineered Hierarchical Porous Carbons for Supercapacitor Applications through Chemical Pretreatment and Activation of Biomass Precursors. *Renew. Energy* **2021**, *163*, 276–287. <https://doi.org/10.1016/j.renene.2020.08.092>.
- (51) Sing, K. S. W. Reporting Physisorption Data for Gas/Solid Systems with Special Reference to the Determination of Surface Area and Porosity. *Pure Appl. Chem.* **1982**, *54* (11), 2201–2218. <https://doi.org/10.1351/pac198254112201>.
- (52) Zheng, G.; Huang, Z.; Liu, Z. Cooperative Utilization of Beet Pulp and Industrial Waste Fly Ash to Produce N/P/O Self-Co-Doped Hierarchically Porous Carbons for High-Performance Supercapacitors. *J. Power Sources* **2021**, *482* (September 2020), 228935. <https://doi.org/10.1016/j.jpowsour.2020.228935>.
- (53) Liang, X.; Liu, R.; Wu, X. Biomass Waste Derived Functionalized Hierarchical Porous Carbon with High Gravimetric and Volumetric Capacitances for Supercapacitors. *Microporous Mesoporous Mater.* **2021**, *310* (September 2020), 110659. <https://doi.org/10.1016/j.micromeso.2020.110659>.
- (54) Zhang, X.; Liu, B.; Yan, X.; Zhao, X.; Zhang, Y.; Wei, Y.; Cao, Q. Design and Structure Optimization of 3D Porous Graphitic Carbon Nanosheets for High-Performance Supercapacitor. *Microporous Mesoporous Mater.* **2020**, *309* (August), 110580.

1  
2  
3  
4  
5  
6  
7  
8  
9  
10  
11  
12  
13  
14  
15  
16  
17  
18  
19  
20  
21  
22  
23  
24  
25  
26  
27  
28  
29  
30  
31  
32  
33  
34  
35  
36  
37  
38  
39  
40  
41  
42  
43  
44  
45  
46  
47  
48  
49  
50  
51  
52  
53  
54  
55  
56  
57  
58  
59  
60

<https://doi.org/10.1016/j.micromeso.2020.110580>.

(55) Wang, Y.; Qiao, M.; Mamat, X. Nitrogen-Doped Macro-Meso-Micro Hierarchical Ordered Porous Carbon Derived from ZIF-8 for Boosting Supercapacitor Performance. *Appl. Surf. Sci.* **2021**, *540* (P1), 148352. <https://doi.org/10.1016/j.apsusc.2020.148352>.

(56) Wu, J.; Xia, M.; Zhang, X.; Chen, Y.; Sun, F.; Wang, X.; Yang, H.; Chen, H. Hierarchical Porous Carbon Derived from Wood Tar Using Crab as the Template: Performance on Supercapacitor. *J. Power Sources* **2020**, *455* (February), 227982. <https://doi.org/10.1016/j.jpowsour.2020.227982>.

(57) Yang, V.; Senthil, R. A.; Pan, J.; Kumar, T. R.; Sun, Y.; Liu, X. Hierarchical Porous Carbon Derived from Jujube Fruits as Sustainable and Ultrahigh Capacitance Material for Advanced Supercapacitors. *J. Colloid Interface Sci.* **2020**, *579*, 347–356. <https://doi.org/10.1016/j.jcis.2020.06.080>.

(58) Huo, S.; Zhang, X.; Liang, B.; Zhao, Y.; Li, K. Synthesis of Interconnected Hierarchically Porous Carbon Networks with Excellent Diffusion Ability Based on NaNO<sub>3</sub> Crystal-Assisted Strategy for High Performance Supercapacitors. *J. Power Sources* **2020**, *450* (December 2019), 227612. <https://doi.org/10.1016/j.jpowsour.2019.227612>.

(59) Sekhon, S. S.; Park, J. S. Biomass-Derived N-Doped Porous Carbon Nanosheets for Energy Technologies. *Chem. Eng. J.* **2021**, *425* (December 2020), 129017. <https://doi.org/10.1016/j.cej.2021.129017>.

(60) Taer, E.; Apriwandi, A.; Rama, D. Solid Coin-like Design Activated Carbon Nanospheres Derived from Shallot Peel Precursor for Boosting Supercapacitor Performance. *J. Mater. Res. Technol.* **2021**, *15*, 1732–1741. <https://doi.org/10.1016/j.jmrt.2021.09.025>.

(61) Hor, A. A.; Hashmi, S. A. Optimization of Hierarchical Porous Carbon

Derived from a Biomass Pollen-Cone as High-Performance Electrodes for Supercapacitors. *Electrochim. Acta* **2020**, *356*, 136826. <https://doi.org/10.1016/j.electacta.2020.136826>.

(62) Liu, H.; Liu, R.; Xu, C.; Ren, Y.; Tang, D.; Zhang, C.; Li, F.; Wei, X.; Zhang, R. Oxygen–Nitrogen–Sulfur Self-Doping Hierarchical Porous Carbon Derived from Lotus Leaves for High-Performance Supercapacitor Electrodes. *J. Power Sources* **2020**, *479*, 228799. <https://doi.org/10.1016/j.jpowsour.2020.228799>.

(63) Zhang, Q.; Han, K.; Li, S.; Li, M.; Li, J.; Ren, K. Synthesis of Garlic Skin-Derived 3D Hierarchical Porous Carbon for High-Performance Supercapacitors. *Nanoscale* **2018**, *10* (5), 2427–2437. <https://doi.org/10.1039/c7nr07158b>.

(64) Liu, H.; Gao, F.; Fan, Q.; Wei, C.; Ma, C.; Shi, J. Preparation of Novel 3D Hierarchical Porous Carbon Membrane as Flexible Free-Standing Electrode for Supercapacitors. *J. Electroanal. Chem.* **2020**, *873*, 114409. <https://doi.org/10.1016/j.jelechem.2020.114409>.

(65) Taer, E.; Taslim, R.; Apriwandi, A. Ultrahigh Capacitive Supercapacitor Derived from Self-Oxygen Doped Biomass-Based 3D Porous Carbon Sources. *ChemNanoMat* **2022**, *8* (2), e202100388. <https://doi.org/10.1002/cnma.202100388>.

(66) Wang, Q.; Yan, J.; Fan, Z. Carbon Materials for High Volumetric Performance Supercapacitors: Design, Progress, Challenges and Opportunities. *Energy Environ. Sci.* **2016**, *9*, 729–762. <https://doi.org/10.1039/C5EE03109E>.

(67) Sajjad, M.; Khan, M. I.; Cheng, F.; Lu, W. A Review on Selection Criteria of Aqueous Electrolytes Performance Evaluation for Advanced Asymmetric Supercapacitors. *J. Energy Storage* **2021**, *40*, 102729. <https://doi.org/10.1016/j.est.2021.102729>.

(68) Aldama, I.; Barranco, V.; Kunowsky, M.; Ibañez, J.; Rojo, J. M.

Contribution of Cations and Anions of Aqueous Electrolytes to the Charge Stored at the Electric Electrolyte/Electrode Interface of Carbon-Based Supercapacitors. *J. Phys. Chem. C* **2017**, *121* (22), 12053–12062.

<https://doi.org/10.1021/acs.jpcc.7b03003>.

(69) Selvaraj, A. R.; Muthusamy, A.; Inho-Cho; Kim, H. J.; Senthil, K.; Prabakar, K. Ultrahigh Surface Area Biomass Derived 3D Hierarchical Porous Carbon Nanosheet Electrodes for High Energy Density Supercapacitors. *Carbon N. Y.* **2021**, *174*, 463–474.

<https://doi.org/10.1016/j.carbon.2020.12.052>

(70) Gogotsi, Y.; Simon, P. True Performance Metrics in Electrochemical Energy Storage. *Science (80-. )*. **2011**, *334* (November), 917–918.

<https://doi.org/10.1126/science.1213003>.

(71) Chen, C.; Zhao, M.; Cai, Y.; Zhao, G.; Xie, Y.; Zhang, L.; Zhu, G.; Pan, L. Scalable Synthesis of Strutted Nitrogen Doped Hierarchical Porous Carbon Nanosheets for Supercapacitors with Both High Gravimetric and Volumetric Performances. *Carbon N. Y.* **2021**, *179*, 458–468.

<https://doi.org/10.1016/j.carbon.2021.04.062>

(72) Sangtong, N.; Chaisuwan, T.; Wongkasemjit, S.; Ishida, H.; Redpradit, W.; Seneesrisakul, K.; Thubsuang, U. Ultrahigh-Surface-Area Activated Biocarbon Based on Biomass Residue as a Supercapacitor Electrode Material: Tuning Pore Structure Using Alkalis with Different Atom Sizes. *Microporous Mesoporous Mater.* **2021**, *326* (June), 111383. <https://doi.org/10.1016/j.micromeso.2021.111383>.

(73) Zheng, L. H.; Chen, M. H.; Liang, S. X.; Lü, Q. F. Oxygen-Rich Hierarchical Porous Carbon Derived from Biomass Waste-Kapok Flower for Supercapacitor Electrode. *Diam. Relat. Mater.* **2021**, *113* (January), 108267. <https://doi.org/10.1016/j.diamond.2021.108267>.

(74) Roy, C. K.; Shah, S. S.; Reaz, A. H.; Sultana, S.; Chowdhury, A. N.; Firoz, S. H.; Zahir, M. H.; Ahmed Qasem, M. A.; Aziz, M. A. Preparation of Hierarchical Porous Activated Carbon from Banana Leaves for High-Performance Supercapacitor: Effect of Type of Electrolytes on Performance. *Chem. - An Asian J.* **2021**, *16* (4), 296–308. <https://doi.org/10.1002/asia.202001342>.

(75) Taer, E.; Natalia, K.; Apriwandi, A.; Taslim, R.; Agustino, A.; Farma, R. The Synthesis of Activated Carbon Nano Fiber Electrode Made from Acacia Leaves (*Acacia Mangium Wild*) as Supercapacitors. *Adv. Nat. Sci. Nanosci. Nanotechnol.* **2020**, *11* (2), 25007. <https://doi.org/10.1088/2043-6254/ab8b60>.

(76) Yao, Y.; Chen, X.; Yu, N.; Wei, F.; Feng, H. Preparation and Supercapacitive Performance of Lead Dioxide Electrodes with Three-Dimensional Porous Structure. *Russ. J. Electrochem.* **2018**, *54* (7), 585–591.

<https://doi.org/10.1134/S1023193518070078>.

---

**Taslim, Rika ao-2022-04301k.R2 - Manuscript Accepted 29-Sep-2022**

1 message

ACS Omega &lt;onbehalf@manuscriptcentral.com&gt;

Thu, Sep 29, 2022 at 4:18 PM

Reply-To: guo-office@omega.acs.org

To: rikataslim@gmail.com

29-Sep-2022

Journal: ACS Omega

Manuscript ID: ao-2022-04301k.R2

Title: "Novel &lt;i&gt;Moringa oleifera&lt;/i&gt; leaves 3D porous carbon-based electrode material as high performance EDLC supercapacitor"

Author(s): Taslim, Rika; Apriwandi, Apriwandi; Taer, Erman

Manuscript Status: Accept

Dear Dr. Taslim:

We are pleased to inform you that your manuscript has been accepted for publication in ACS Omega.

You will soon receive an email invitation from the ACS Journal Publishing Staff that contains a link to the online Journal Publishing Agreement. Please sign and submit the journal publishing agreement within 48 hours.

You will be contacted in approximately a week by the ACS Journal Publishing Staff regarding the proofs for your manuscript. Although production of your manuscript will start immediately, your manuscript will not be published until you pay the Article Publishing Charges, <https://acsopscience.org/open-access/pricing/>. You may qualify for discounts. You will also be contacted shortly with information on how to pay your publishing charges. Article Publishing Charges are waived for invited Editorials and Perspectives.

After you submit corrections for your proofs and pay the article publishing charges, your manuscript will be published on the Web in approximately 48 hours. In view of this fast publication time, it is important to review your proofs carefully. Once a manuscript appears on the Web, it is considered published. Any change to the manuscript once it appears on the Web will need to be submitted to the journal office as a separate Addition & Correction manuscript via the ACS Paragon Plus environment.

Once your paper is published, you can track downloads and citations of your work by logging into the ACS Publishing Center (<https://pubs.acs.org/publish/dashboard>) and selecting "Published."

Sincerely,

Prof. Shaojun Guo

Associate Editor

ACS Omega

Email: [guo-office@omega.acs.org](mailto:guo-office@omega.acs.org)

-----  
PLEASE NOTE: This email message, including any attachments, contains confidential information related to peer review and is intended solely for the personal use of the recipient(s) named above. No part of this communication or any related attachments may be shared with or disclosed to any third party or organization without the explicit prior written consent of the journal Editor and ACS. If the reader of this message is not the intended recipient or is not responsible for delivering it to the intended recipient, you have received this communication in error. Please notify the sender immediately by e-mail, and delete the original message.

As an author or reviewer for ACS Publications, we may send you communications about related journals, topics or products and services from the American Chemical Society. Please email us at [pubs-comms-unsub@acs.org](mailto:pubs-comms-unsub@acs.org) if you do not want to receive these. Note, you will still receive updates about your manuscripts, reviews, or future invitations to review.

Thank you.